

GoudsmIT NdFeB Grade System



This document provides magnetic, physical and mechanical data of all the Neodymium magnets GoudsmIT sells and which are relevant for the selection of magnets and design of magnetic systems.

Grade Quality Code	Coercivity Description	Maximum Operating Temperature
N	Normal coercivity	80°C
M	Medium coercivity	100°C
H	High coercivity	120°C
SH	Super- H igh coercivity	150°C
UH	Ultra- H igh coercivity	180°C
EH	Extremely H igh coercivity	200°C
AH	Absolutely H igh coercivity	220°C
VH	Virtually H igh coercivity	250°C


N- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N35	1170	860	955	259	-0.12	-0.78	80
N38	1220	860	955	281	-0.12	-0.78	80
N40	1250	860	955	300	-0.12	-0.78	80
N42	1280	860	955	318	-0.12	-0.78	80
N45	1320	860	955	338	-0.12	-0.78	80
N48	1370	836	955	358	-0.12	-0.78	80
N50	1390	836	955	376	-0.12	-0.78	80
N52	1420	836	876	390	-0.12	-0.78	80
N54	1440	836	875	406	-0.12	-0.78	70
N55	1460	716	876	414	-0.12	-0.62	80

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N35 – Anisotropic Sintered

Demagnetisation Curve N35

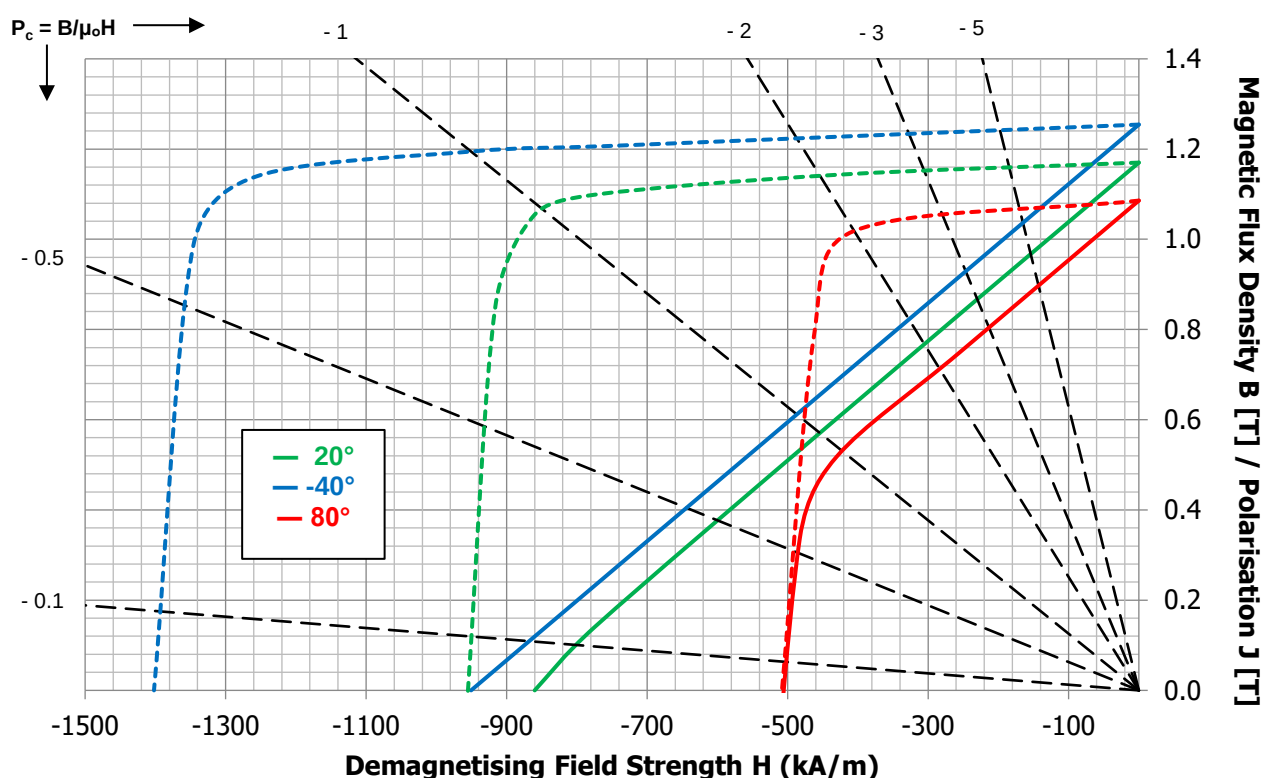

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.17	T
H_{cB}	min	860	kA/m
H_{cJ}	min	955	kA/m
$(BH)_{ma}$	min	259	kJ/m^3
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m^3
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38 – Anisotropic Sintered

Demagnetisation Curve N38

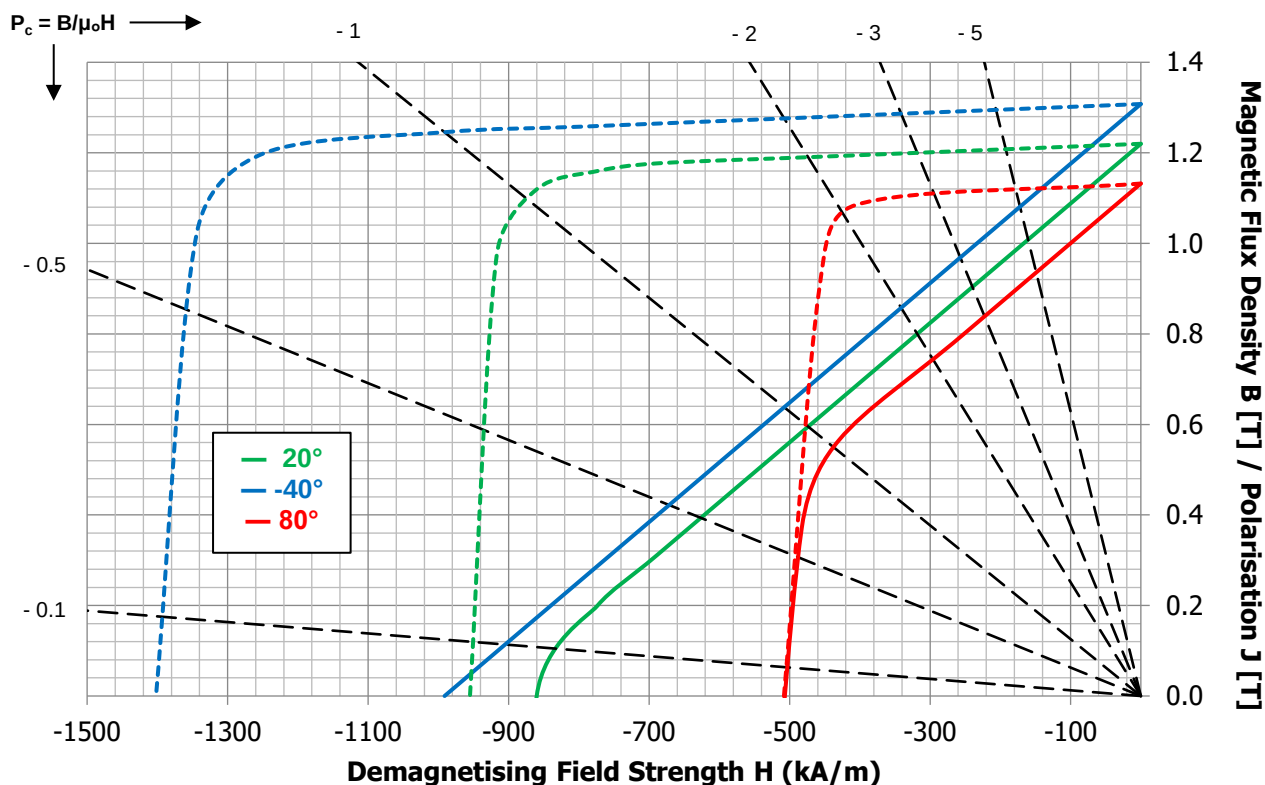

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.22	T
H_{cB}	min	860	kA/m
H_{cJ}	min	955	kA/m
$(BH)_{ma}$	min	281	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40 – Anisotropic Sintered

Demagnetisation Curve N40

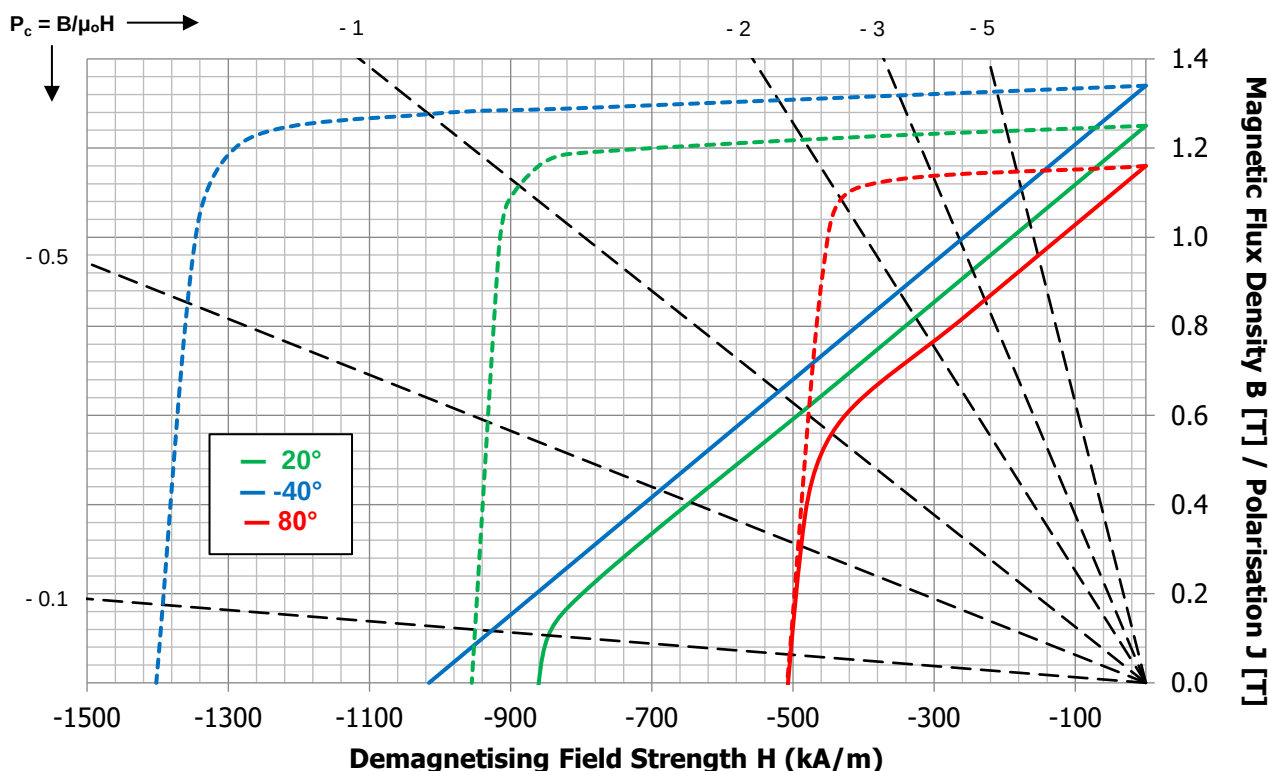

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.25	T
H_{cB}	min	860	kA/m
H_{cJ}	min	955	kA/m
$(BH)_{ma}$	min	300	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42 – Anisotropic Sintered

Demagnetisation Curve N42

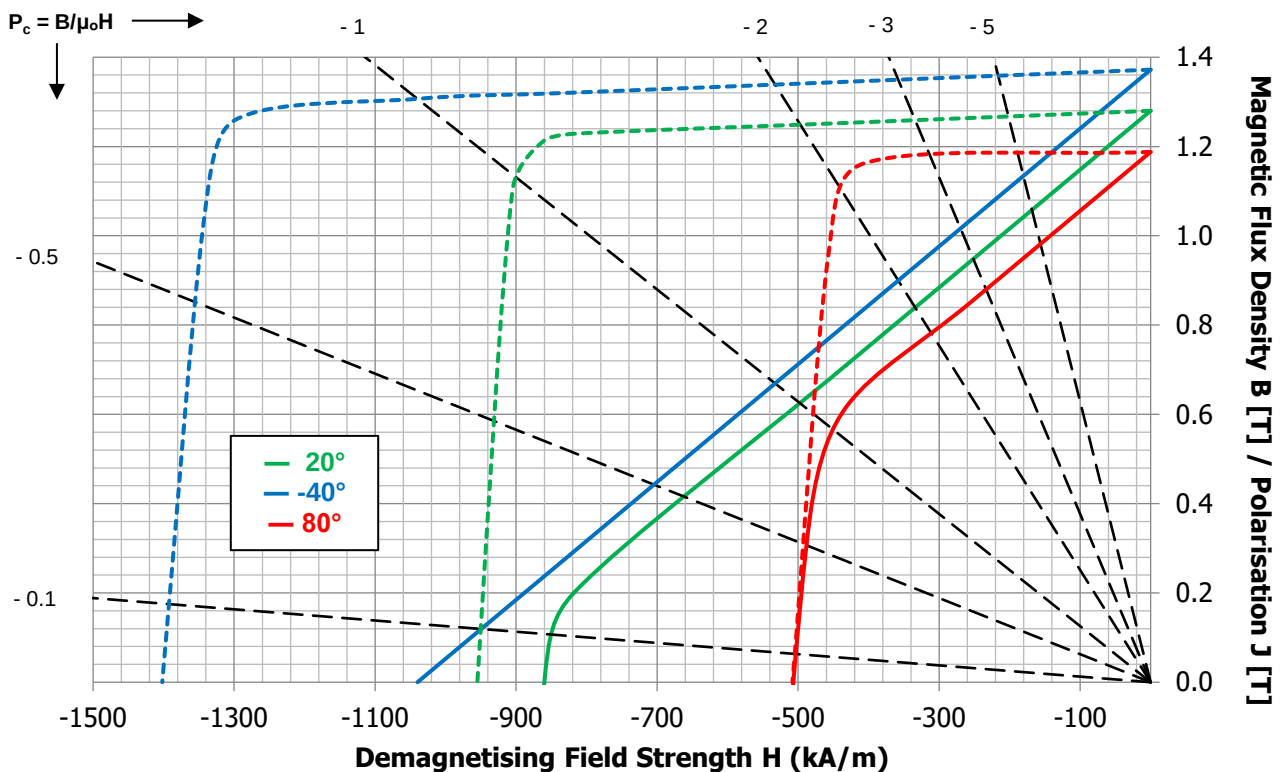

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.28	T
H_{cB}	min	860	kA/m
H_{cJ}	min	955	kA/m
(BH)_{ma}	min	318	kJ/m ³
α(B_r)	min typ	-0.12	%/°C
β(H_{cJ})	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	μΩm
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K
Coefficient of linear thermal expansion, ⊥ DOM*	typ	-3 - 0	10 ⁻⁶ /K

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45 – Anisotropic Sintered

Demagnetisation Curve N45

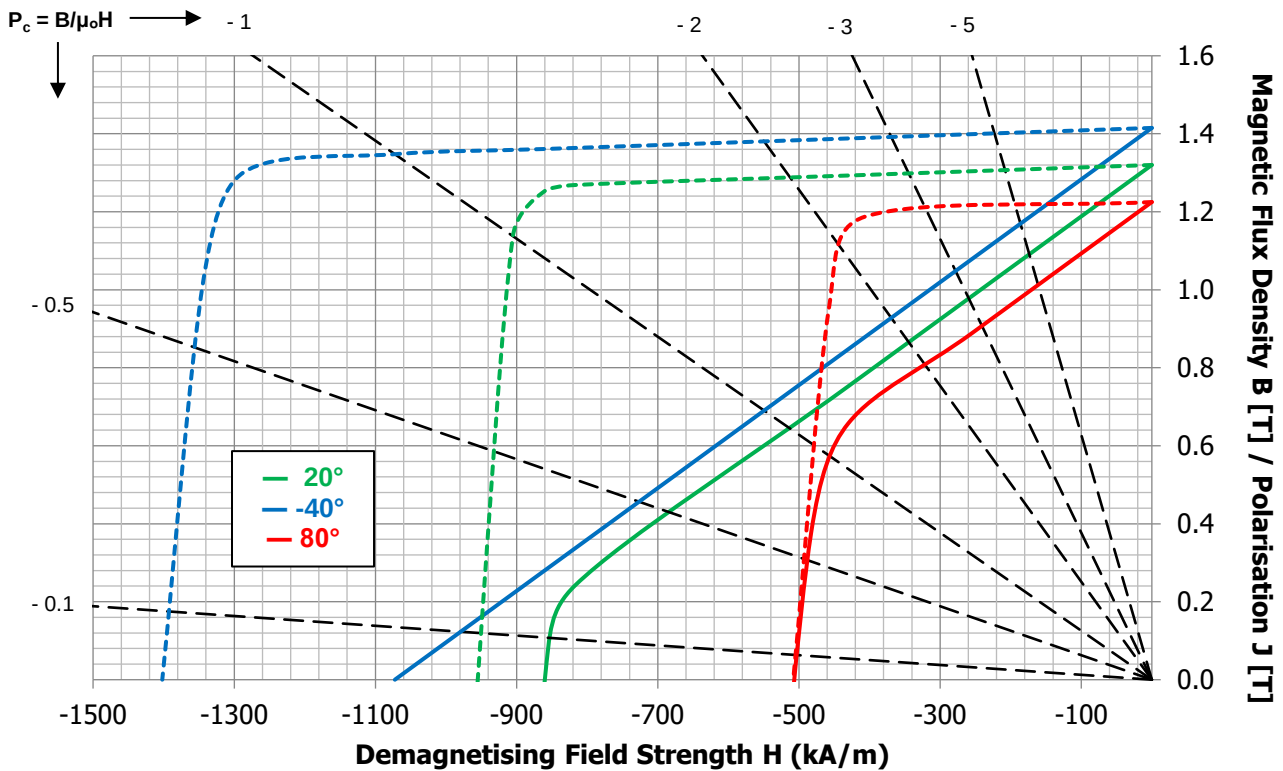

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.32	T	
H_{cB}	min	860	kA/m	
H_{cJ}	min	955	kA/m	
$(BH)_{ma}$	min	338	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.78	%/°C	
T_{max}		80	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N48 – Anisotropic Sintered

Demagnetisation Curve N48

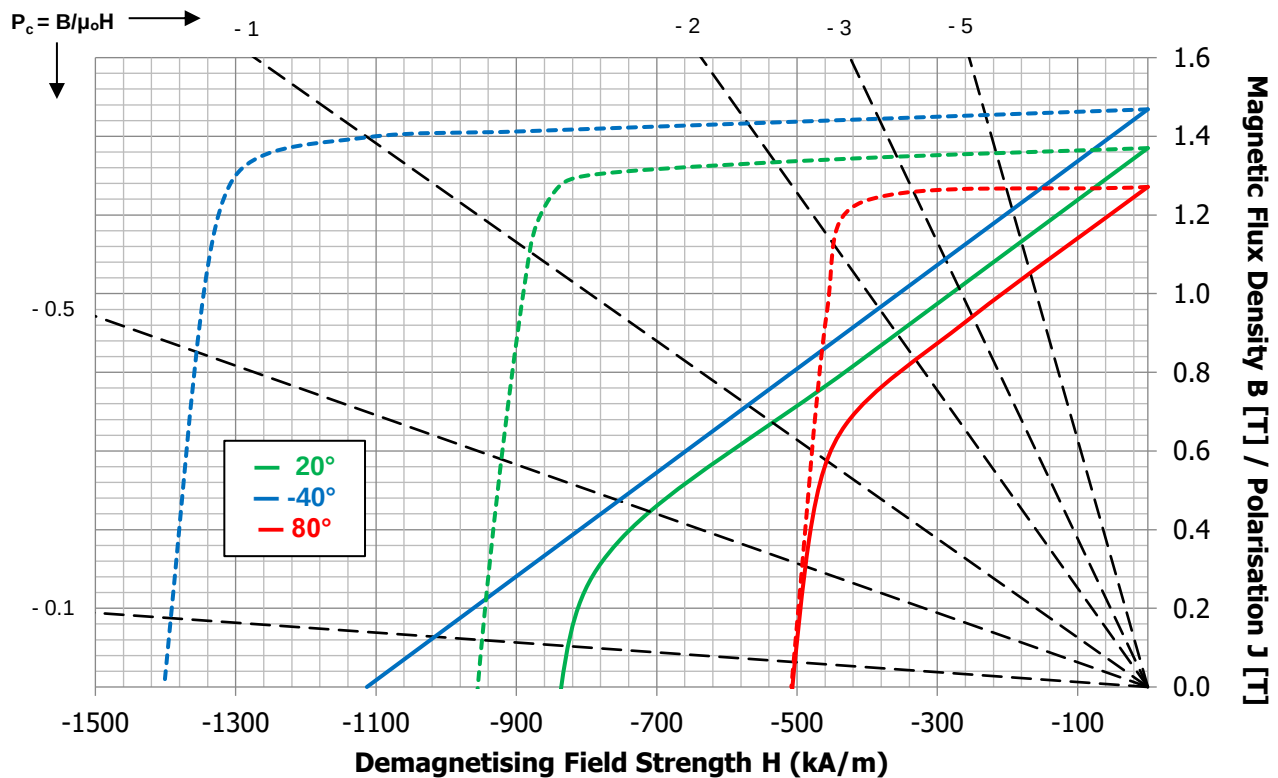

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic properties @20°C				
B_r	min	1.37	T	
H_{cB}	min	836	kA/m	
H_{cJ}	min	955	kA/m	
$(BH)_{ma}$	min	358	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.78	%/°C	
T_{max}		80	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N50 – Anisotropic Sintered

Demagnetisation Curve N50

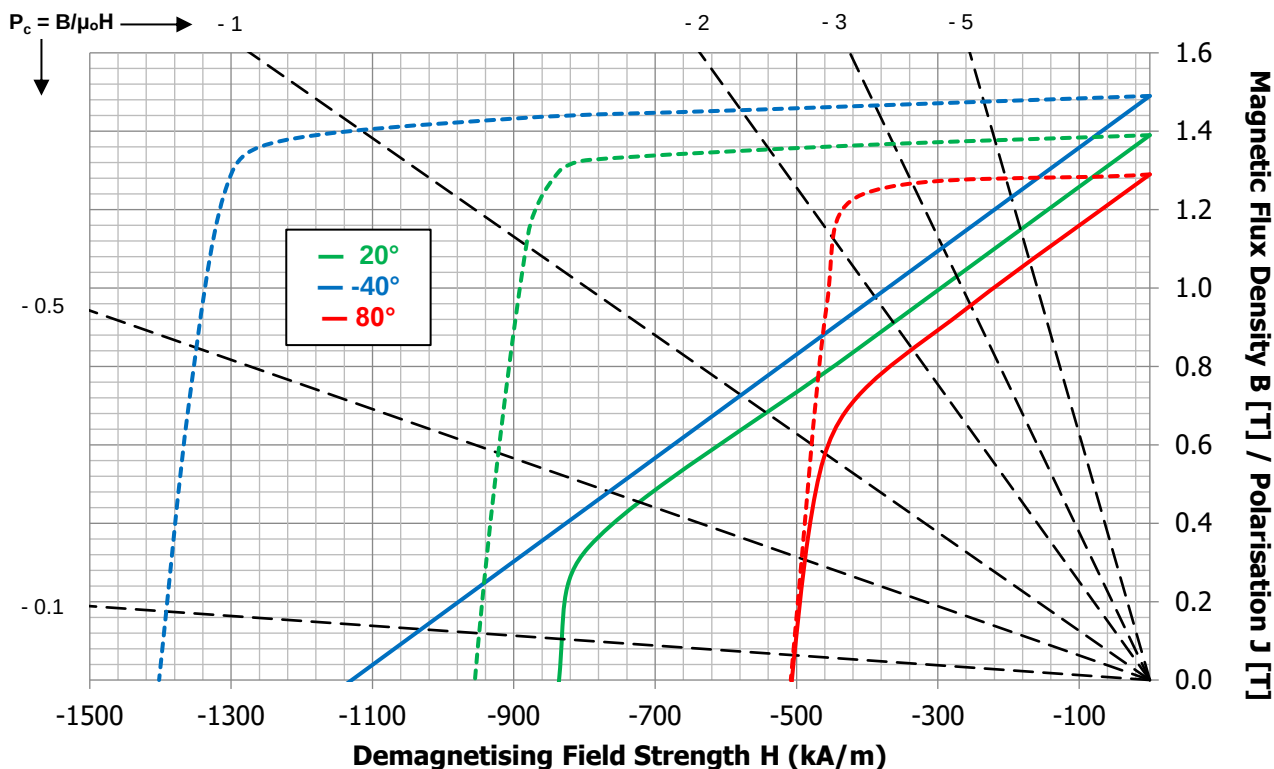

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.39	T
H_{cB}	min	836	kA/m
H_{cJ}	min	955	kA/m
$(BH)_{ma}$	min	376	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N52 – Anisotropic Sintered

Demagnetisation Curve N52

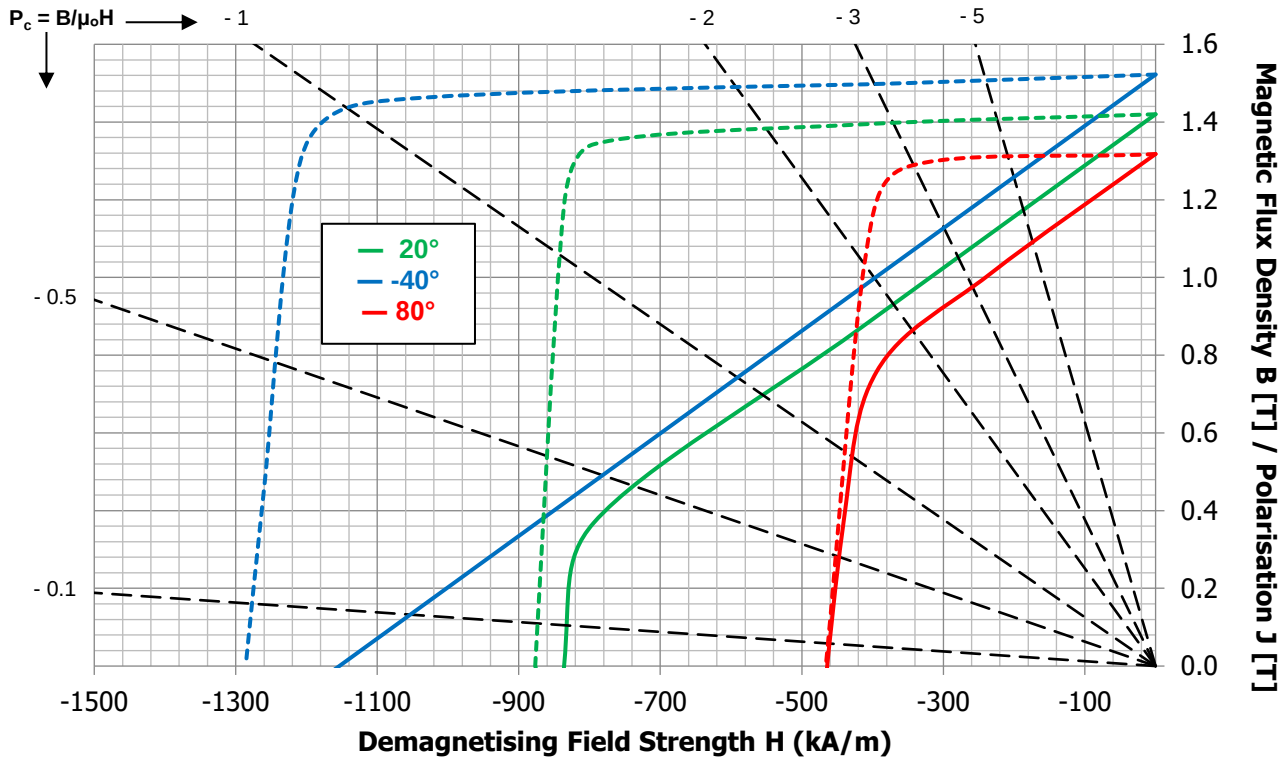

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.42	T
H_{cB}	min	836	kA/m
H_{cJ}	min	876	kA/m
$(BH)_{ma}$	min	390	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.78	%/°C
T_{max}		80	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N54 – Anisotropic Sintered

Demagnetisation Curve N54

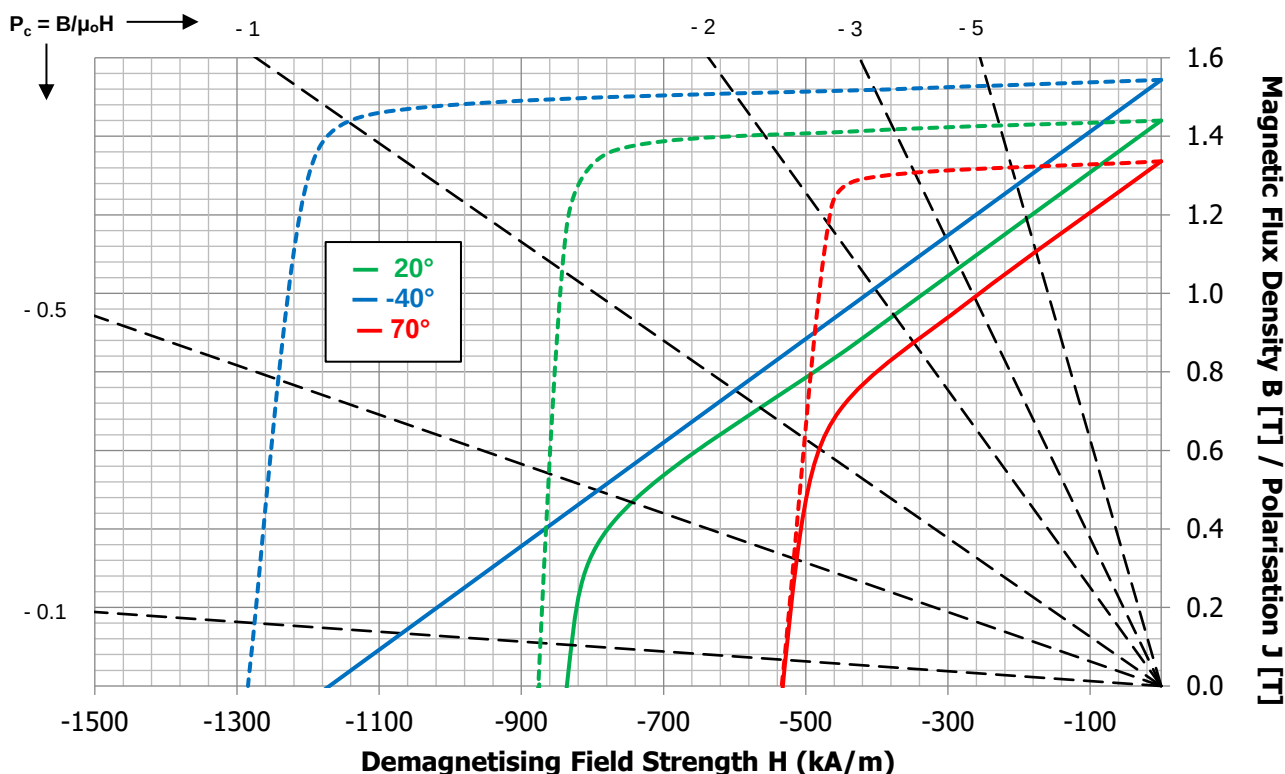

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.44	T	
H_{cB}	min	836	kA/m	
H_{cJ}	min	875	kA/m	
$(BH)_{ma}$	min	406	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.78	%/°C	
T_{max}		70	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N55 – Anisotropic Sintered

Demagnetisation Curve N55

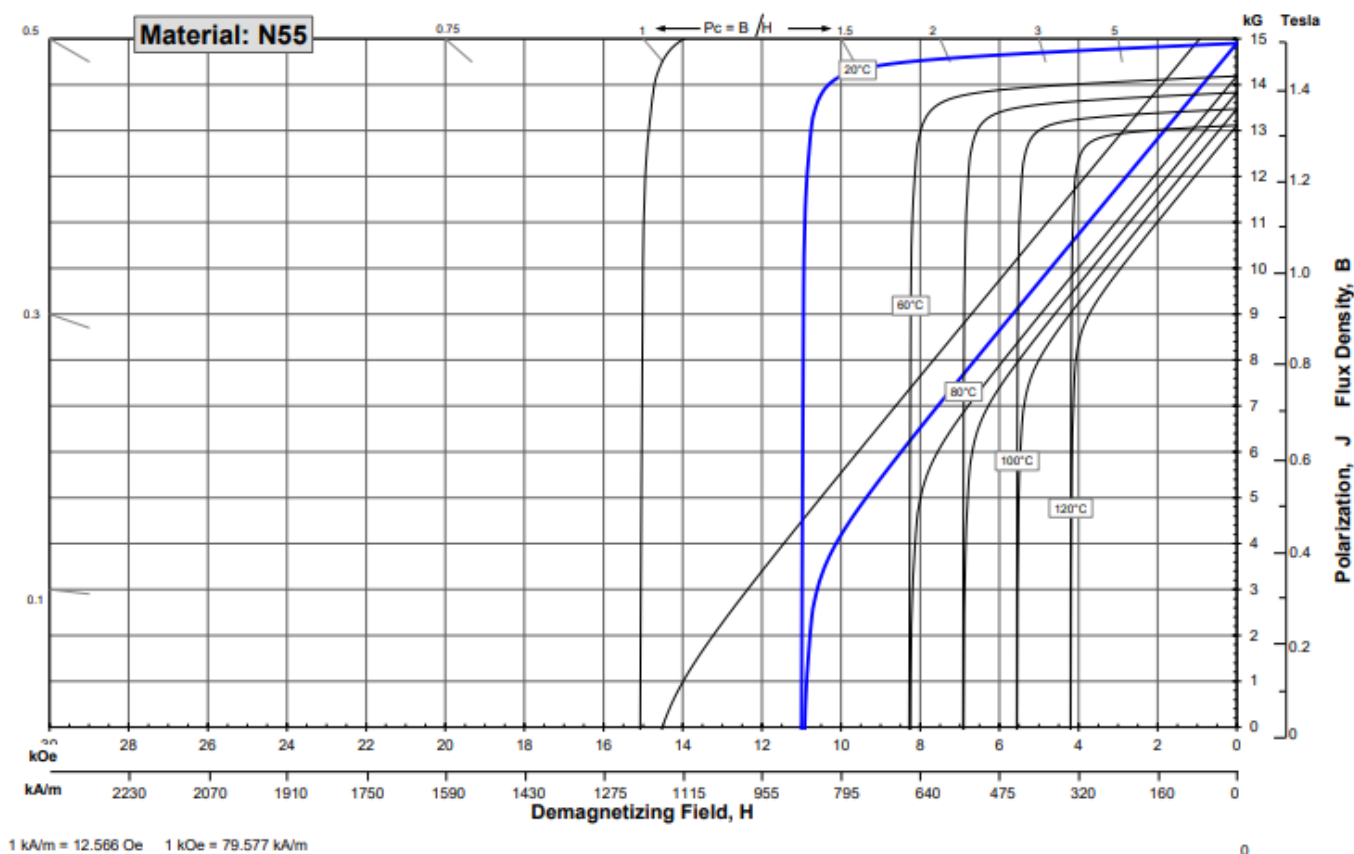

The material data and demagnetization curves shown above represent typical properties that may vary due to product shape and size. Demagnetisation curves show nominal B_r and minimum H_{ci} . On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C			
B_r	min	1460	mT
H_{cB}	min	716	kA/m
H_{cJ}	min	876	kA/m
$(BH)_{ma}$	min	414	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		80	°C

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation


M- Grades

GoudsmIT Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N35M	1170	868	1114	259	-0.12	-0.72	100
N38M	1220	899	1114	281	-0.12	-0.72	100
N40M	1250	923	1114	300	-0.12	-0.72	100
N42M	1280	955	1114	318	-0.12	-0.72	100
N45M	1320	971	1114	338	-0.12	-0.72	100
N48M	1360	995	1114	358	-0.12	-0.72	100
N50M	1390	1035	1114	376	-0.12	-0.72	100
N52M	1420	1056	1114	390	-0.12	-0.72	100

These are the most common grades. Please contact us for questions on other grades available at GoudsmIT.

Technical Datasheet: Neodymium N35M – Anisotropic Sintered

Demagnetisation Curve N35M

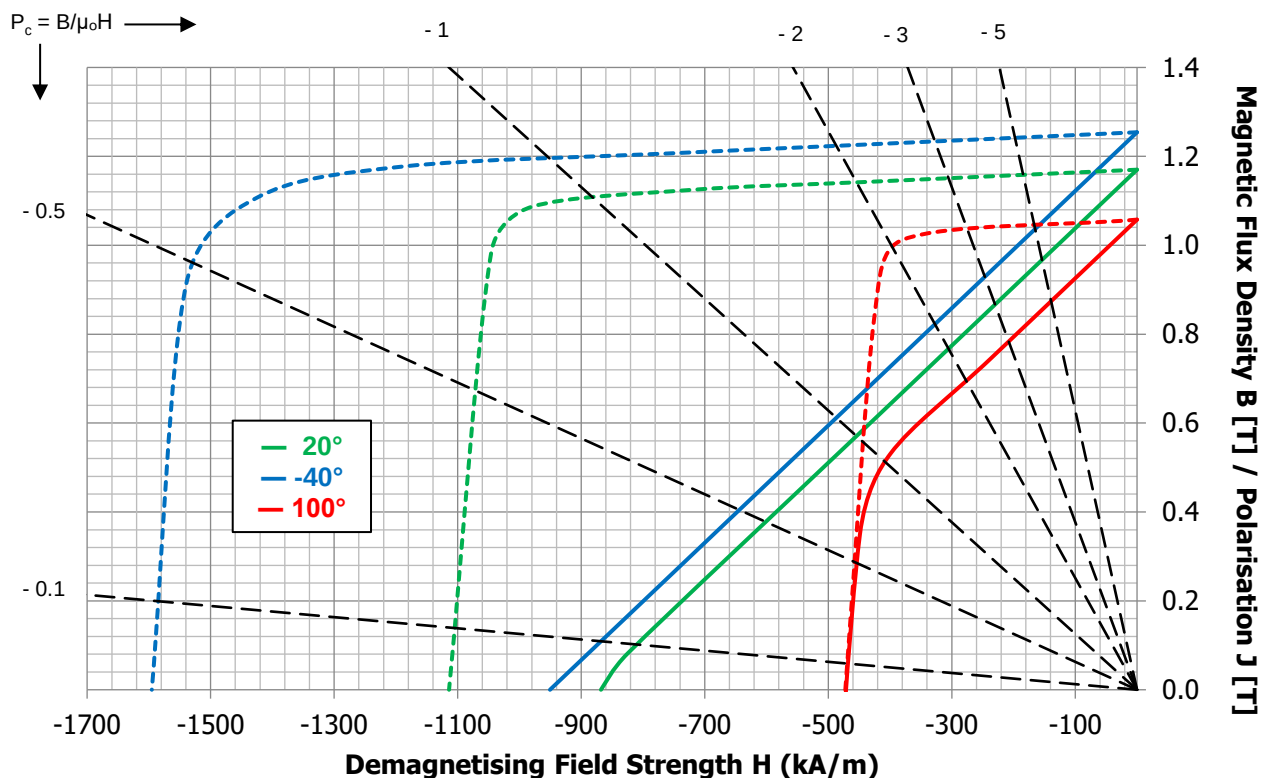

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.17	T	
H_{cB}	min	868	kA/m	
H_{cJ}	min	1114	kA/m	
$(BH)_{ma}$	min	259	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.72	%/°C	
T_{max}		100	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38M – Anisotropic Sintered

Demagnetisation Curve N38M

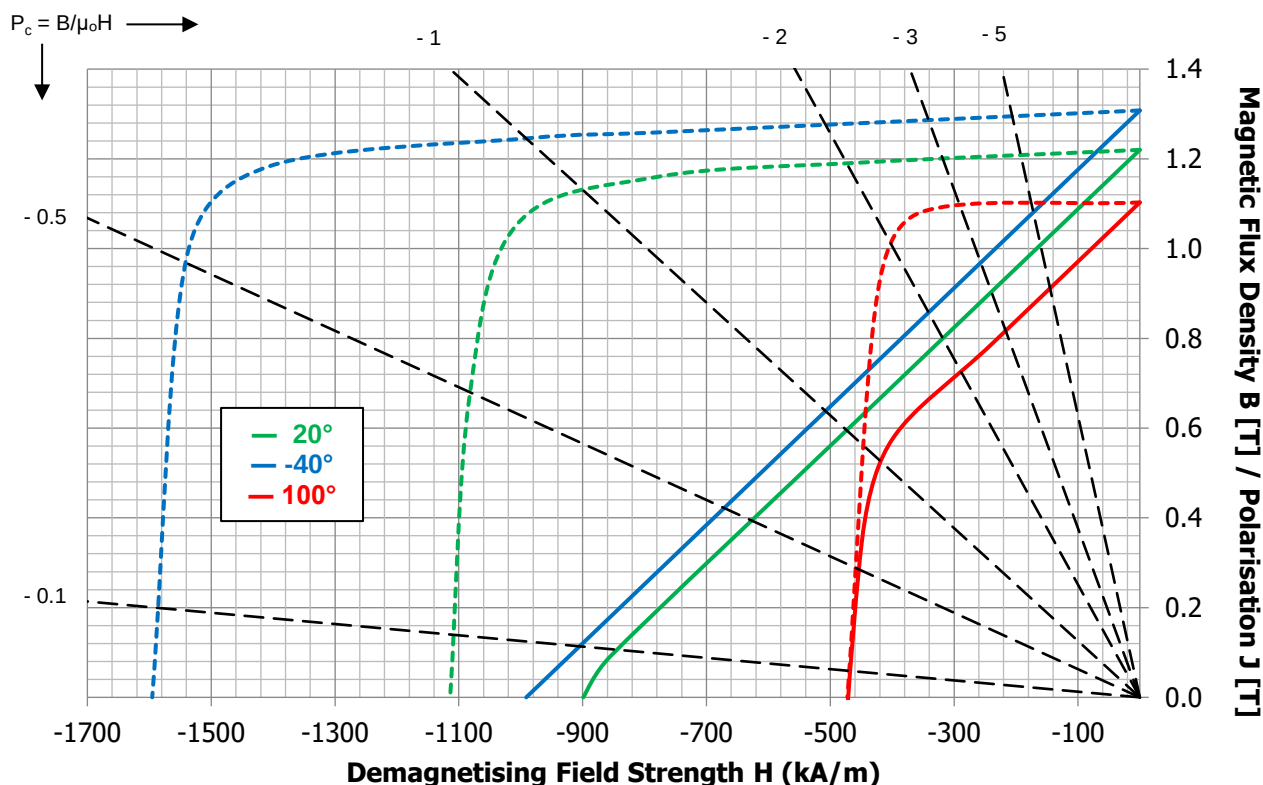

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic properties @20°C			
B_r	min	1.22	T
H_{cB}	min	899	kA/m
H_{cJ}	min	1114	kA/m
$(BH)_{ma}$	min	281	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.72	%/°C
T_{max}		100	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40M – Anisotropic Sintered

Demagnetisation Curve N40M

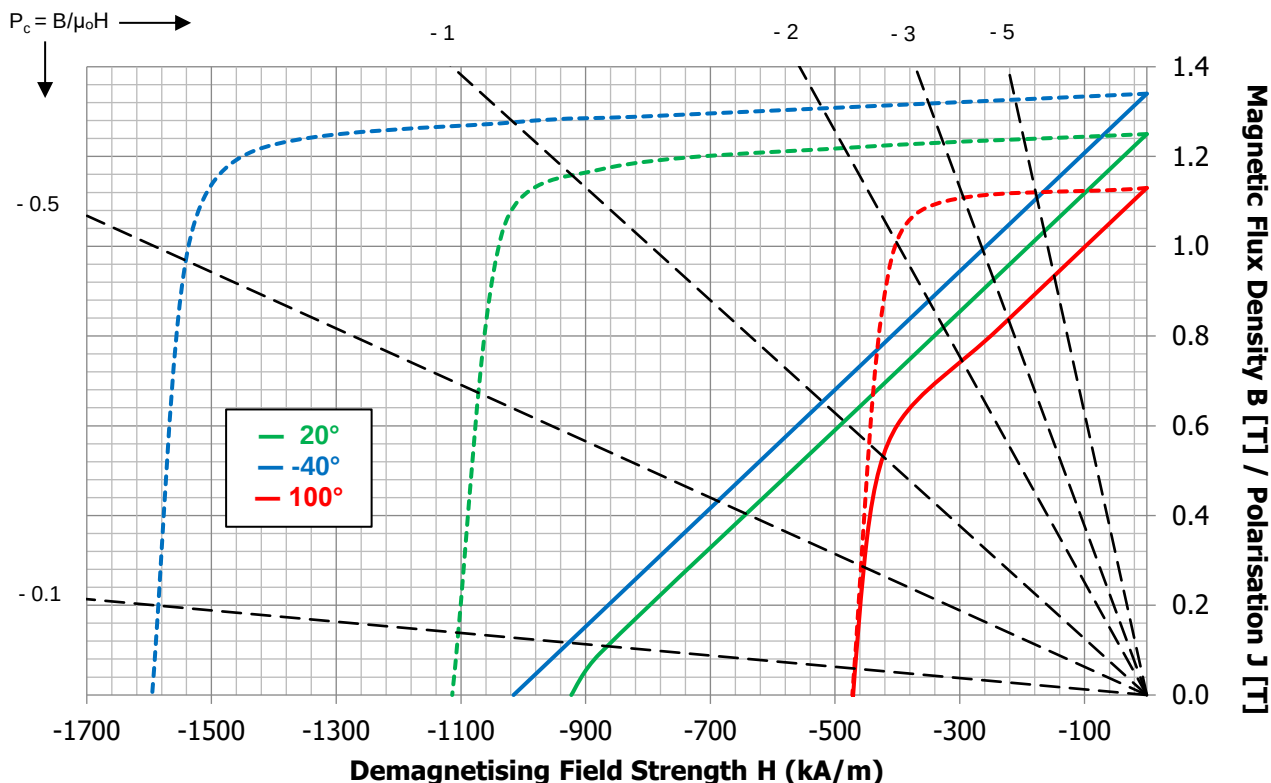

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmnit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.25	T	
H_{cB}	min	923	kA/m	
H_{cJ}	min	1114	kA/m	
$(BH)_{ma}$	min	300	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.72	%/°C	
T_{max}		100	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42M – Anisotropic Sintered

Demagnetisation Curve N42M

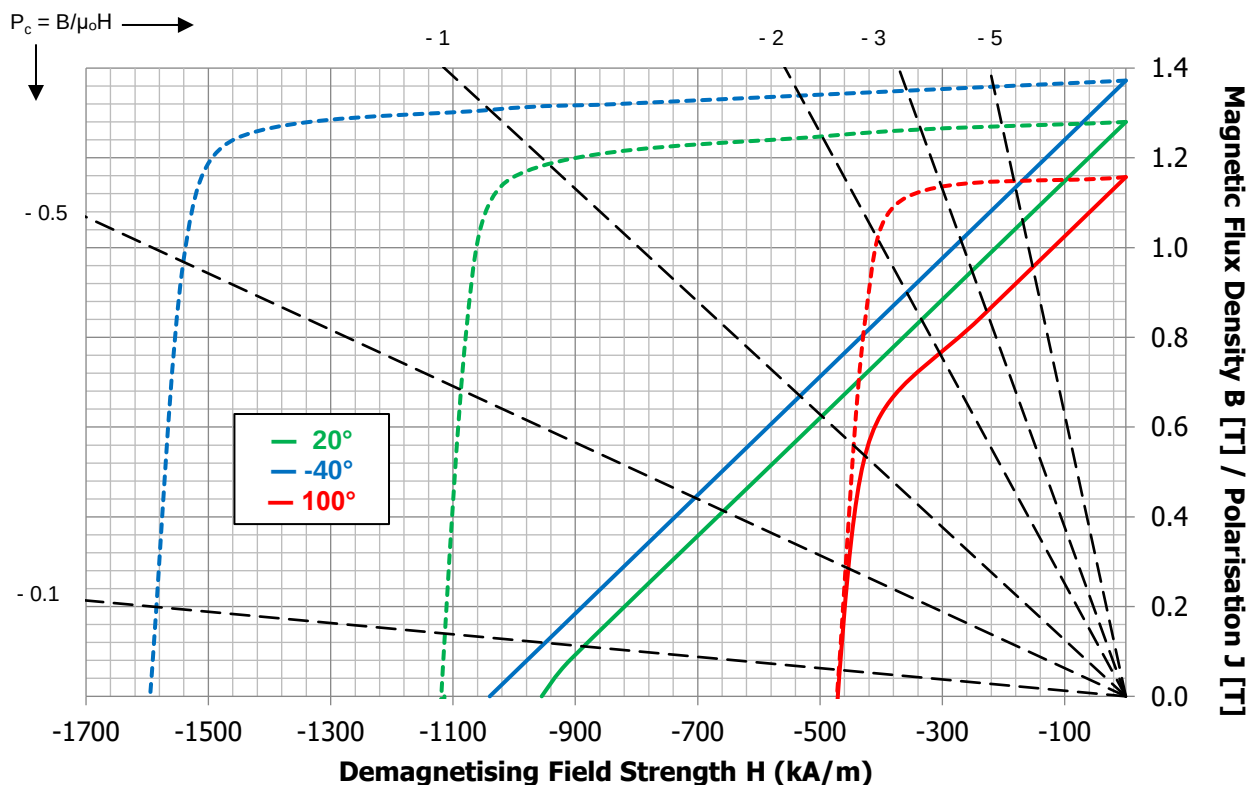

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.28	T
H_{cB}	min	955	kA/m
H_{cJ}	min	1114	kA/m
$(BH)_{ma}$	min	318	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.72	%/°C
T_{max}		100	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45M – Anisotropic Sintered

Demagnetisation Curve N45M

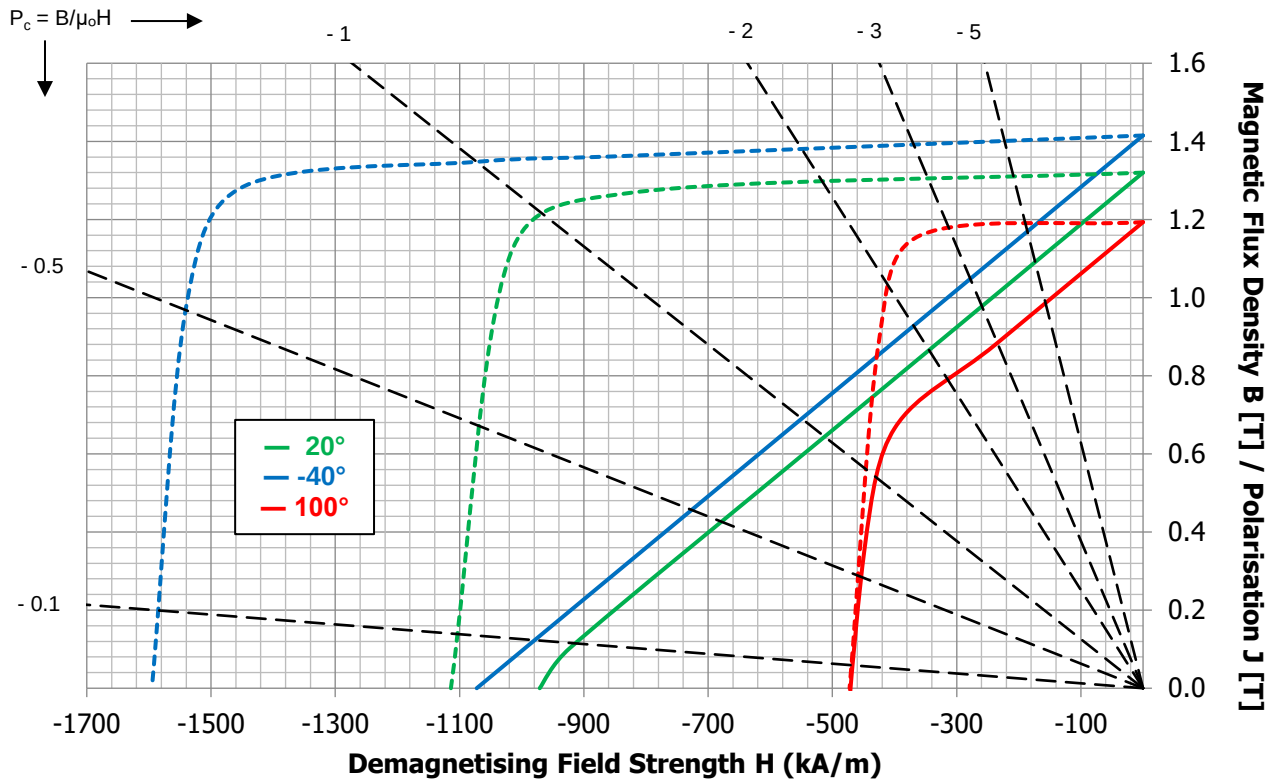

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.32	T
H_{cB}	min	971	kA/m
H_{cJ}	min	1114	kA/m
$(BH)_{ma}$	min	338	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.72	%/°C
T_{max}		100	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N48M – Anisotropic Sintered

Demagnetisation Curve N48M

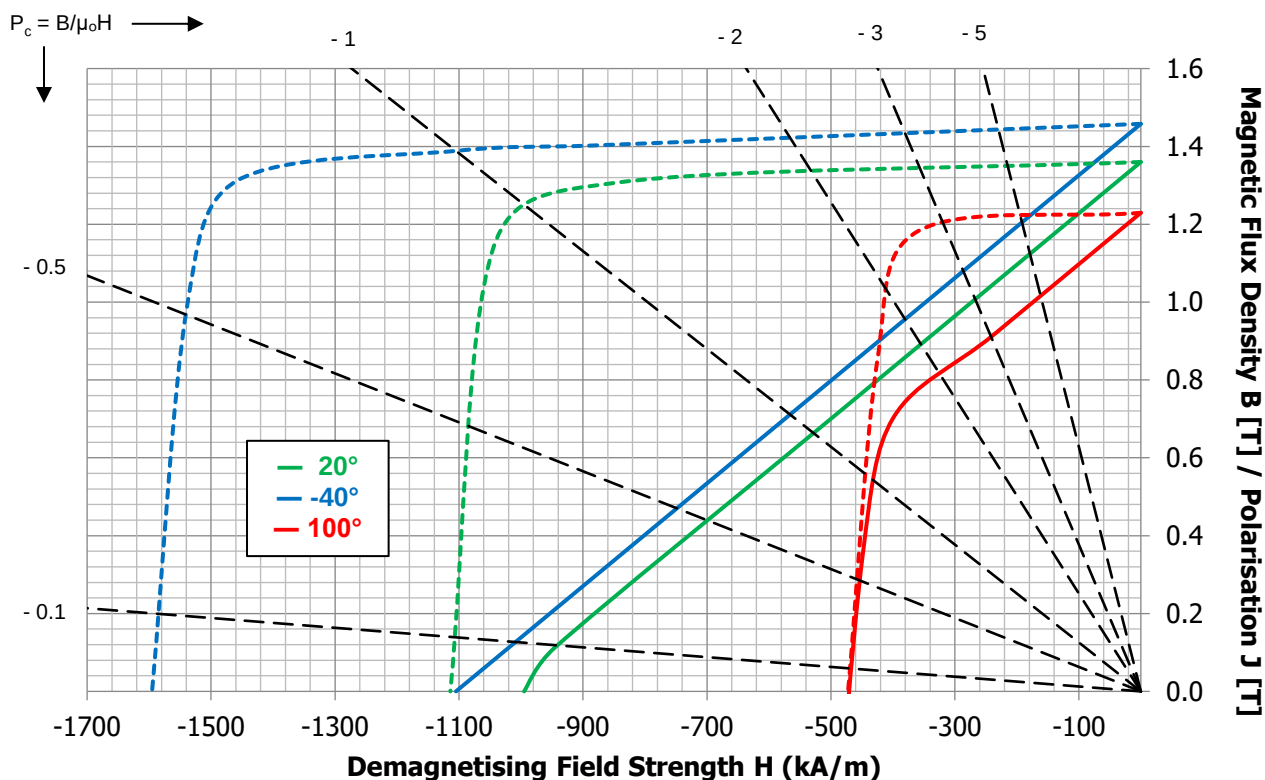

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmi grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.36	T	
H_{cB}	min	995	kA/m	
H_{cJ}	min	1114	kA/m	
$(BH)_{ma}$	min	358	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.72	%/°C	
T_{max}		100	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N50M – Anisotropic Sintered

Demagnetisation Curve N50M

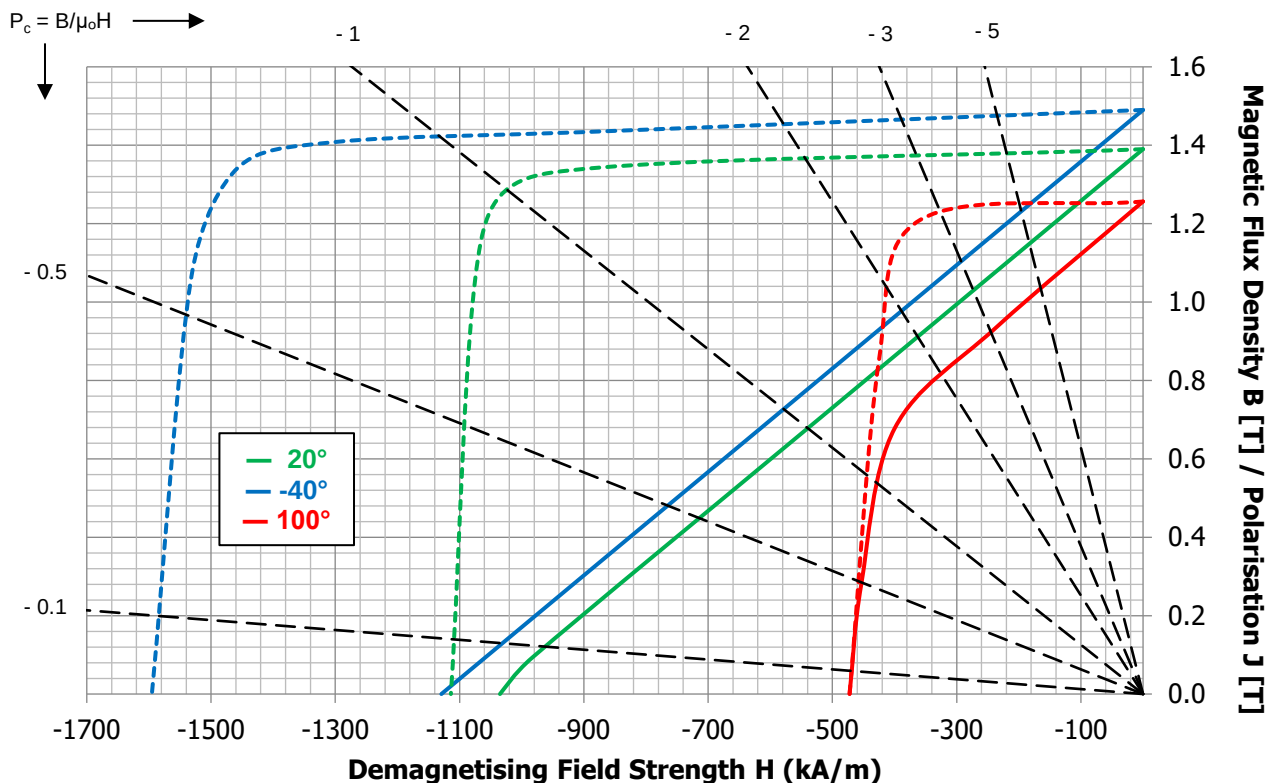

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.39	T	
H_{cB}	min	1035	kA/m	
H_{cJ}	min	1114	kA/m	
$(BH)_{ma}$	min	376	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.72	%/°C	
T_{max}		100	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N52M – Anisotropic Sintered

Demagnetisation Curve N52M

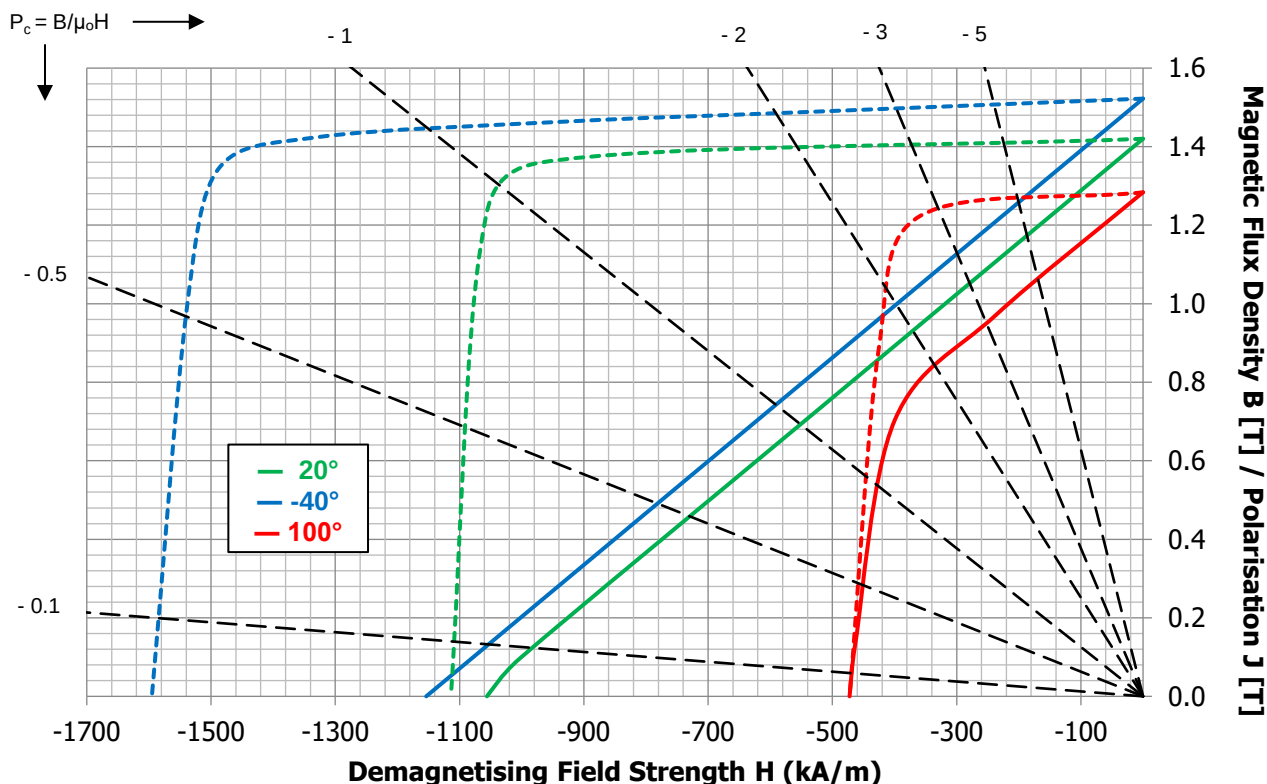

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C				
B_r	min	1.42	T	
H_{cB}	min	1056	kA/m	
H_{cJ}	min	1114	kA/m	
$(BH)_{ma}$	min	390	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.72	%/°C	
T_{max}		100	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	10 ⁻⁶ /K	

* DOM = Direction Of Magnetisation


H- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N35H	1170	868	1353	259	-0.12	-0.66	120
N38H	1220	899	1353	281	-0.12	-0.66	120
N40H	1250	923	1353	300	-0.12	-0.66	120
N42H	1280	955	1353	318	-0.12	-0.66	120
N45H	1320	971	1353	333	-0.12	-0.66	120
N48H	1360	1011	1353	358	-0.12	-0.66	120
N50H	1390	1035	1353	374	-0.12	-0.66	120
N52H	1420	1035	1353	390	-0.12	-0.66	120

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N35H – Anisotropic Sintered

Demagnetisation Curve N35H

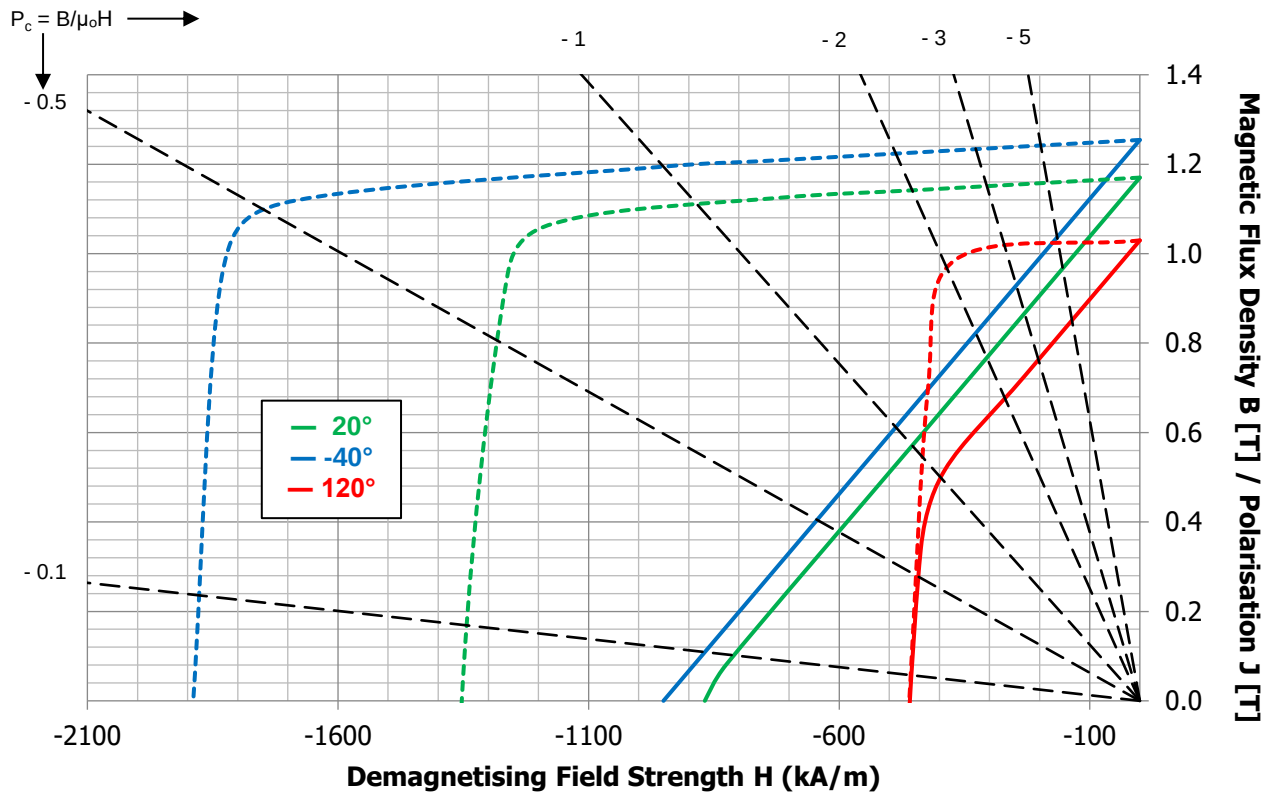

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmnit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.17	T	
H_{cB}	min	868	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	259	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38H – Anisotropic Sintered

Demagnetisation Curve N38H

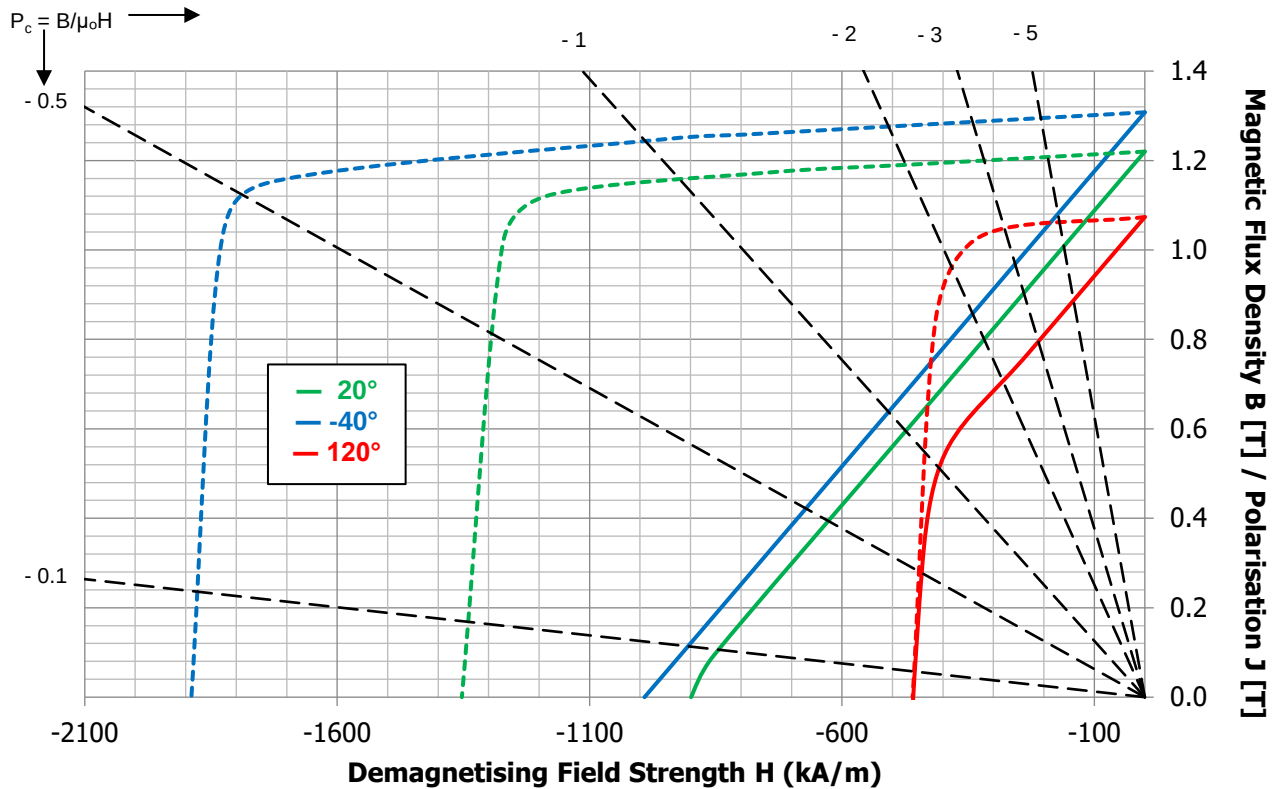

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.22	T
H_{cB}	min	899	kA/m
H_{cJ}	min	1353	kA/m
$(BH)_{ma}$	min	281	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.66	%/°C
T_{max}		120	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40H – Anisotropic Sintered

Demagnetisation Curve N40H

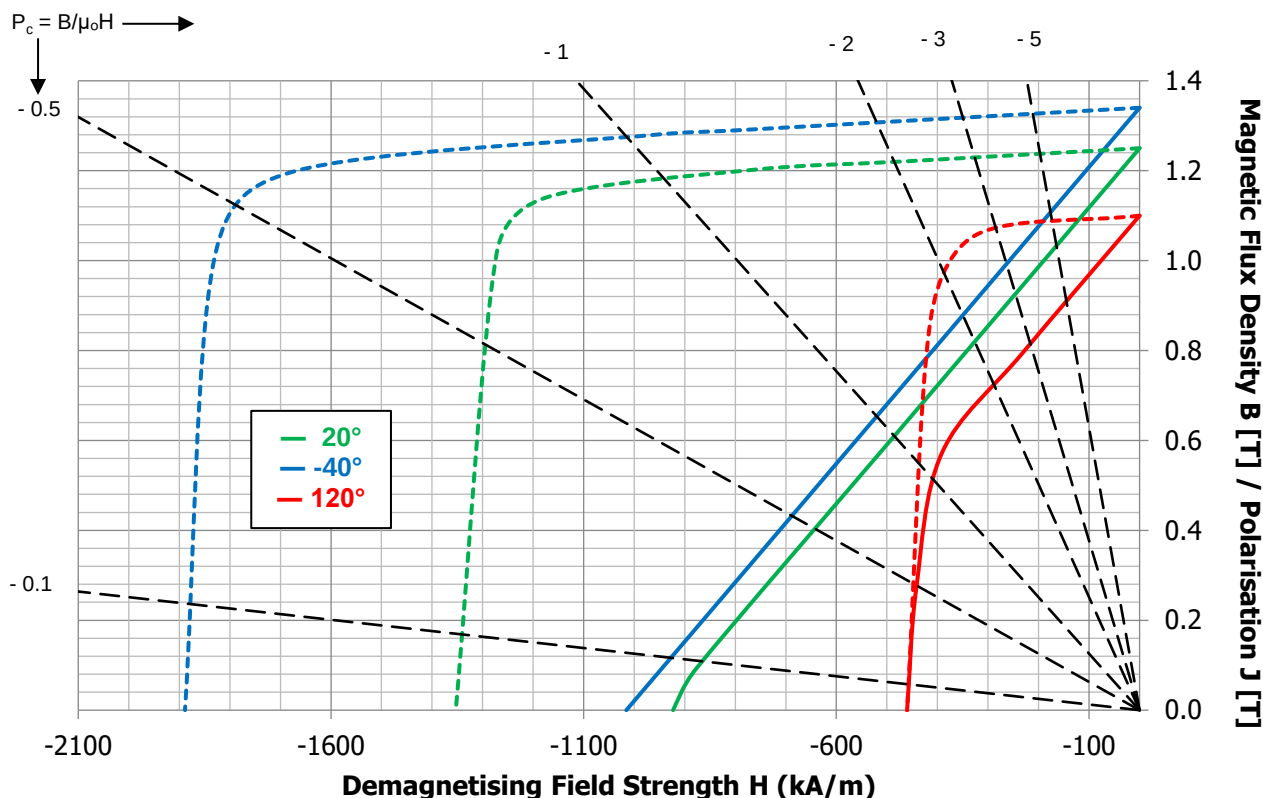

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.25	T	
H_{cB}	min	923	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	300	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42H – Anisotropic Sintered

Demagnetisation Curve N42H

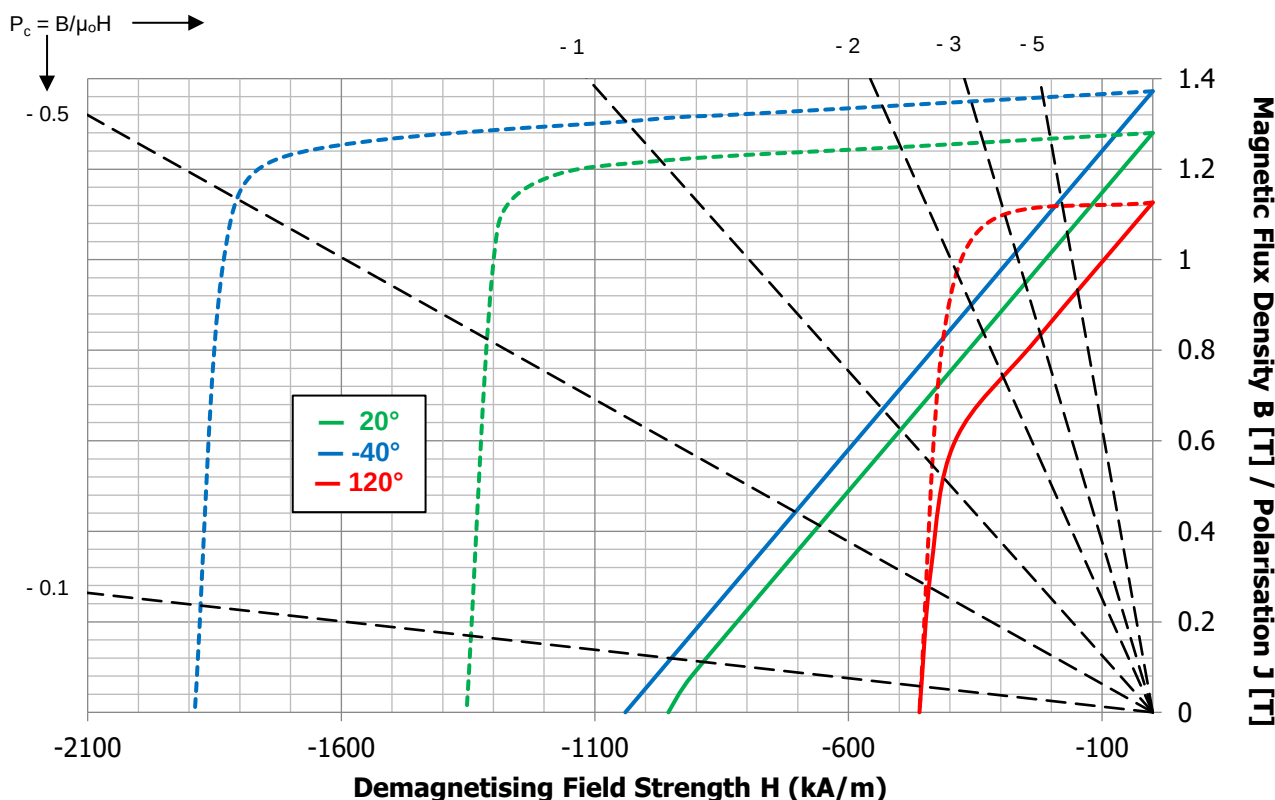

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.28	T	
H_{cB}	min	955	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	318	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45H – Anisotropic Sintered

Demagnetisation Curve N45H

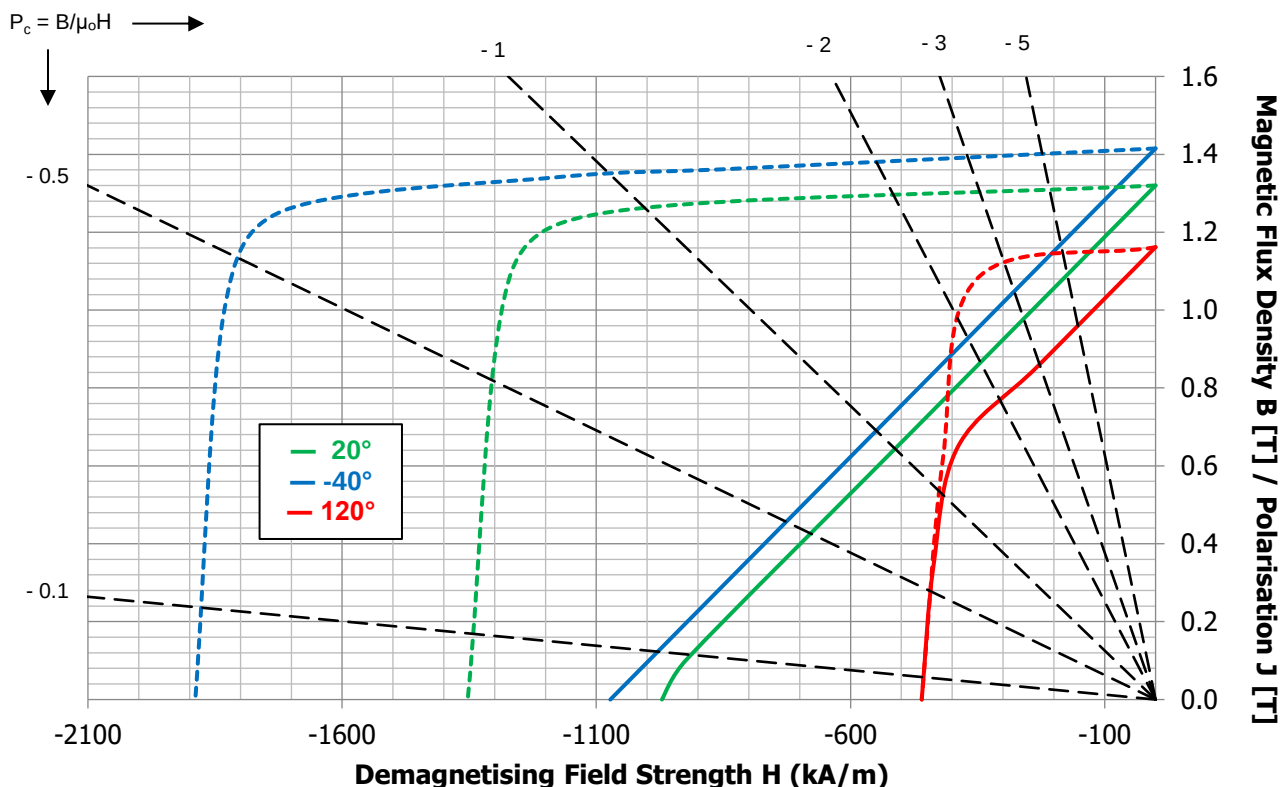

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.32	T	
H_{cB}	min	971	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	333	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N48H – Anisotropic Sintered

Demagnetisation Curve N48H

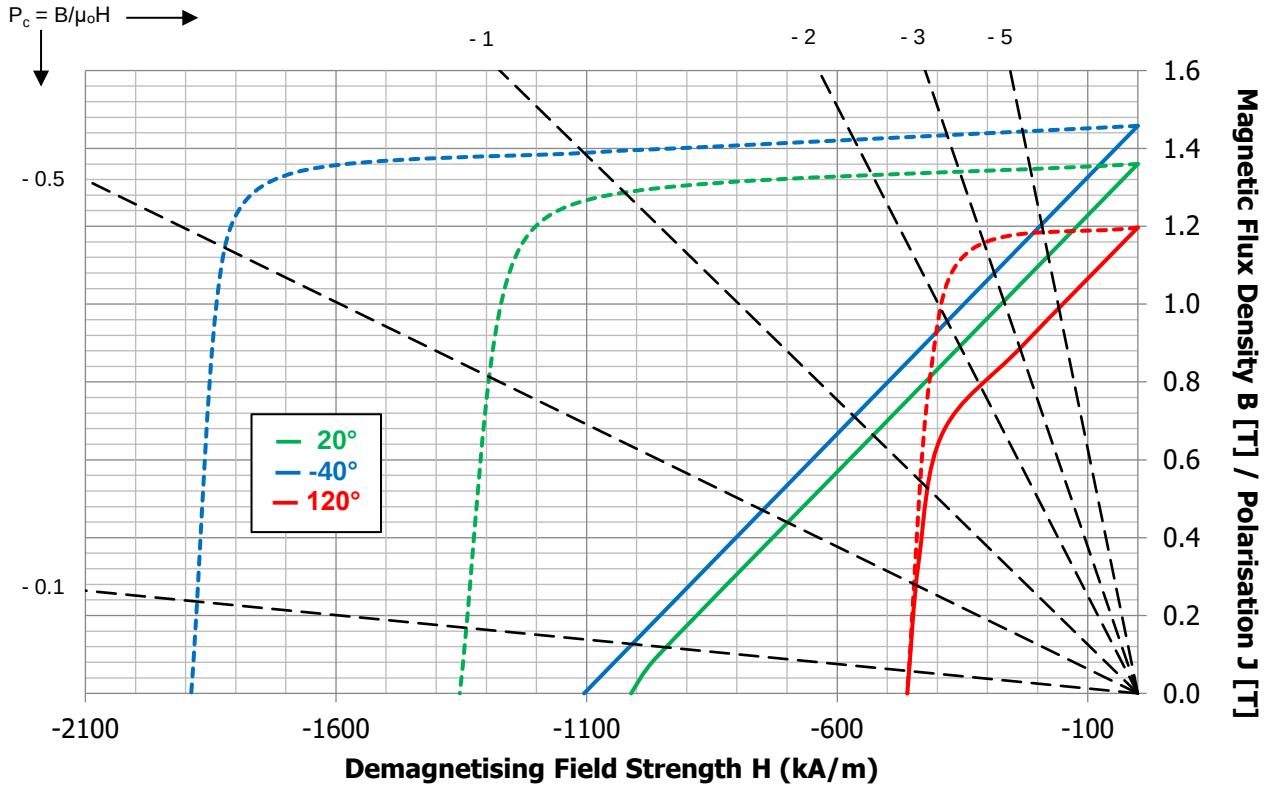

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.36	T	
H_{cB}	min	1011	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	358	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N50H – Anisotropic Sintered

Demagnetisation Curve N50H

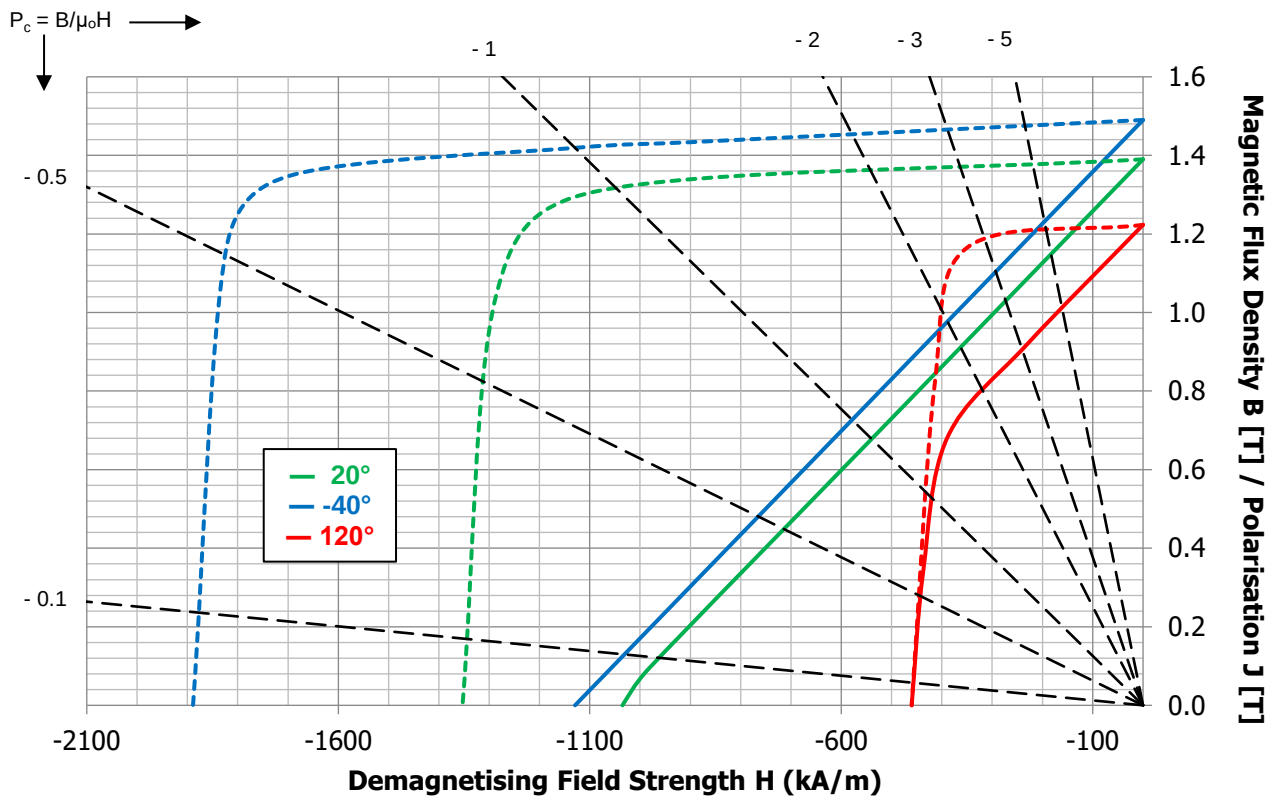

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.39	T	
H_{cB}	min	1035	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	374	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N52H – Anisotropic Sintered

Demagnetisation Curve N52H

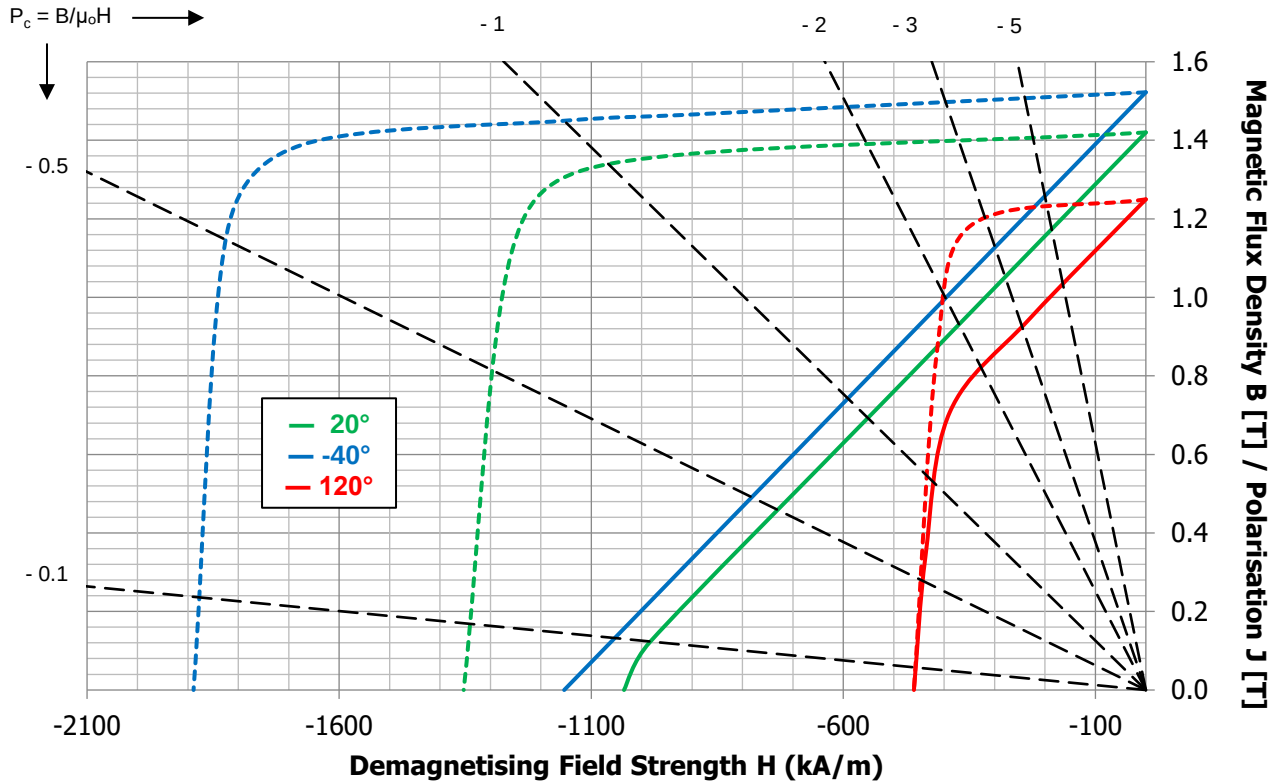

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C				
B_r	min	1.42	T	
H_{cB}	min	1035	kA/m	
H_{cJ}	min	1353	kA/m	
$(BH)_{ma}$	min	390	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.66	%/°C	
T_{max}		120	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation


SH- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N33SH	1130	844	1592	246	-0.12	-0.62	150
N35SH	1170	876	1592	259	-0.12	-0.62	150
N38SH	1220	907	1592	281	-0.12	-0.62	150
N40SH	1250	939	1592	300	-0.12	-0.62	150
N42SH	1280	955	1592	318	-0.12	-0.62	150
N45SH	1320	979	1592	333	-0.12	-0.62	150
N48SH	1360	995	1592	358	-0.12	-0.62	150
N50SH	1390	995	1592	374	-0.12	-0.62	150
N52SH	1420	995	1592	390	-0.12	-0.62	150

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N33SH – Anisotropic Sintered

Demagnetisation Curve N33SH

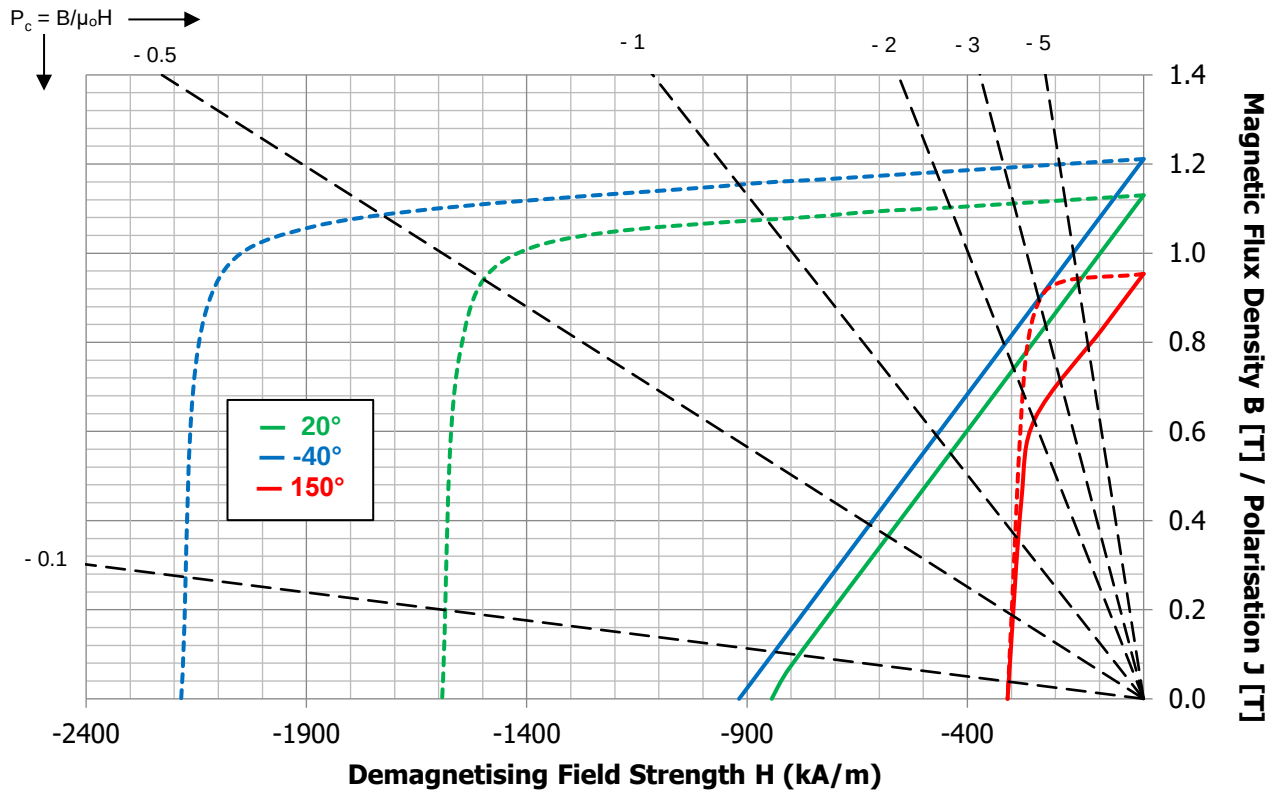

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.13	T	
H_{cB}	min	844	kA/m	
H_{cJ}	min	1592	kA/m	
$(BH)_{ma}$	min	246	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.62	%/°C	
T_{max}		150	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N35SH – Anisotropic Sintered

Demagnetisation Curve N35SH

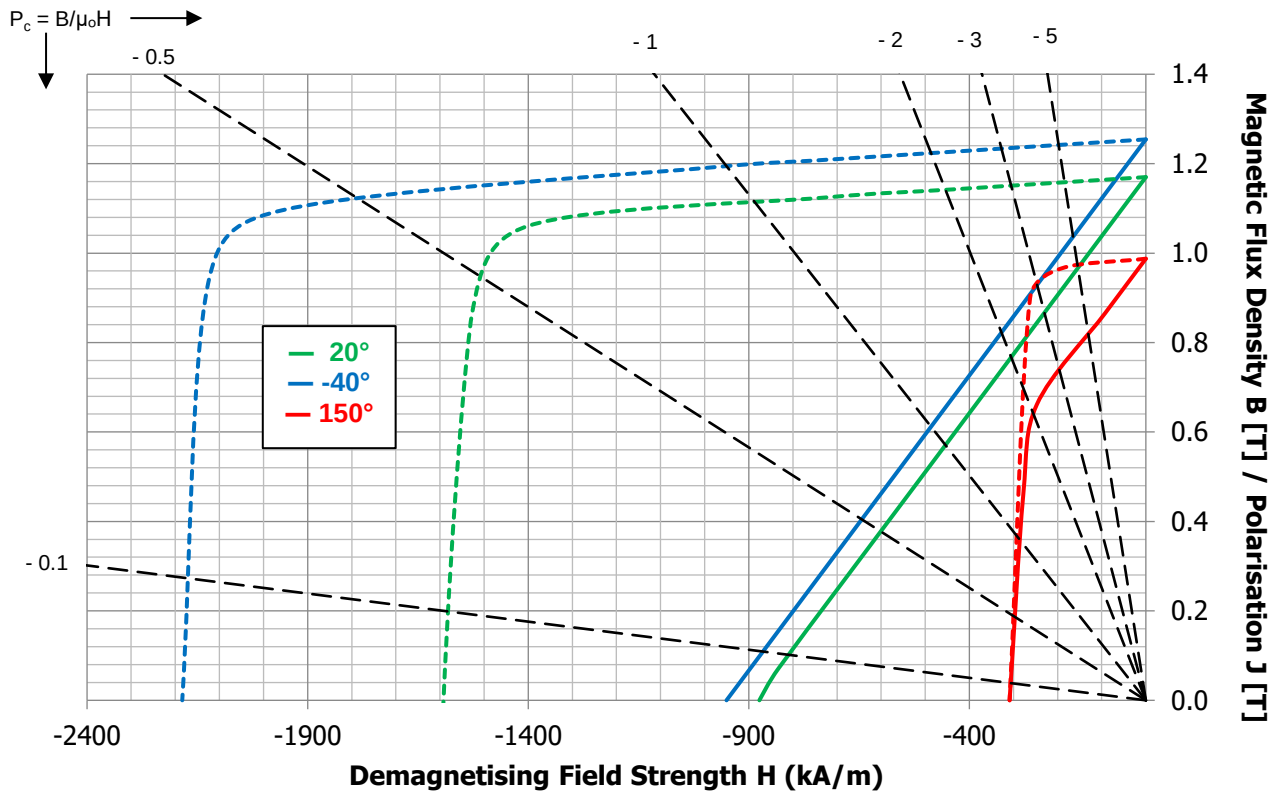

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.17	T
H_{cB}	min	876	kA/m
H_{cJ}	min	1592	kA/m
(BH)_{ma}	min	259	kJ/m ³
α(B_r)	min typ	-0.12	%/°C
β(H_{cJ})	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	μΩm
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K
Coefficient of linear thermal expansion, ⊥ DOM*	typ	-3 - 0	10 ⁻⁶ /K

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38SH – Anisotropic Sintered

Demagnetisation Curve N38SH

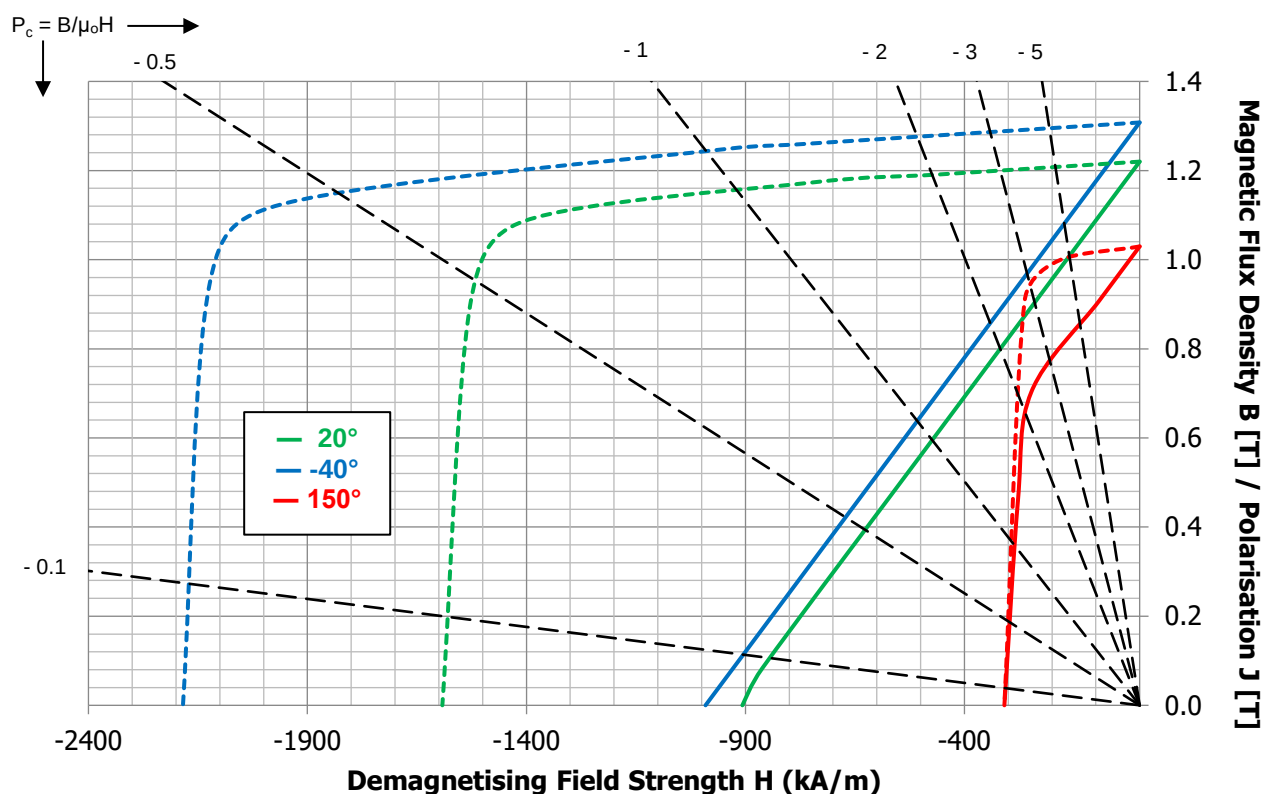

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.22	T	
H_{cB}	min	907	kA/m	
H_{cJ}	min	1592	kA/m	
$(BH)_{ma}$	min	281	kJ/m^3	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.62	%/°C	
T_{max}		150	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40SH – Anisotropic Sintered

Demagnetisation Curve N40SH

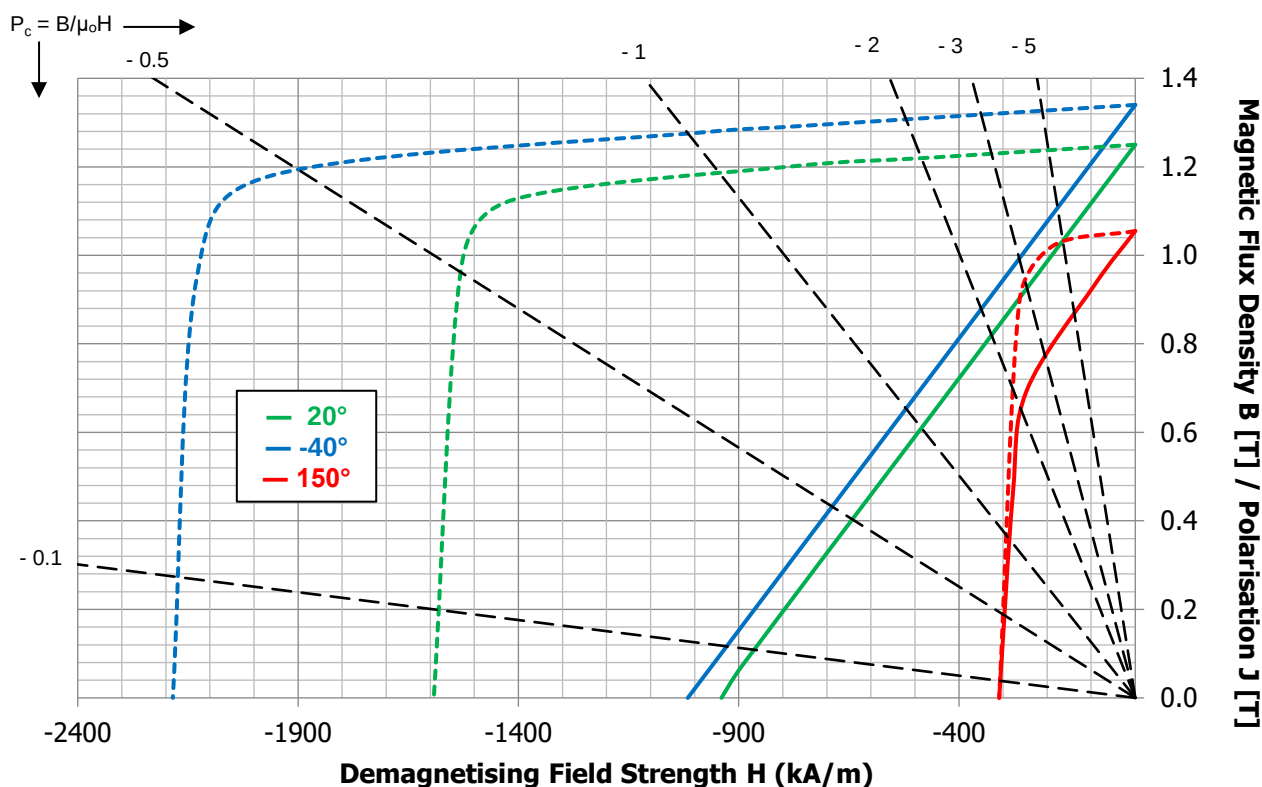

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.25	T
H_{cB}	min	939	kA/m
H_{cJ}	min	1592	kA/m
$(BH)_{ma}$	min	300	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42SH – Anisotropic Sintered

Demagnetisation Curve N42SH

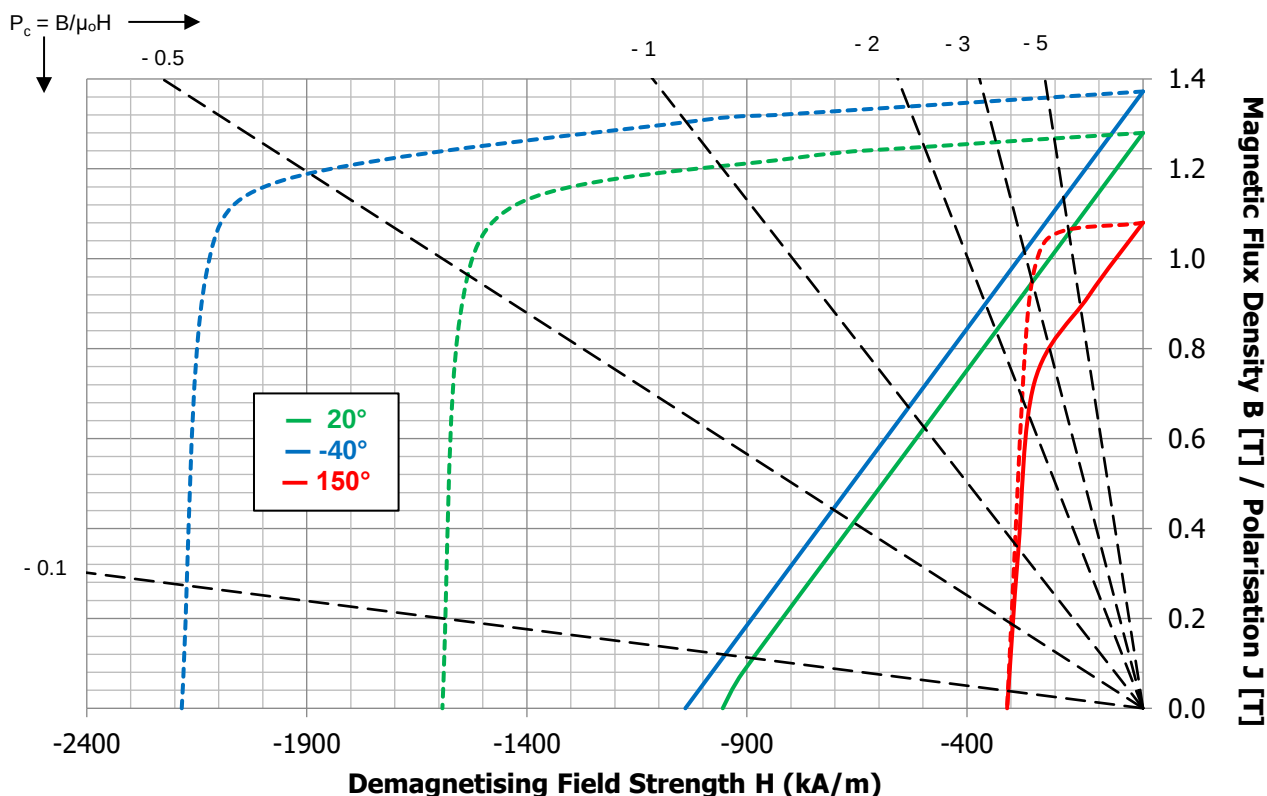

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.28	T
H_{cB}	min	955	kA/m
H_{cJ}	min	1592	kA/m
$(BH)_{ma}$	min	318	kJ/m^3
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m^3
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45SH – Anisotropic Sintered

Demagnetisation Curve N45SH

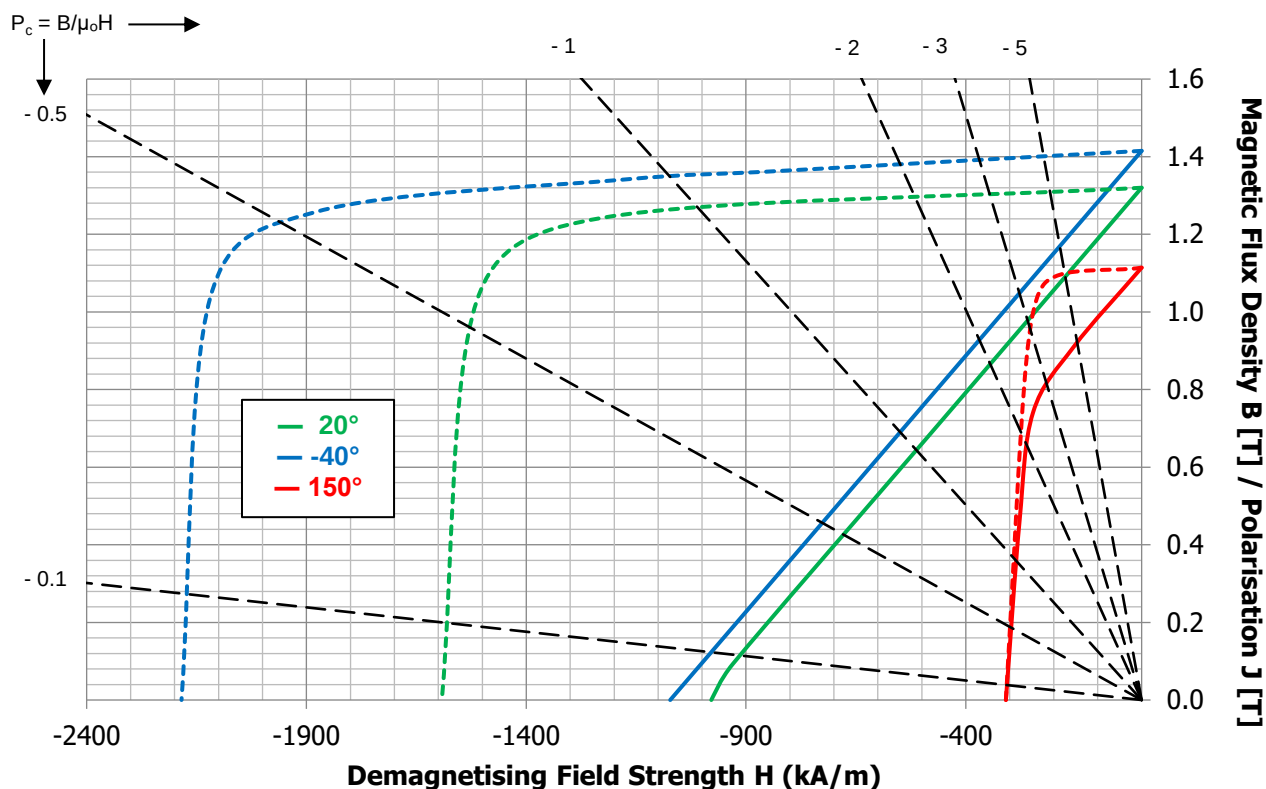

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.32	T
H_{cB}	min	979	kA/m
H_{cJ}	min	1592	kA/m
$(BH)_{ma}$	min	333	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega$ m
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	10 ⁻⁶ /K

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N48SH – Anisotropic Sintered

Demagnetisation Curve N48SH

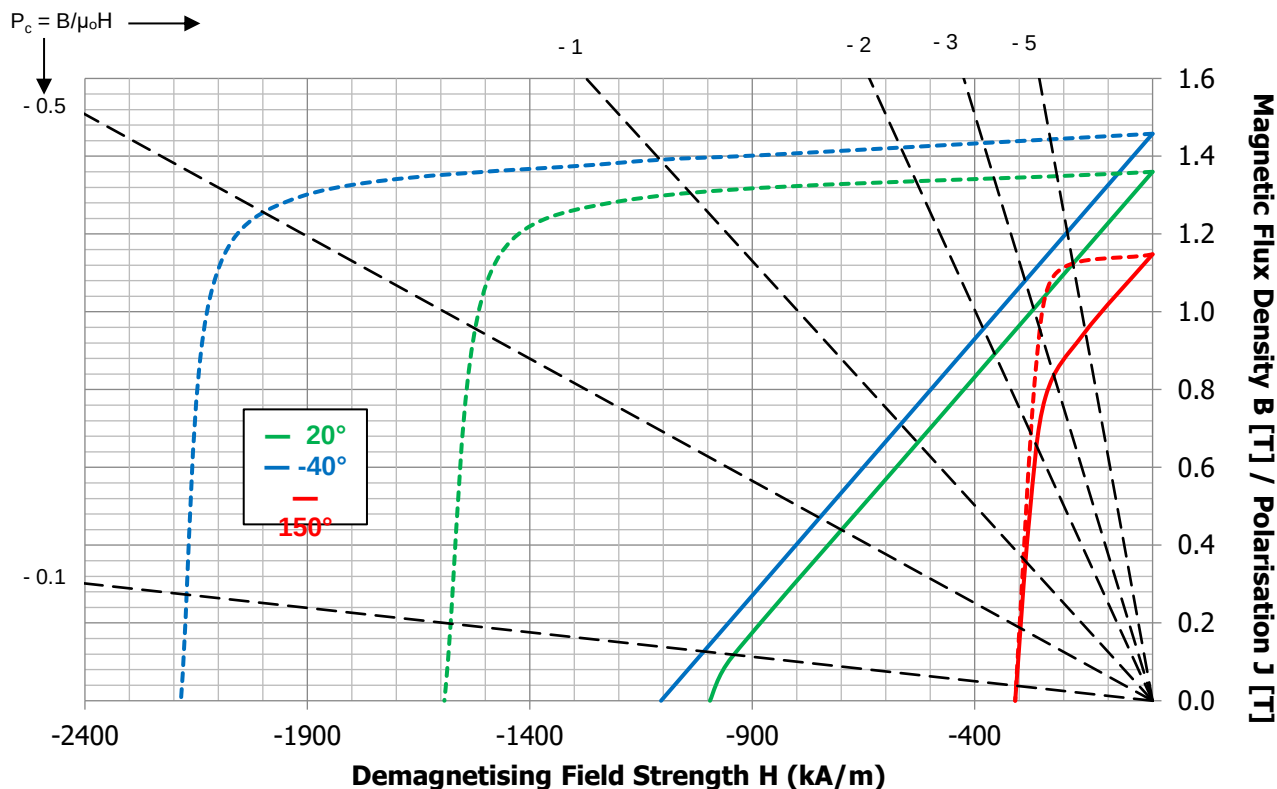

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.36	T
H_{cB}	min	995	kA/m
H_{cJ}	min	1592	kA/m
$(BH)_{ma}$	min	358	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N50SH – Anisotropic Sintered

Demagnetisation Curve N50SH

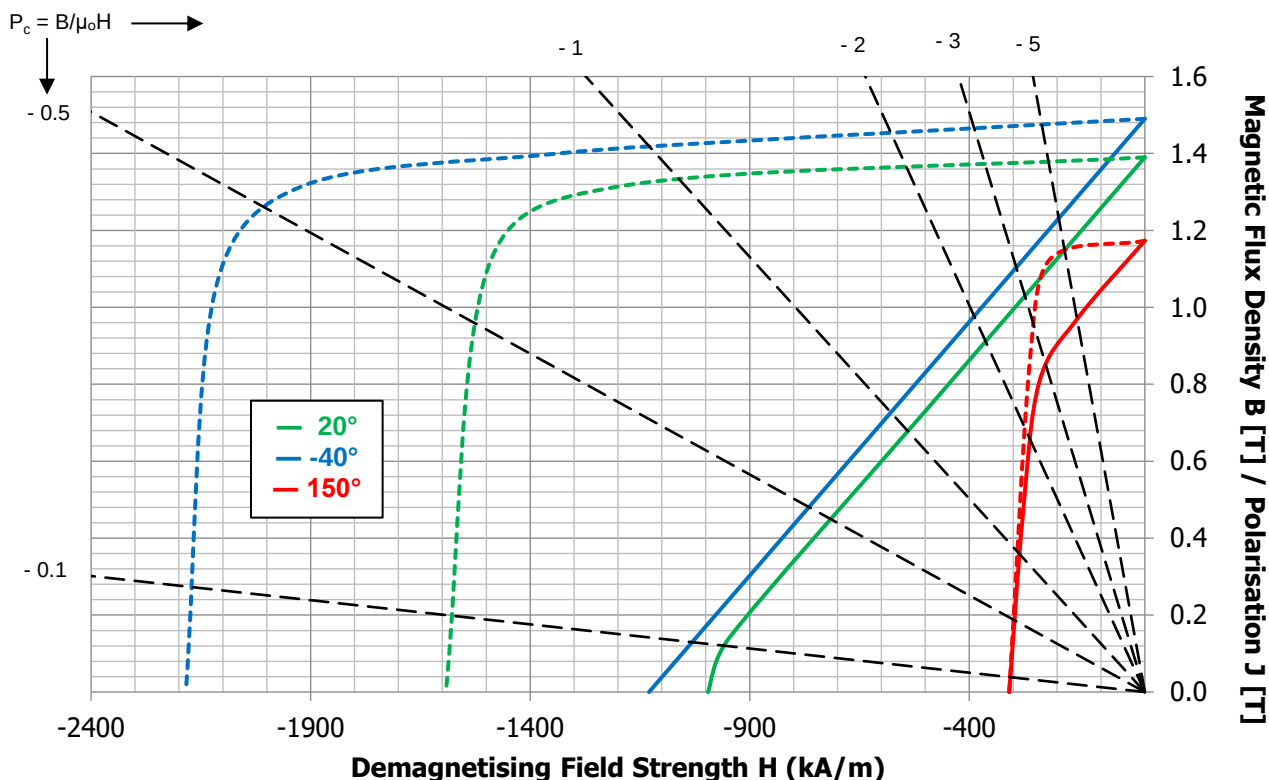

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.39	T	
H_{cB}	min	995	kA/m	
H_{cJ}	min	1592	kA/m	
$(BH)_{ma}$	min	374	kJ/m ³	
$\alpha(B_r)$	min typ	-0.12	%/°C	
$\beta(H_{cJ})$	min typ	-0.62	%/°C	
T_{max}		150	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N52SH – Anisotropic Sintered

Demagnetisation Curve N52SH

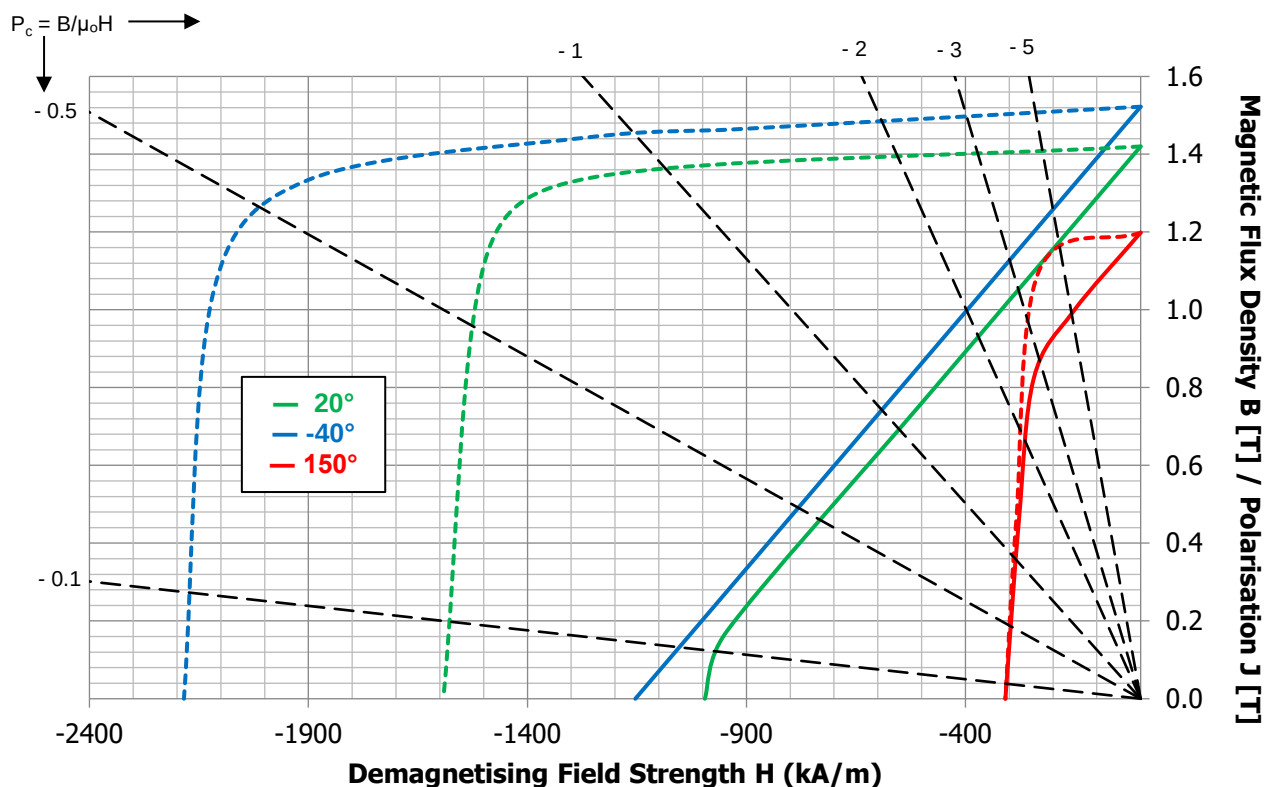

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C			
B_r	min	1.42	T
H_{cB}	min	995	kA/m
H_{cJ}	min	1592	kA/m
$(BH)_{ma}$	min	390	kJ/m ³
$\alpha(B_r)$	min typ	-0.12	%/°C
$\beta(H_{cJ})$	min typ	-0.62	%/°C
T_{max}		150	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation


UH- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N30UH	1080	812	1989	220	-0.115	-0.58	180
N33UH	1130	852	1989	246	-0.115	-0.58	180
N35UH	1170	860	1989	259	-0.115	-0.58	180
N38UH	1220	876	1989	281	-0.115	-0.58	180
N40UH	1250	915	1989	300	-0.115	-0.58	180
N42UH	1270	955	1989	318	-0.115	-0.58	180
N45UH	1320	995	1989	333	-0.115	-0.58	180
N48UH	1370	995	1989	358	-0.115	-0.58	180
N50UH	1390	995	1989	374	-0.115	-0.58	180

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N30UH – Anisotropic Sintered

Demagnetisation Curve N30UH

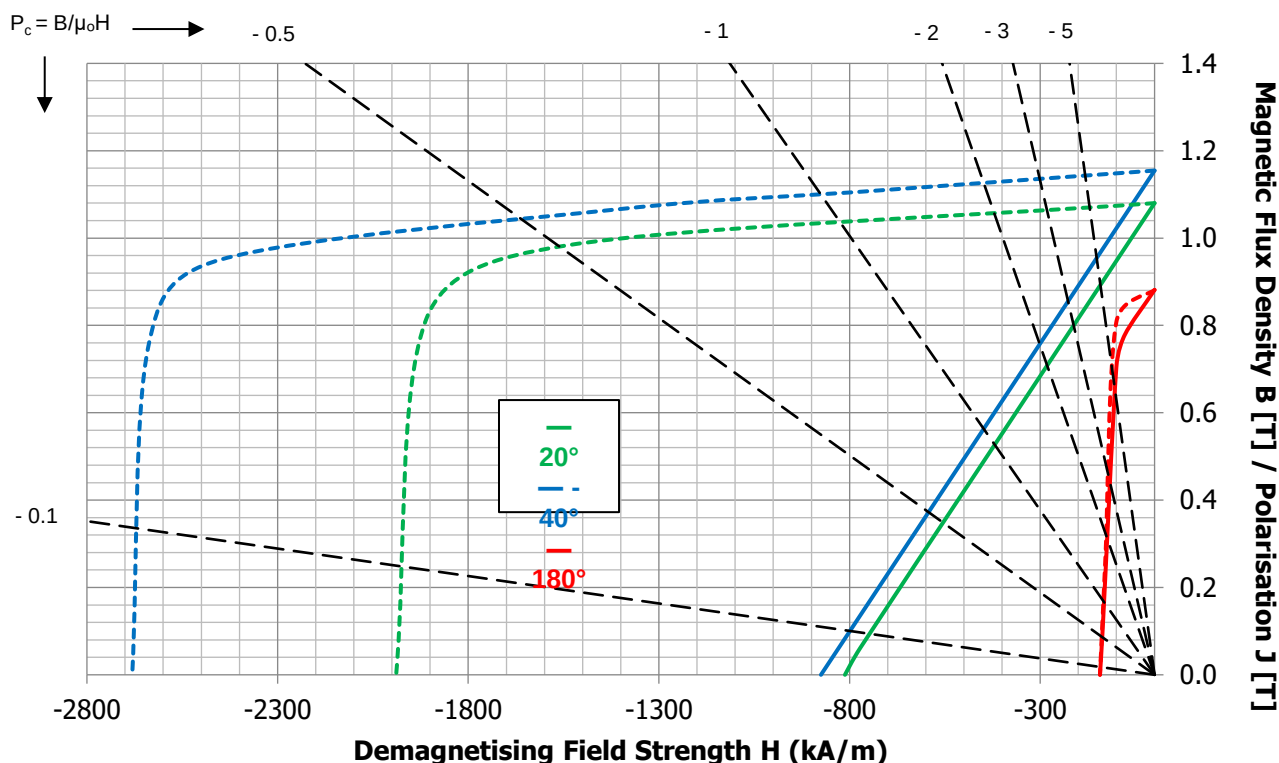

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.08	T
H_{cB}	min	812	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	220	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N33UH – Anisotropic Sintered

Demagnetisation Curve N33UH

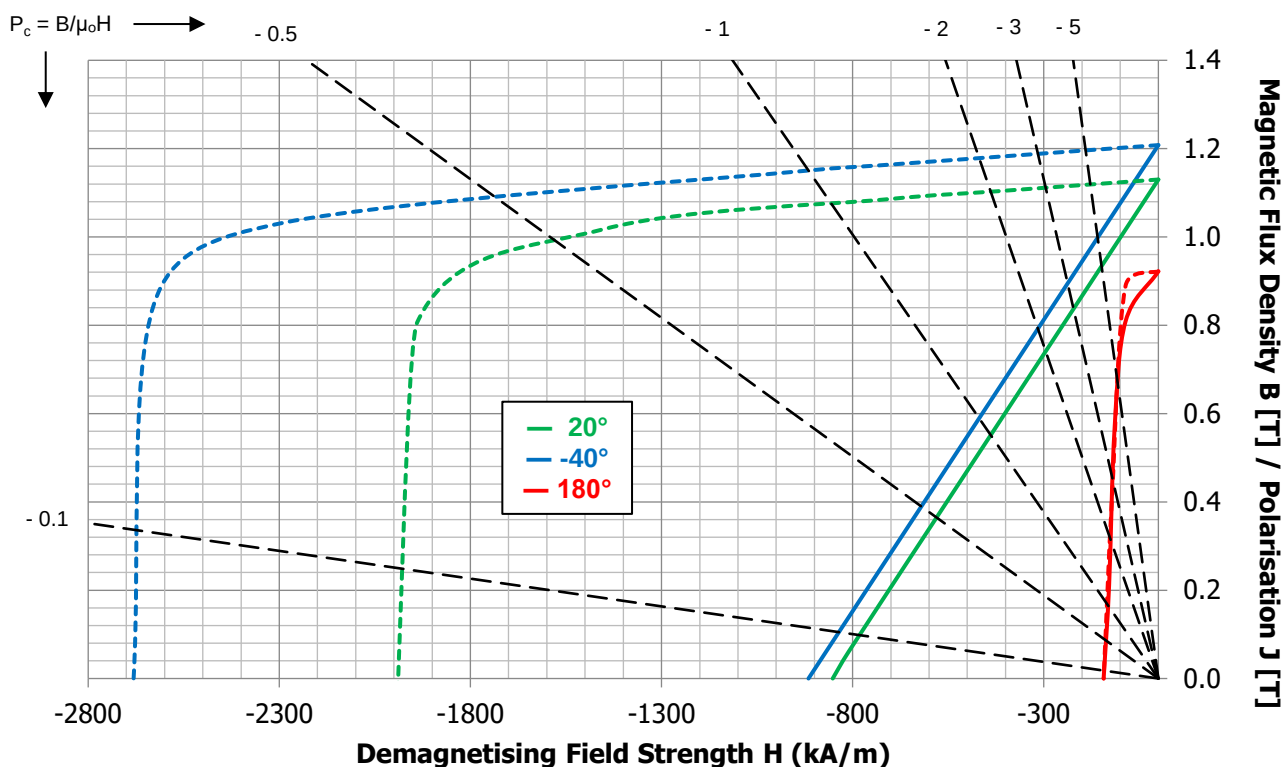

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic properties @20°C			
B_r	min	1.13	T
H_{cB}	min	852	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	246	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N35UH – Anisotropic Sintered

Demagnetisation Curve N35UH

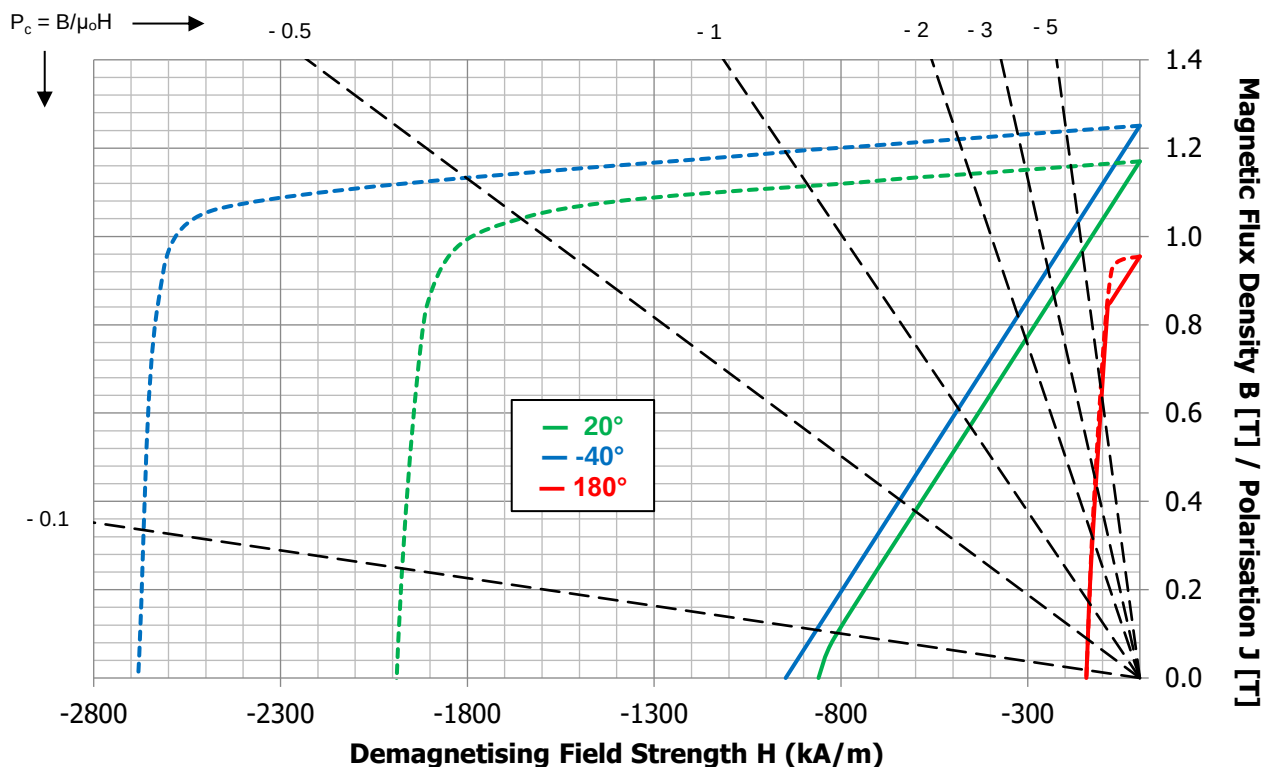

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.17	T
H_{cB}	min	860	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	259	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38UH – Anisotropic Sintered

Demagnetisation Curve N38UH

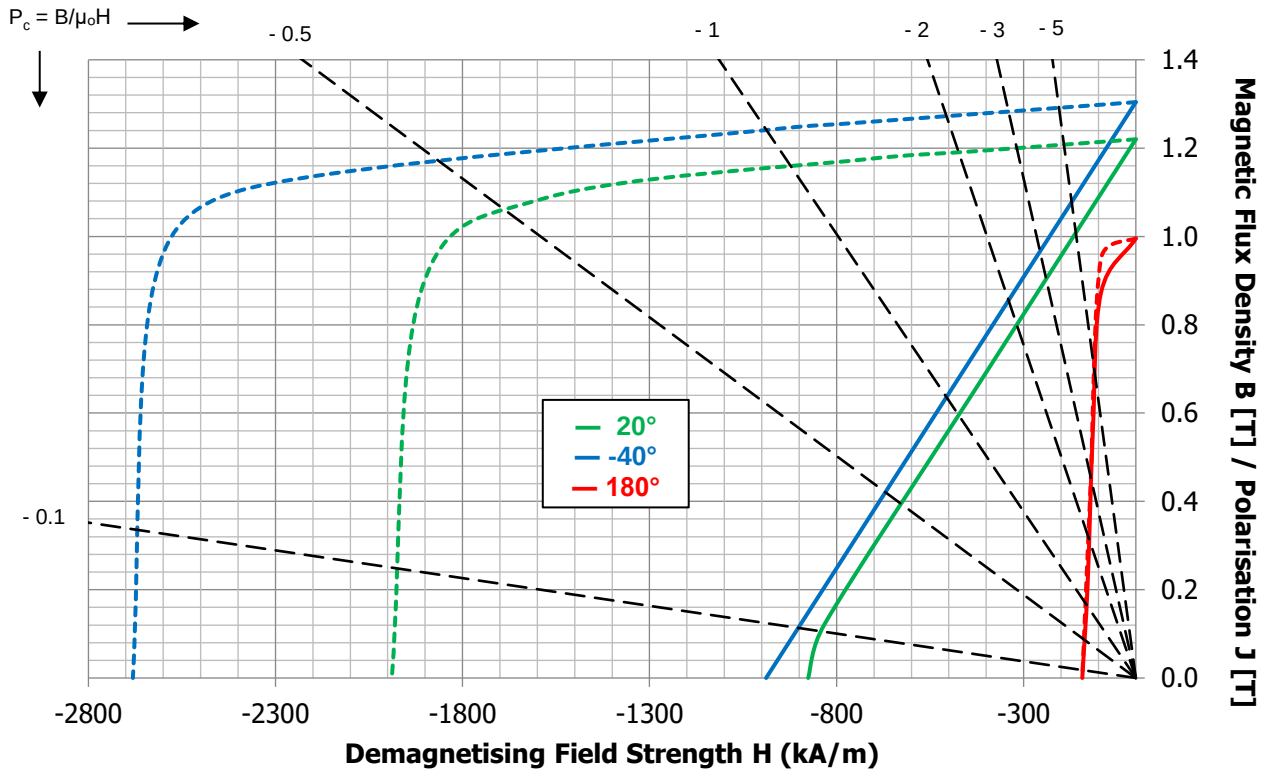

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic properties @20°C			
B_r	min	1.22	T
H_{cB}	min	876	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	281	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40UH – Anisotropic Sintered

Demagnetisation Curve N40UH

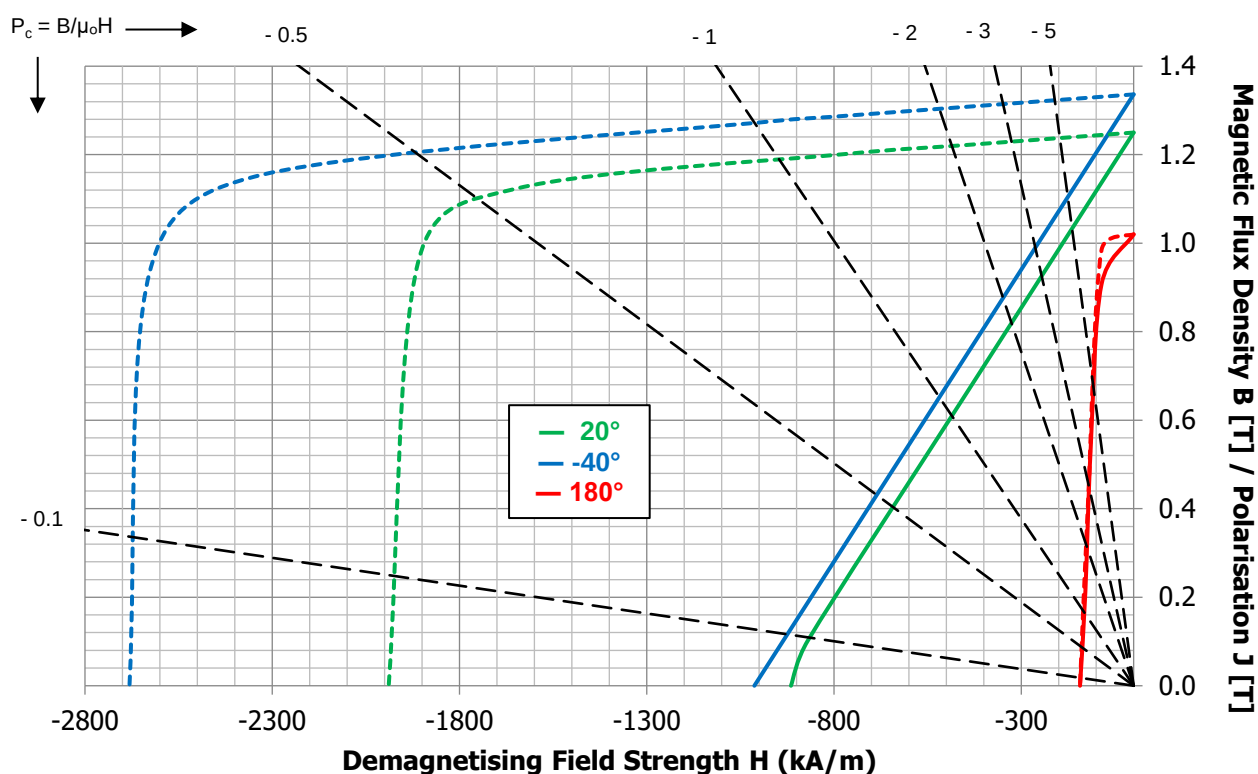

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.25	T	
H_{cB}	min	915	kA/m	
H_{cJ}	min	1989	kA/m	
$(BH)_{ma}$	min	300	kJ/m^3	
$\alpha(B_r)$	min typ	-0.115	%/°C	
$\beta(H_{cJ})$	min typ	-0.58	%/°C	
T_{max}		180	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42UH – Anisotropic Sintered

Demagnetisation Curve N42UH

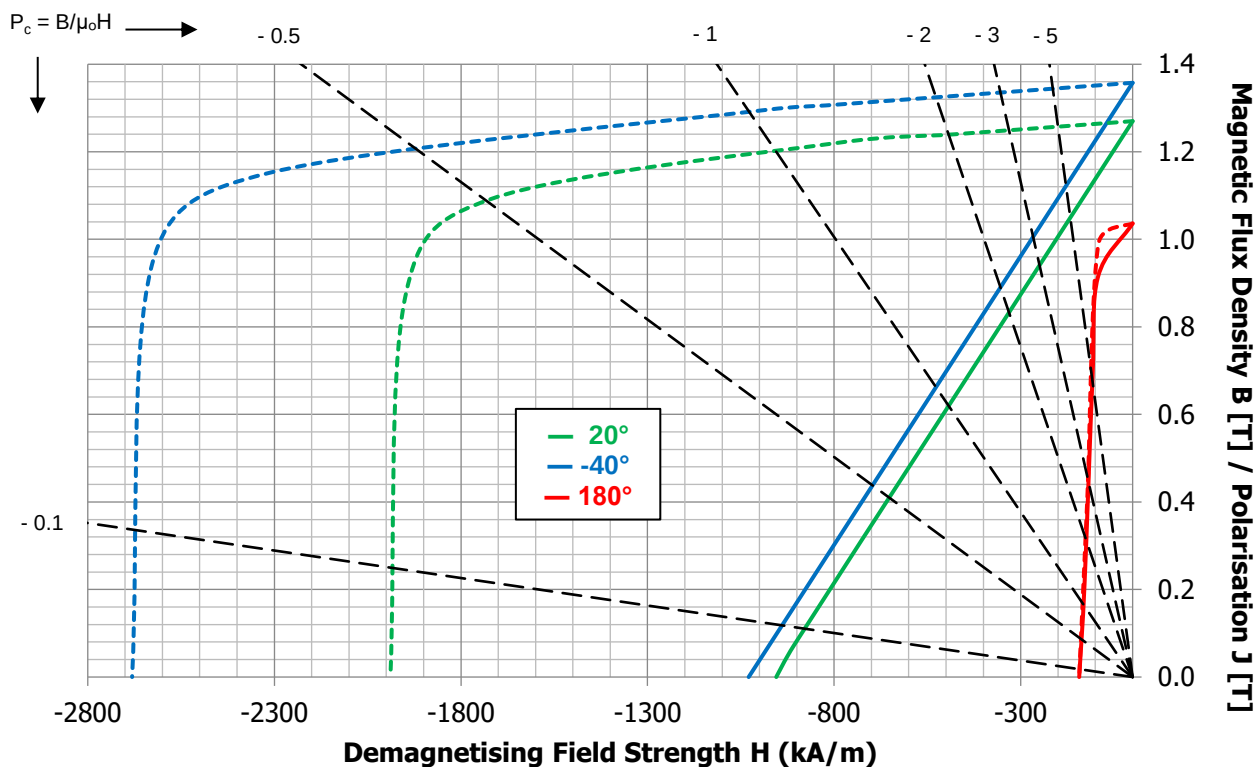

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic properties @20°C				
B_r	min	1.27	T	
H_{cB}	min	955	kA/m	
H_{cJ}	min	1989	kA/m	
$(BH)_{ma}$	min	318	kJ/m^3	
$\alpha(B_r)$	min typ	-0.115	%/°C	
$\beta(H_{cJ})$	min typ	-0.58	%/°C	
T_{max}		180	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45UH – Anisotropic Sintered

Demagnetisation Curve N45UH

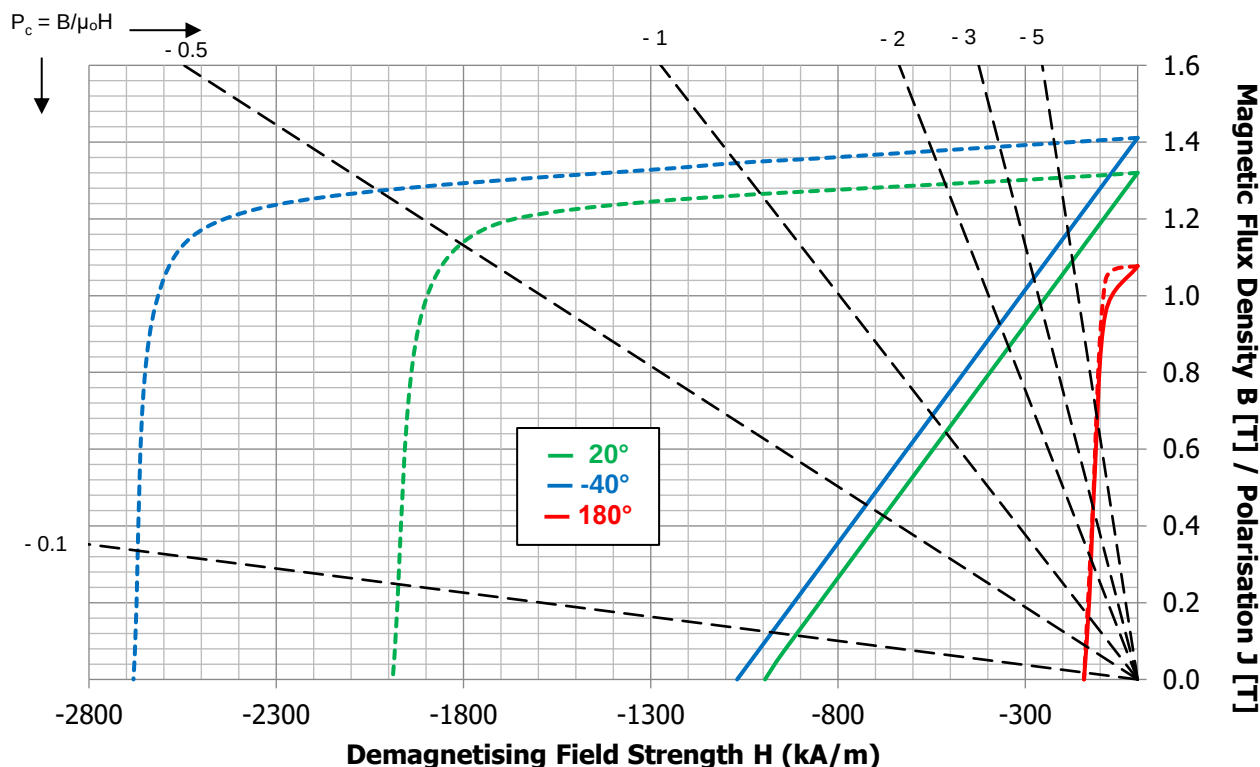

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.32	T
H_{cB}	min	995	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	333	kJ/m^3
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m^3
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N48UH – Anisotropic Sintered

Demagnetisation Curve N48UH

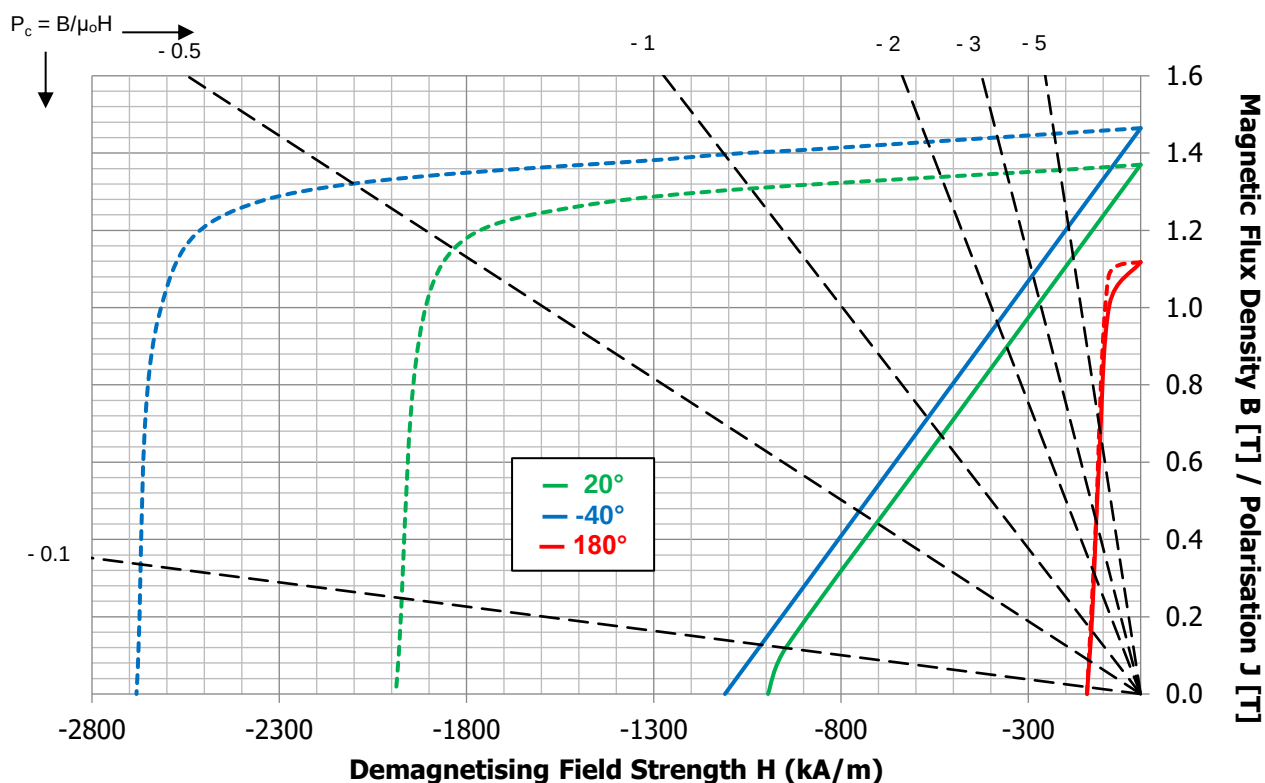

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.37	T
H_{cB}	min	995	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	358	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N50UH – Anisotropic Sintered

Demagnetisation Curve N50UH

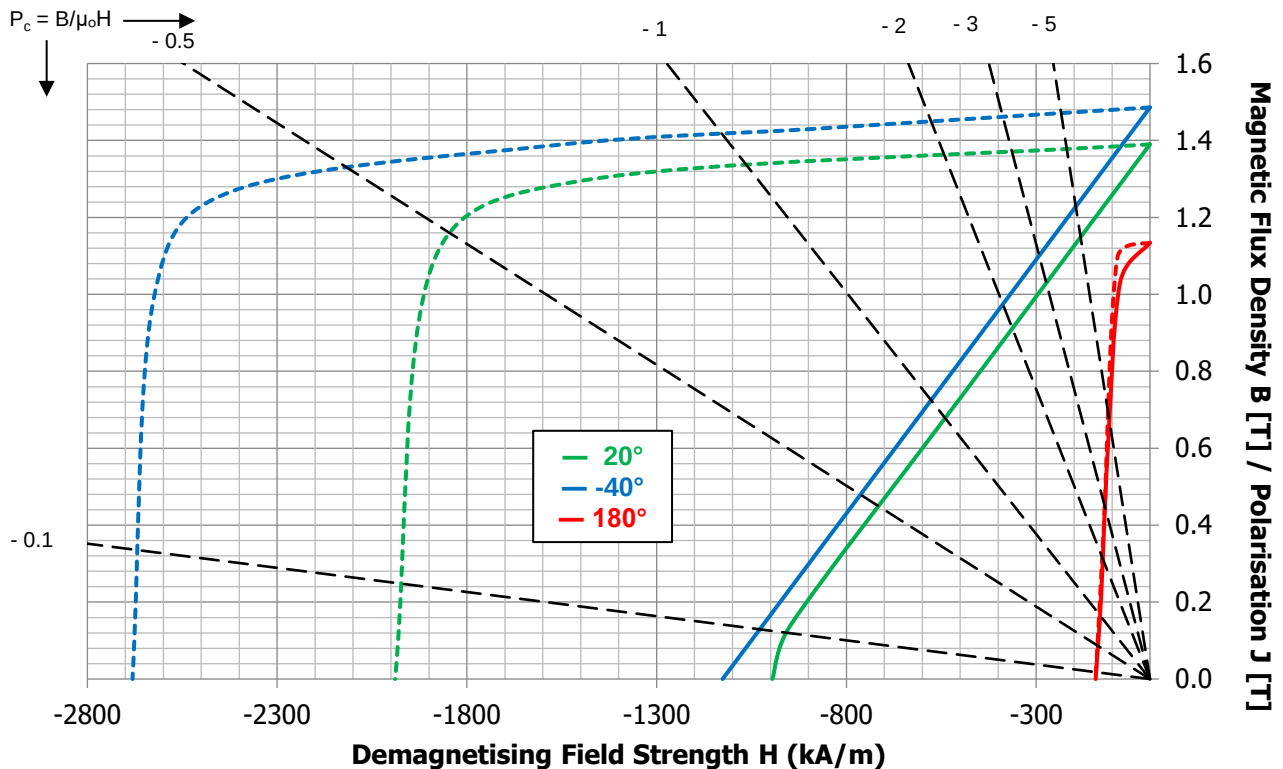

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C			
B_r	min	1.39	T
H_{cB}	min	995	kA/m
H_{cJ}	min	1989	kA/m
$(BH)_{ma}$	min	374	kJ/m ³
$\alpha(B_r)$	min typ	-0.115	%/°C
$\beta(H_{cJ})$	min typ	-0.58	%/°C
T_{max}		180	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation


EH- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N30EH	1080	812	2387	220	-0.11	-0.48	200
N33EH	1130	820	2387	246	-0.11	-0.48	200
N35EH	1170	836	2387	259	-0.11	-0.48	200
N38EH	1200	899	2387	281	-0.11	-0.48	200
N40EH	1250	915	2387	300	-0.11	-0.48	200
N42EH	1270	971	2387	318	-0.11	-0.48	200
N45EH	1320	971	2387	333	-0.11	-0.48	200

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N30EH – Anisotropic Sintered

Demagnetisation Curve N30EH

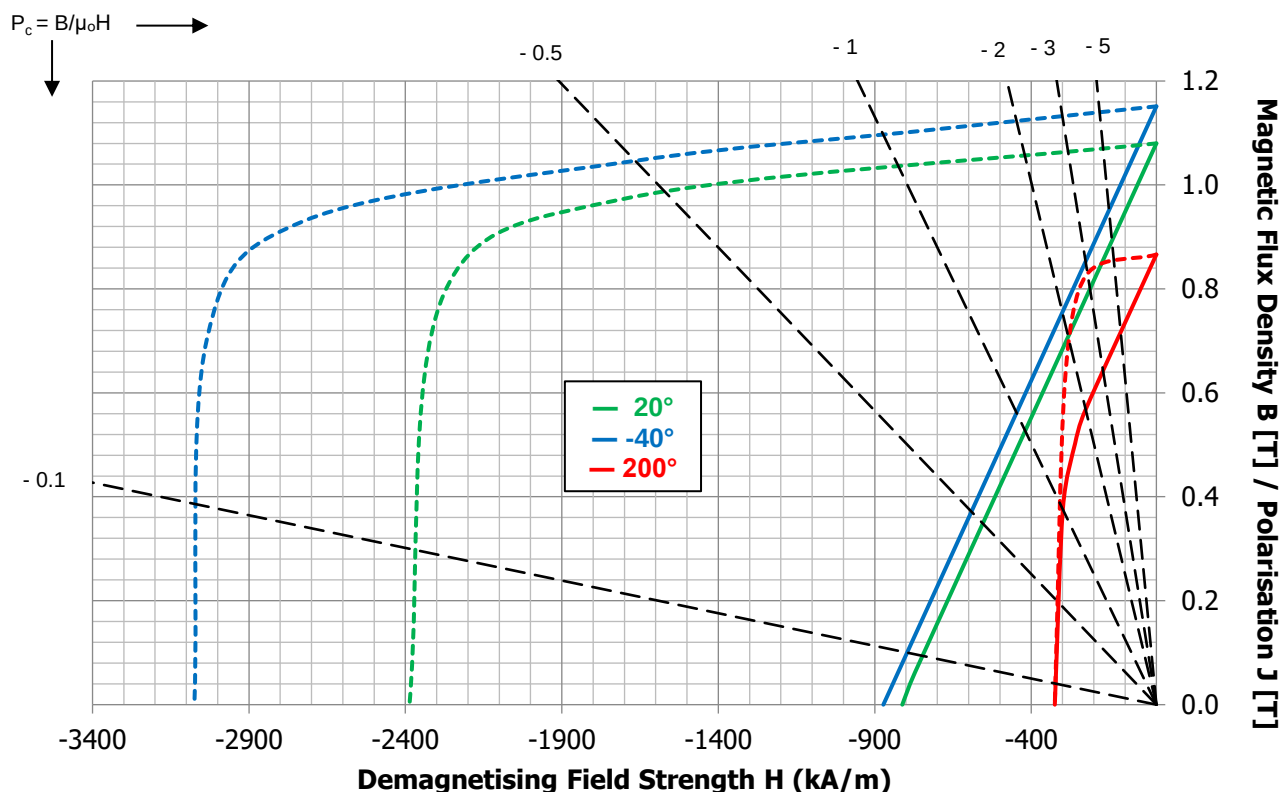

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.08	T	
H_{cB}	min	812	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	220	kJ/m^3	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N33EH – Anisotropic Sintered

Demagnetisation Curve N33EH

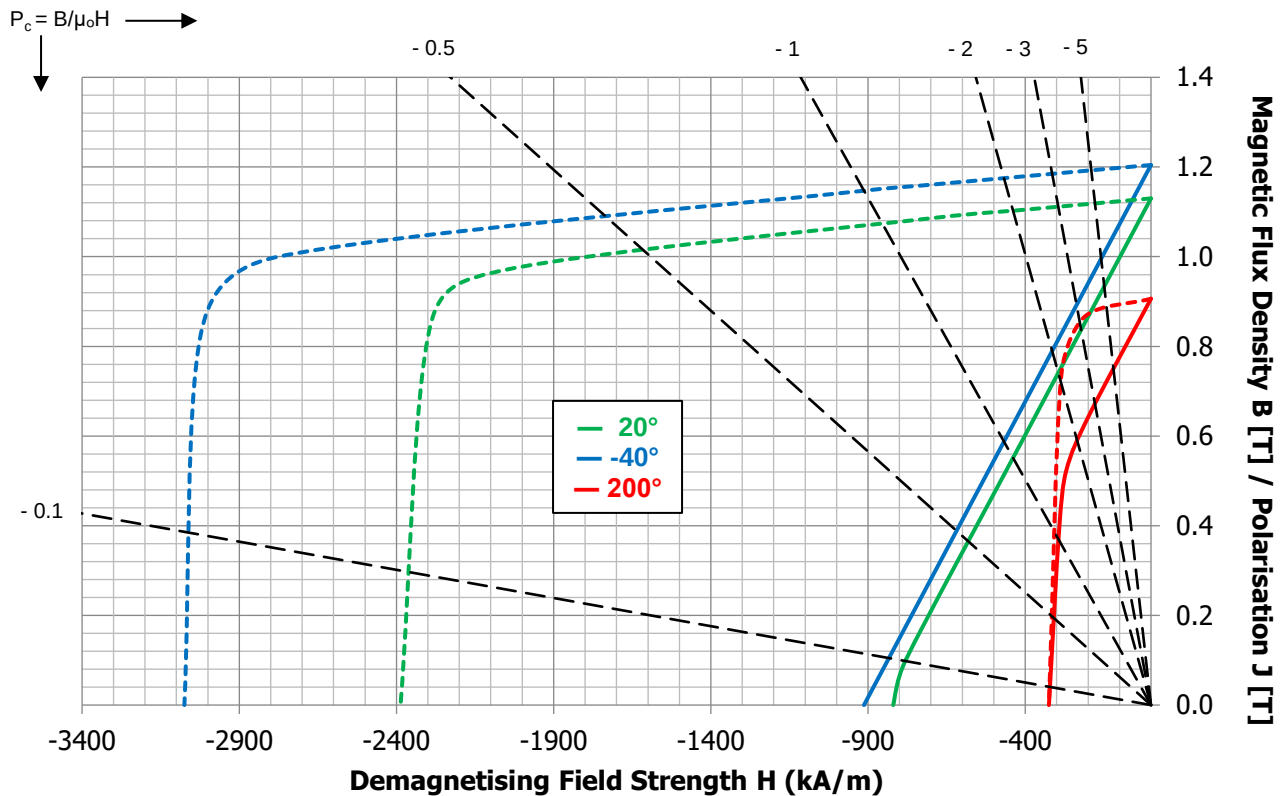

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.13	T
H_{cB}	min	820	kA/m
H_{cJ}	min	2387	kA/m
$(BH)_{ma}$	min	246	kJ/m ³
$\alpha(B_r)$	min typ	-0.11	%/°C
$\beta(H_{cJ})$	min typ	-0.48	%/°C
T_{max}		200	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N35EH – Anisotropic Sintered

Demagnetisation Curve N35EH

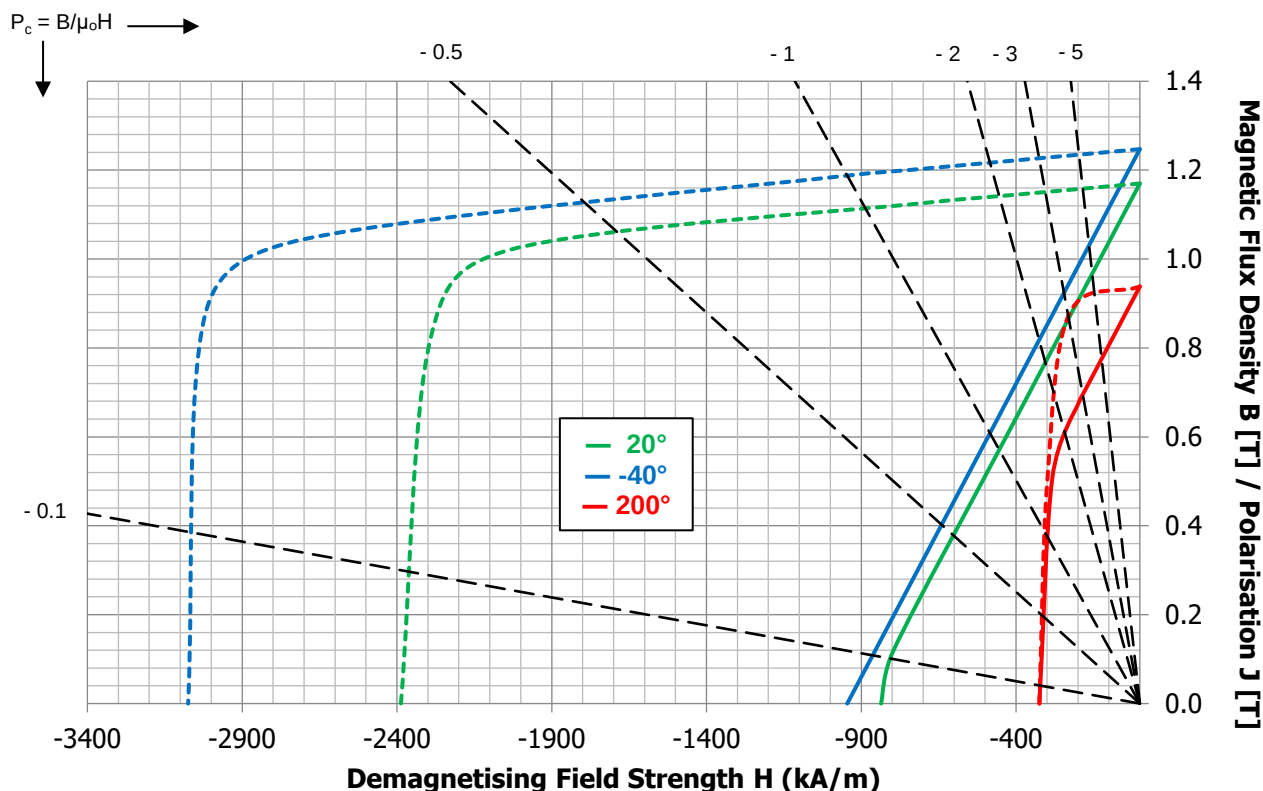

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.17	T	
H_{cB}	min	836	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	259	kJ/m ³	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38EH – Anisotropic Sintered

Demagnetisation Curve N38EH

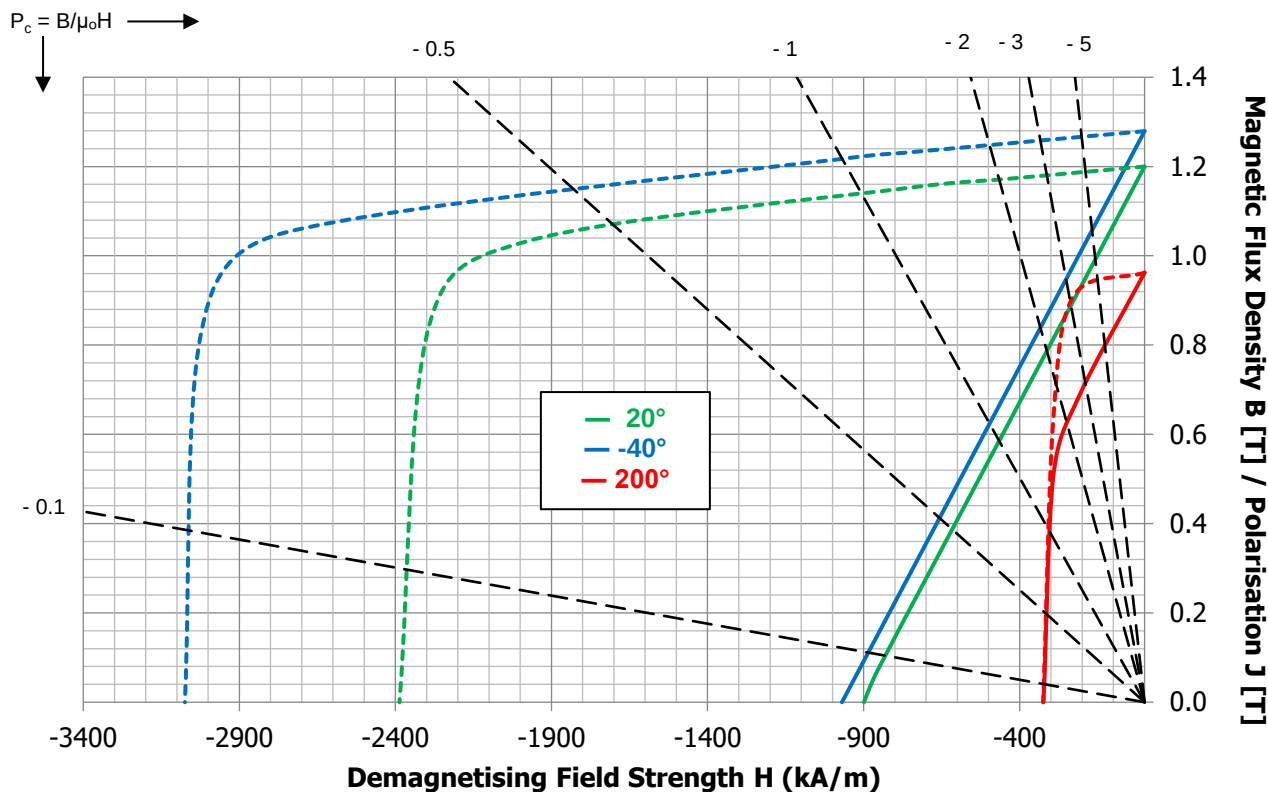

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.20	T	
H_{cB}	min	899	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	281	kJ/m^3	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40EH – Anisotropic Sintered

Demagnetisation Curve N40EH

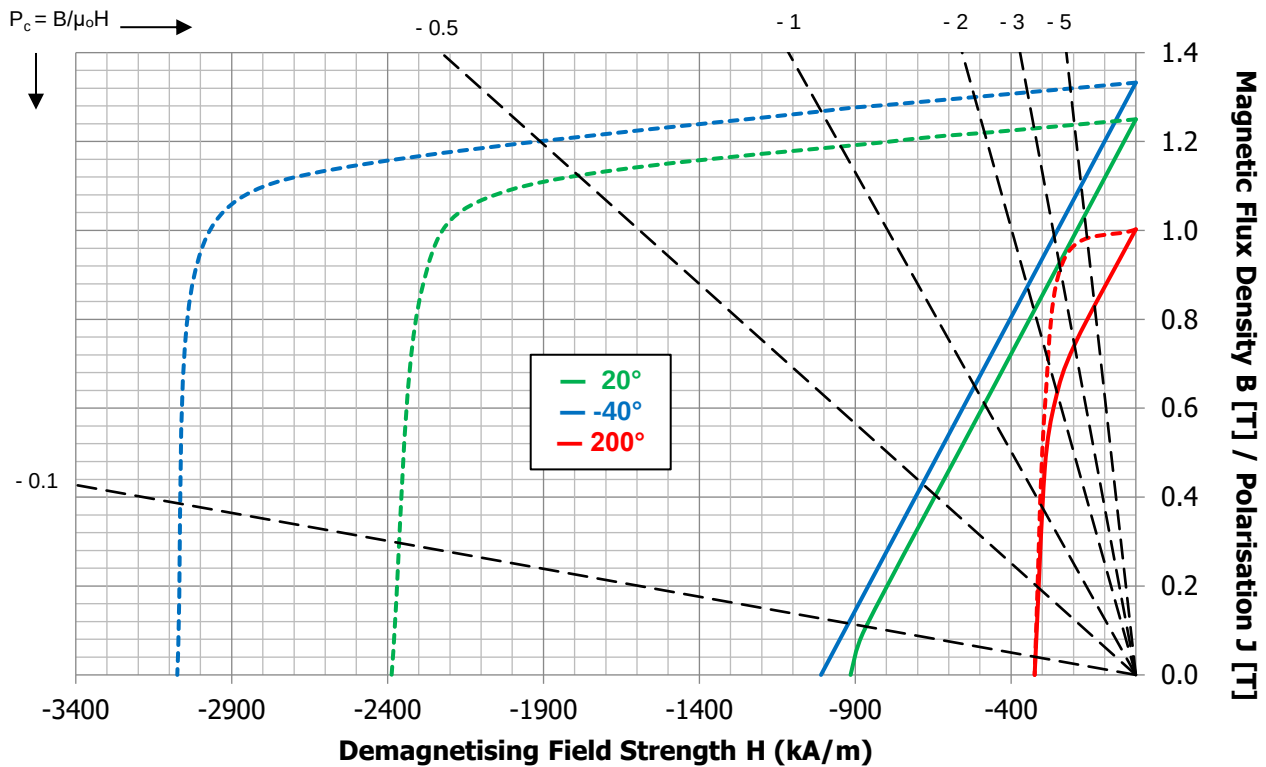

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.25	T	
H_{cB}	min	915	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	300	kJ/m^3	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42EH – Anisotropic Sintered

Demagnetisation Curve N42EH

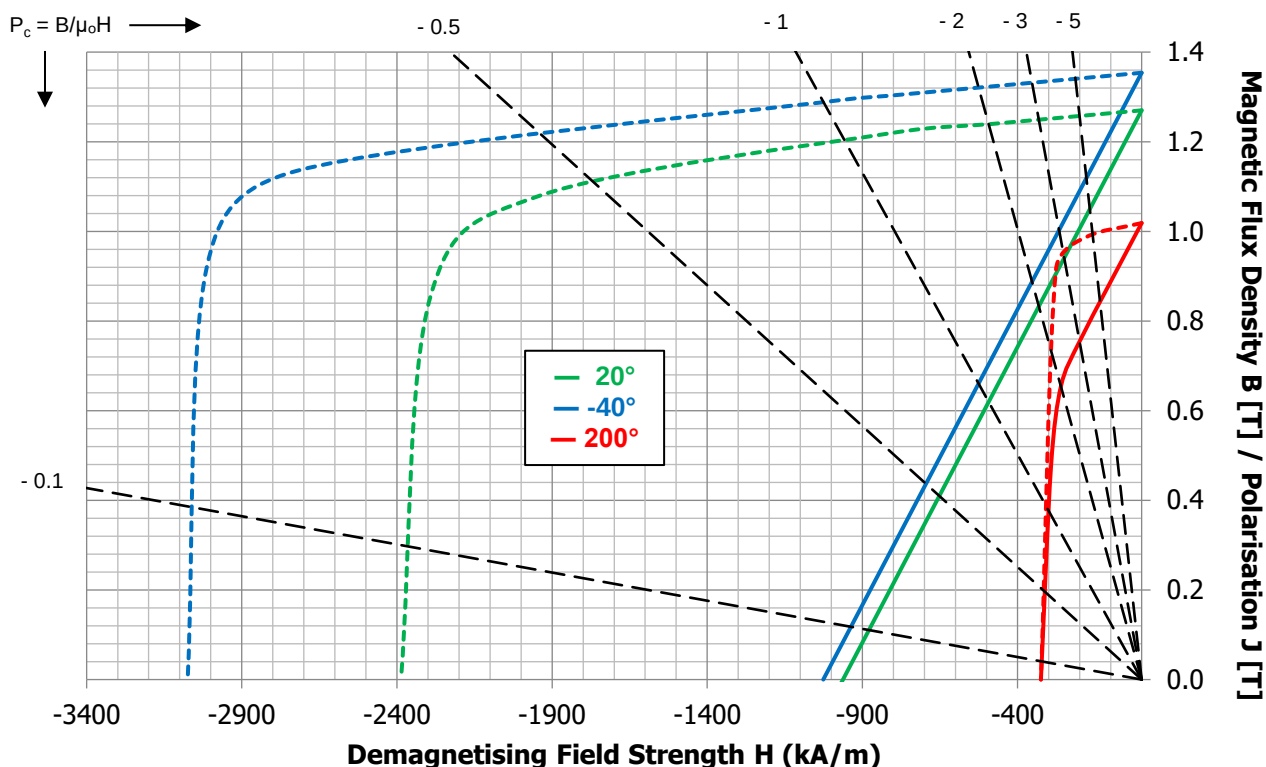

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.27	T	
H_{cB}	min	971	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	318	kJ/m^3	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N45EH – Anisotropic Sintered

Demagnetisation Curve N45EH

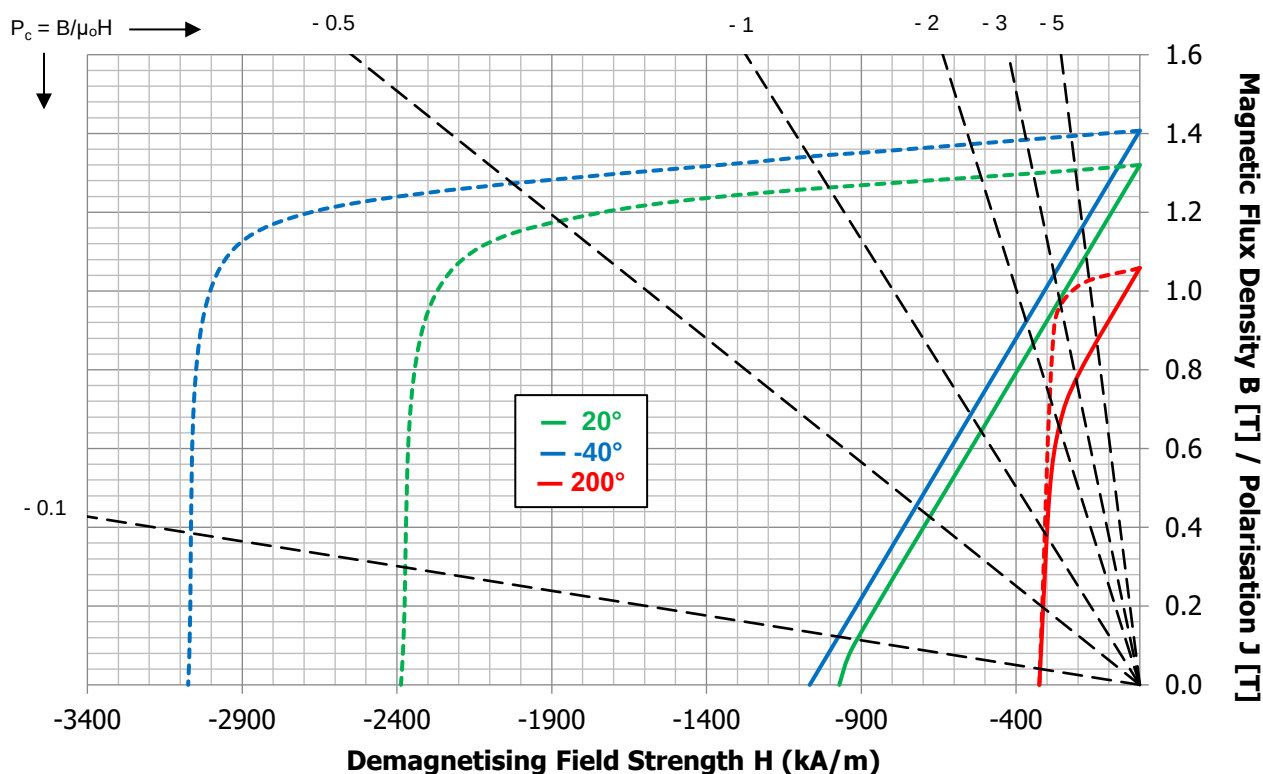

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C				
B_r	min	1.32	T	
H_{cB}	min	971	kA/m	
H_{cJ}	min	2387	kA/m	
$(BH)_{ma}$	min	333	kJ/m ³	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.48	%/°C	
T_{max}		200	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation


AH-Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	Minimum Value	Minimum Value	Minimum Value	Minimum Value	Minimum Typical Value	Minimum Typical Value	Maximum Value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N28AH	1040	780	2706	204	-0.11	-0.50	220
N30AH	1080	812	2706	220	-0.11	-0.50	220
N33AH	1140	812	2706	246	-0.11	-0.50	220
N35AH	1170	883	2706	259	-0.11	-0.50	220
N38AH	1200	923	2706	281	-0.11	-0.50	220
N40AH	1250	923	2706	300	-0.11	-0.50	220
N42AH	1280	923	2706	318	-0.11	-0.50	220

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N28AH – Anisotropic Sintered

Demagnetisation Curve N28AH

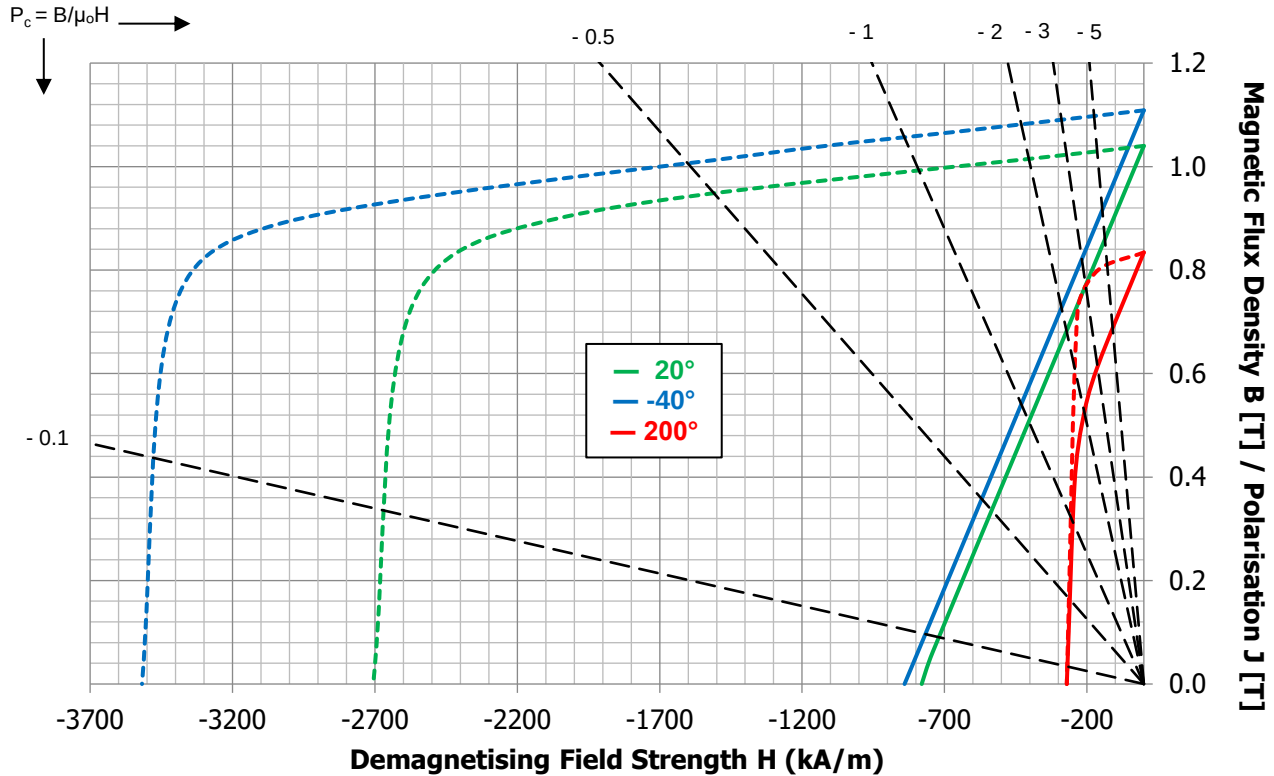

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.04	T	
H_{cB}	min	780	kA/m	
H_{cJ}	min	2706	kA/m	
$(BH)_{ma}$	min	204	kJ/m ³	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.50	%/°C	
T_{max}		220	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N30AH – Anisotropic Sintered

Demagnetisation Curve N30AH

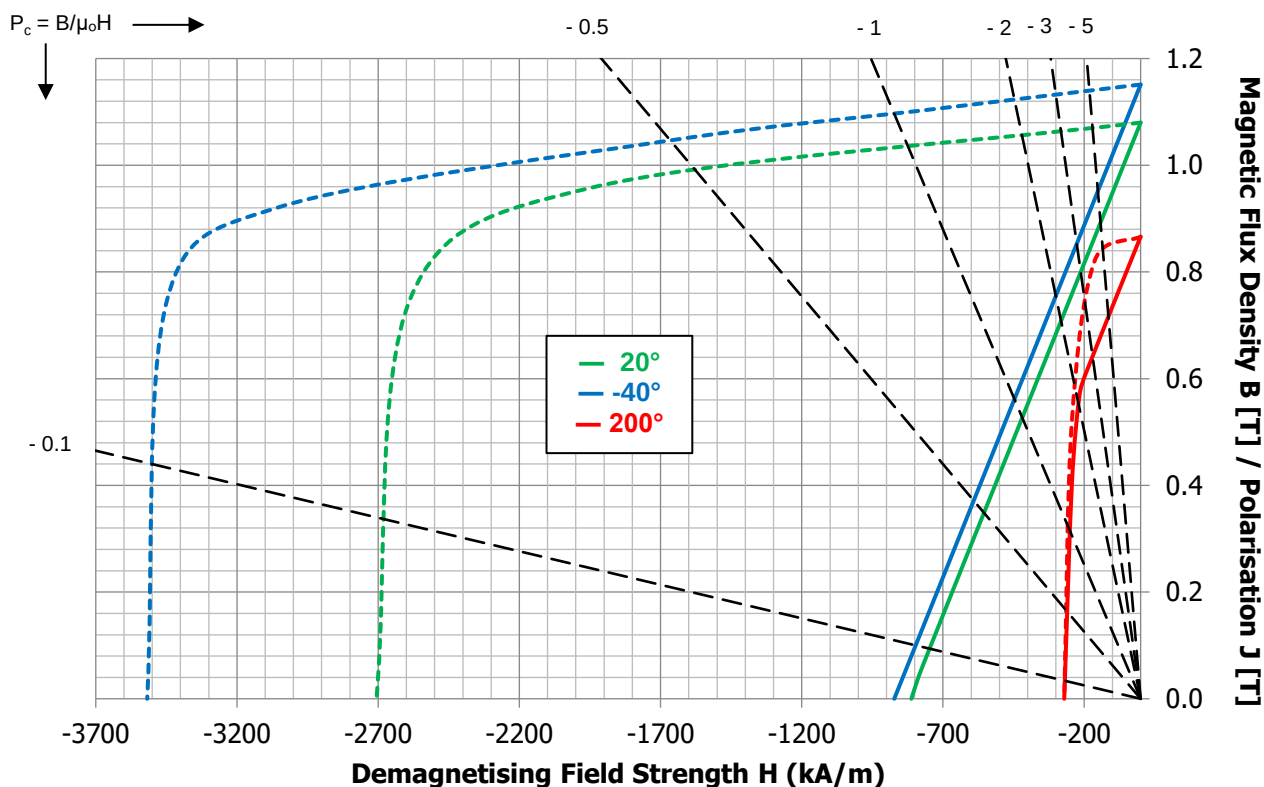

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmi grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.08	T
H_{cB}	min	812	kA/m
H_{cJ}	min	2706	kA/m
$(BH)_{ma}$	min	220	kJ/m ³
$\alpha(B_r)$	min typ	-0.11	%/°C
$\beta(H_{cJ})$	min typ	-0.50	%/°C
T_{max}		220	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N33AH – Anisotropic Sintered

Demagnetisation Curve N33AH

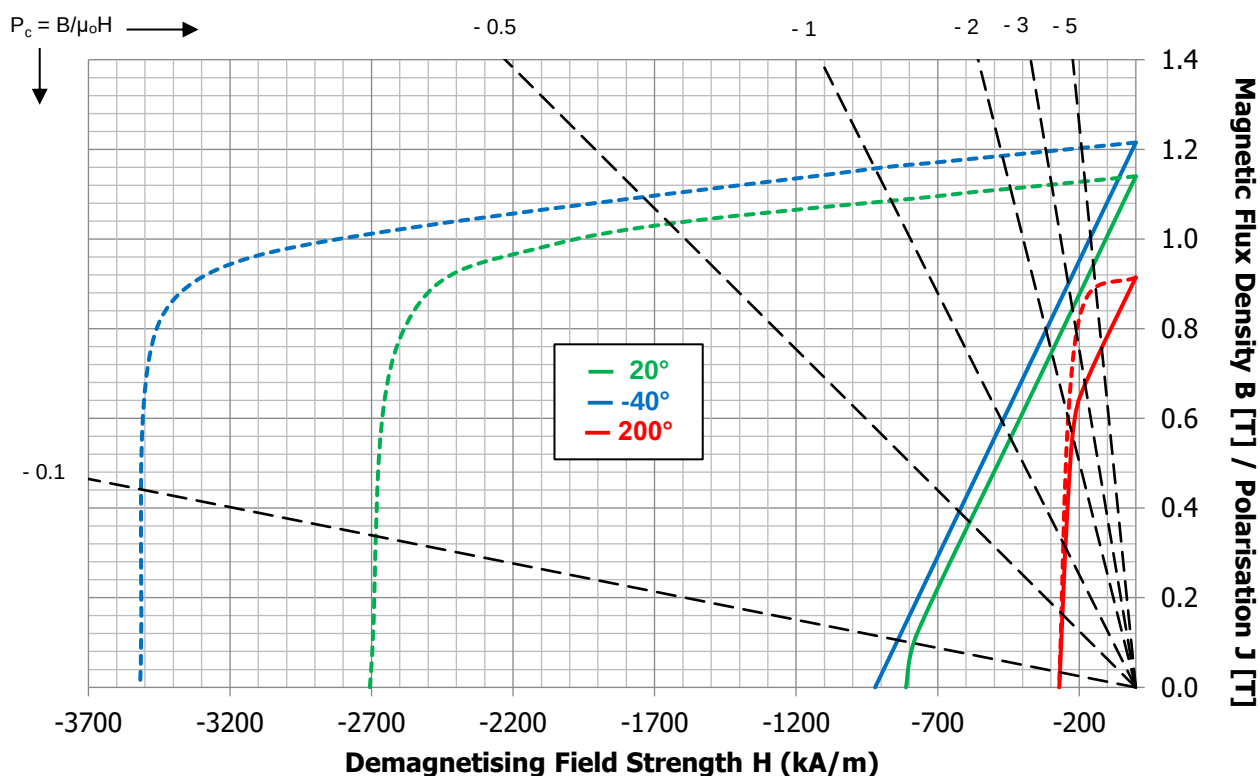

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.14	T
H_{cB}	min	812	kA/m
H_{cJ}	min	2706	kA/m
$(BH)_{ma}$	min	246	kJ/m ³
$\alpha(B_r)$	min typ	-0.11	%/°C
$\beta(H_{cJ})$	min typ	-0.50	%/°C
T_{max}		220	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N35AH – Anisotropic Sintered

Demagnetisation Curve N35AH

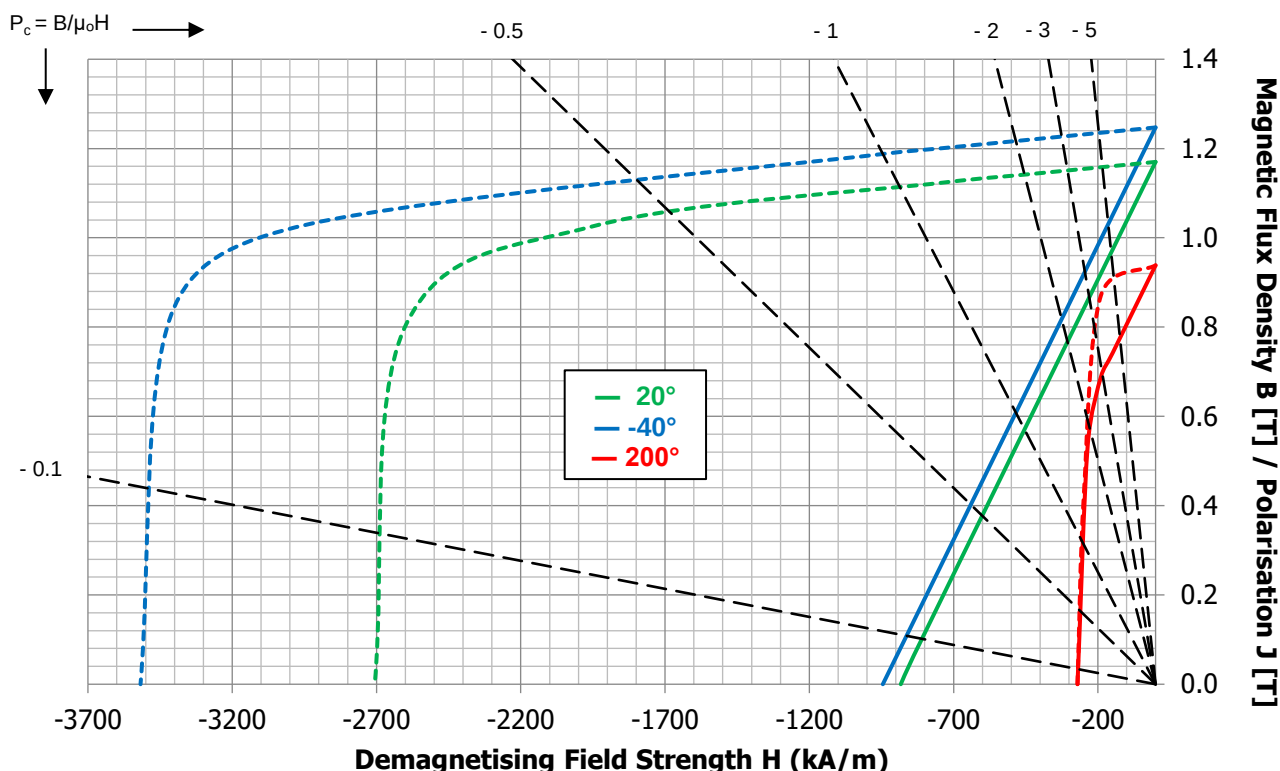

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.17	T	
H_{cB}	min	883	kA/m	
H_{cJ}	min	2706	kA/m	
$(BH)_{ma}$	min	259	kJ/m^3	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.50	%/°C	
T_{max}		220	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38AH – Anisotropic Sintered

Demagnetisation Curve N38AH

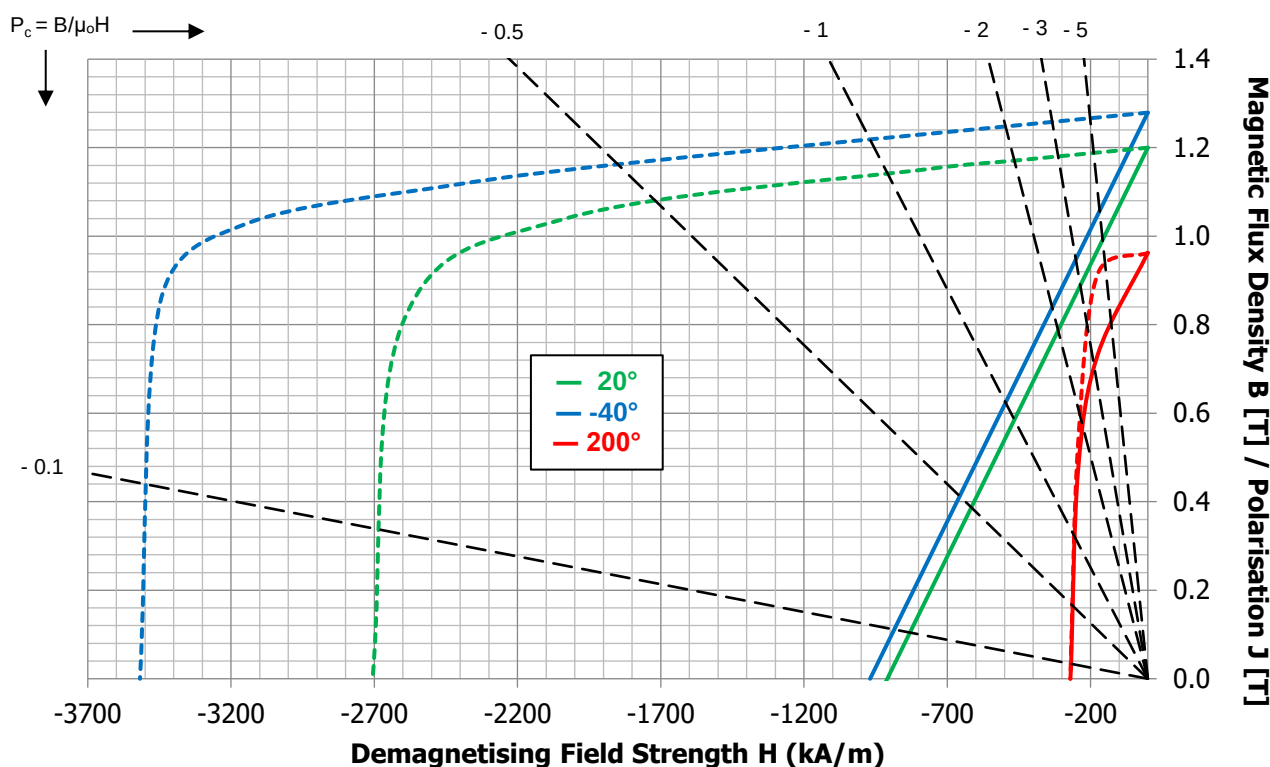

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmi grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.20	T
H_{cB}	min	923	kA/m
H_{cJ}	min	2706	kA/m
$(BH)_{ma}$	min	281	kJ/m ³
$\alpha(B_r)$	min typ	-0.11	%/°C
$\beta(H_{cJ})$	min typ	-0.50	%/°C
T_{max}		220	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N40AH – Anisotropic Sintered

Demagnetisation Curve N40AH

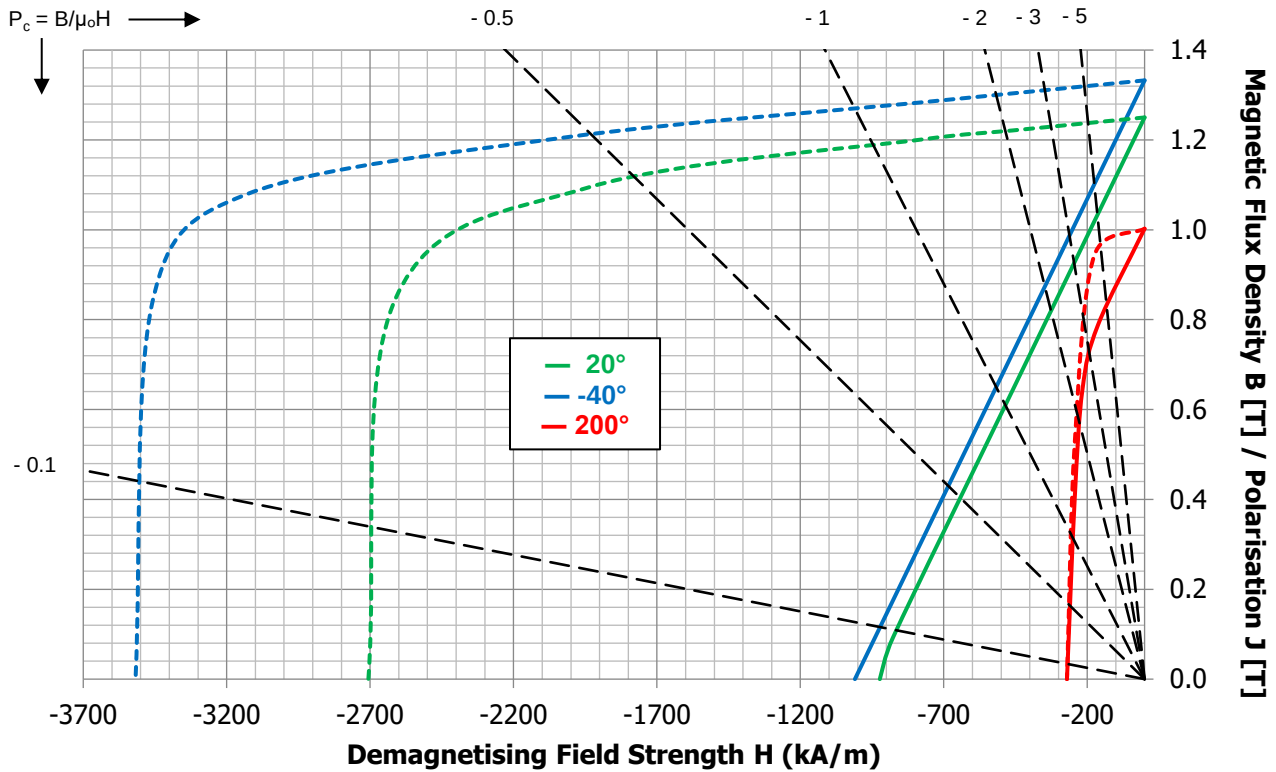

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.25	T
H_{cB}	min	923	kA/m
H_{cJ}	min	2706	kA/m
$(BH)_{ma}$	min	300	kJ/m^3
$\alpha(B_r)$	min typ	-0.11	%/°C
$\beta(H_{cJ})$	min typ	-0.50	%/°C
T_{max}		220	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m^3
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N42AH – Anisotropic Sintered

Demagnetisation Curve N42AH

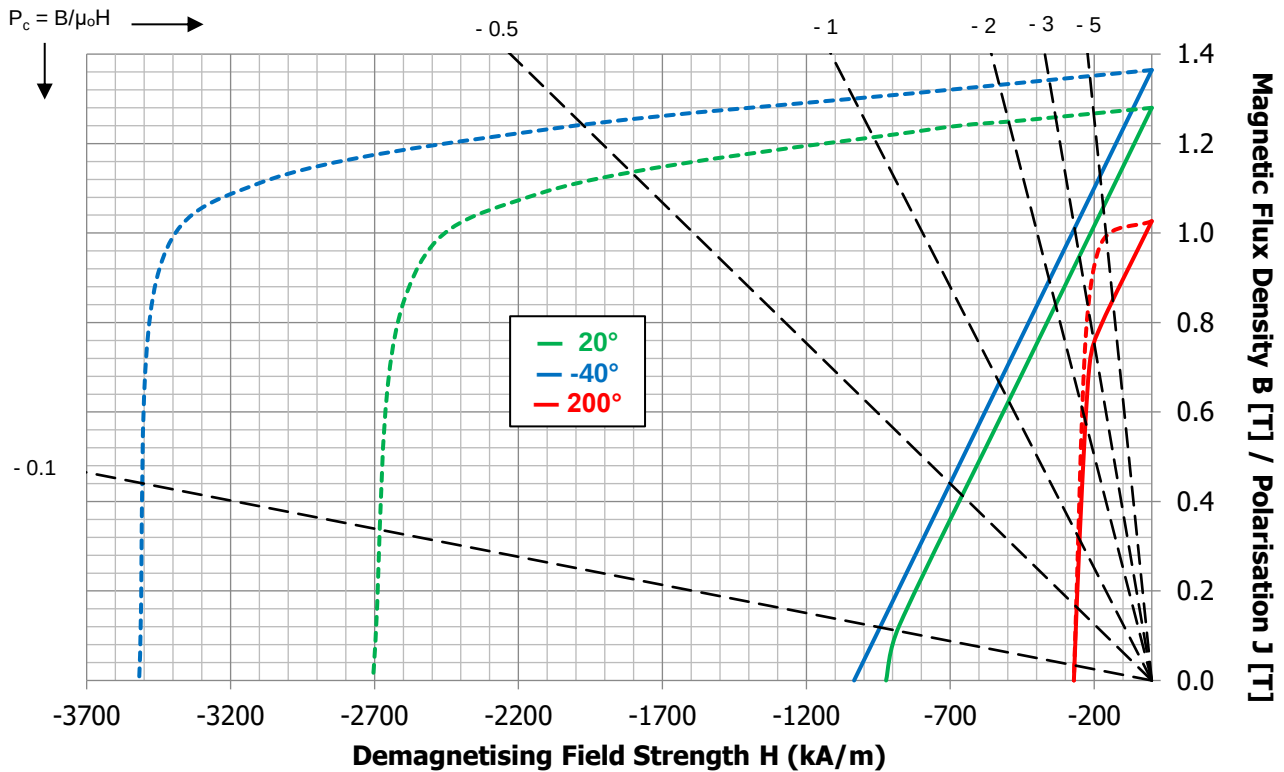

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C				
B_r	min	1.28	T	
H_{cB}	min	923	kA/m	
H_{cJ}	min	2706	kA/m	
$(BH)_{ma}$	min	318	kJ/m ³	
$\alpha(B_r)$	min typ	-0.11	%/°C	
$\beta(H_{cJ})$	min typ	-0.50	%/°C	
T_{max}		220	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m ³	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$	
Specific heat capacity	typ	350 - 550	J/(kg K)	
Thermal conductivity	typ	5 - 15	W/(m K)	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$	

* DOM = Direction Of Magnetisation


VH- Grades

Goudsmit Grade Code	Remanence B_r	Normal Coercivity H_{cB}	Intrinsic Coercivity H_{cJ}	Maximum Energy Product $(BH)_{max}$	Remanence Temperature Coefficient $\alpha(B_r)$	Intrinsic Coercivity Temperature Coefficient $\beta(H_{cJ})$	Maximum Operating Temperature T_{max}
	minimum value	minimum value	minimum value	minimum value	minimum typical value	minimum typical value	maximum value
	[mT]	[kA/m]	[kA/m]	[kJ/m ³]	[%/°C]	[%/°C]	[°C]
N28VH	1020	780	3104	207	-0.10	-0.393	250
N30VH	1080	812	3104	223	-0.10	-0.393	250
N33VH	1130	812	3104	247	-0.10	-0.393	250
N35VH	1170	883	3104	263	-0.10	-0.393	250
N38VH	1220	923	3104	287	-0.10	-0.393	250

These are the most common grades. Please contact us for questions on other grades available at Goudsmit.

Technical Datasheet: Neodymium N28VH – Anisotropic Sintered

Demagnetisation Curve N28VH

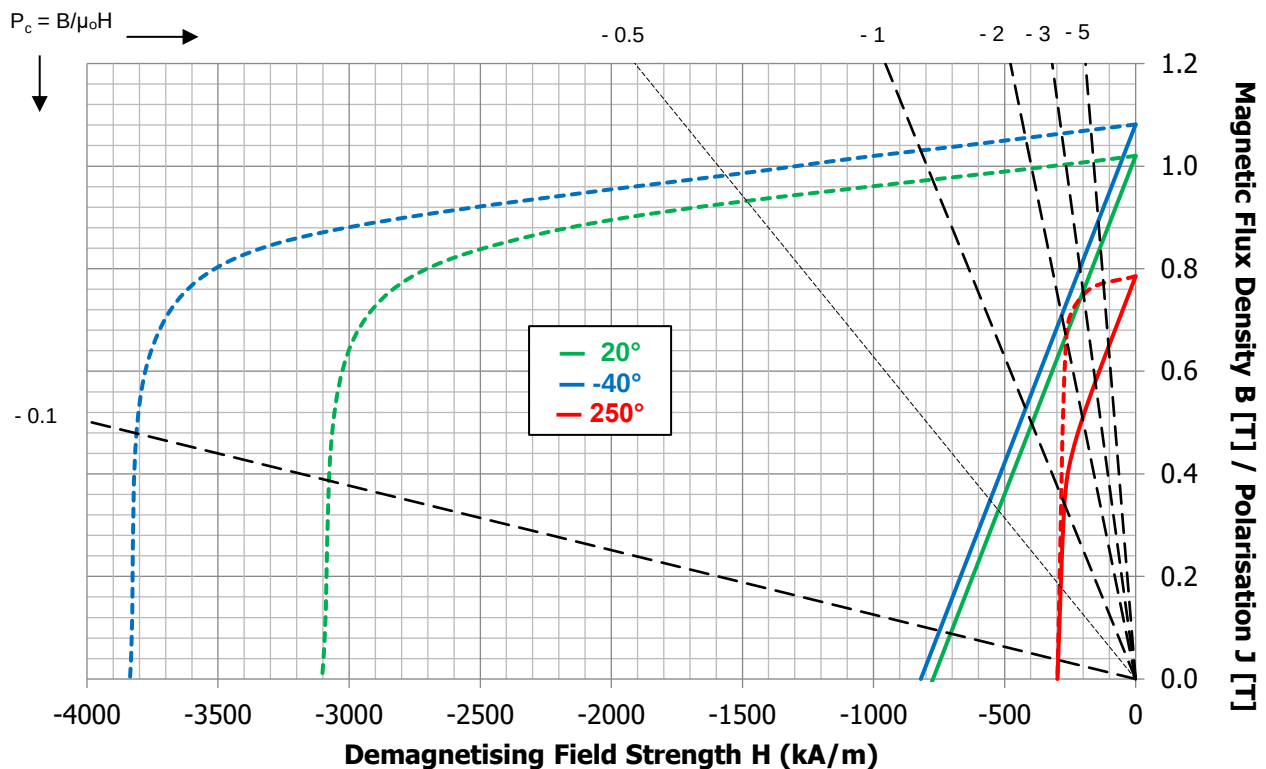

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmi grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.02	T
H_{cB}	min	780	kA/m
H_{cJ}	min	3104	kA/m
$(BH)_{ma}$	min	207	kJ/m ³
$\alpha(B_r)$	min typ	-0.10	%/°C
$\beta(H_{cJ})$	min typ	-0.393	%/°C
T_{max}		250	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega$ m
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	10 ⁻⁶ /K

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N30VH – Anisotropic Sintered

Demagnetisation Curve N30VH

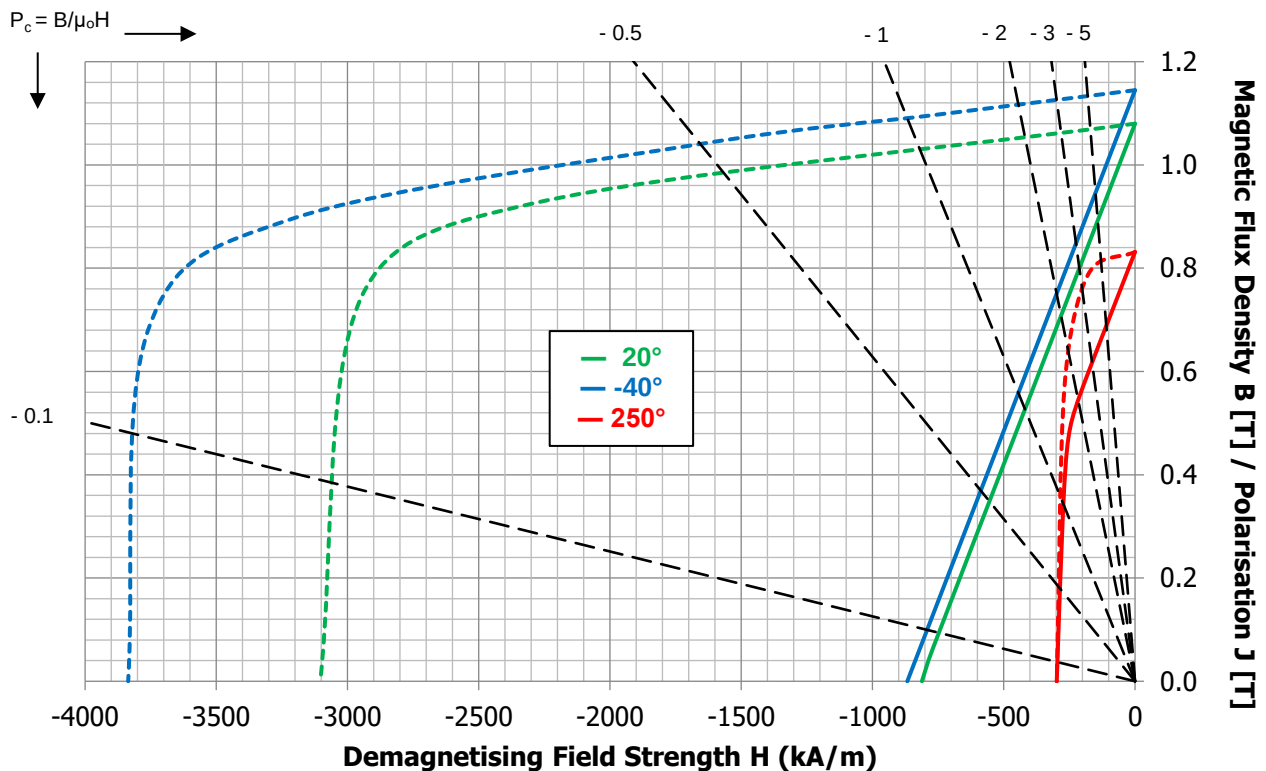

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.08	T
H_{cB}	min	812	kA/m
H_{cJ}	min	3104	kA/m
$(BH)_{ma}$	min	223	kJ/m ³
$\alpha(B_r)$	min typ	-0.10	%/°C
$\beta(H_{cJ})$	min typ	-0.393	%/°C
T_{max}		250	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	10 ⁻⁶ /K
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	10 ⁻⁶ /K

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N33VH – Anisotropic Sintered

Demagnetisation Curve N33VH

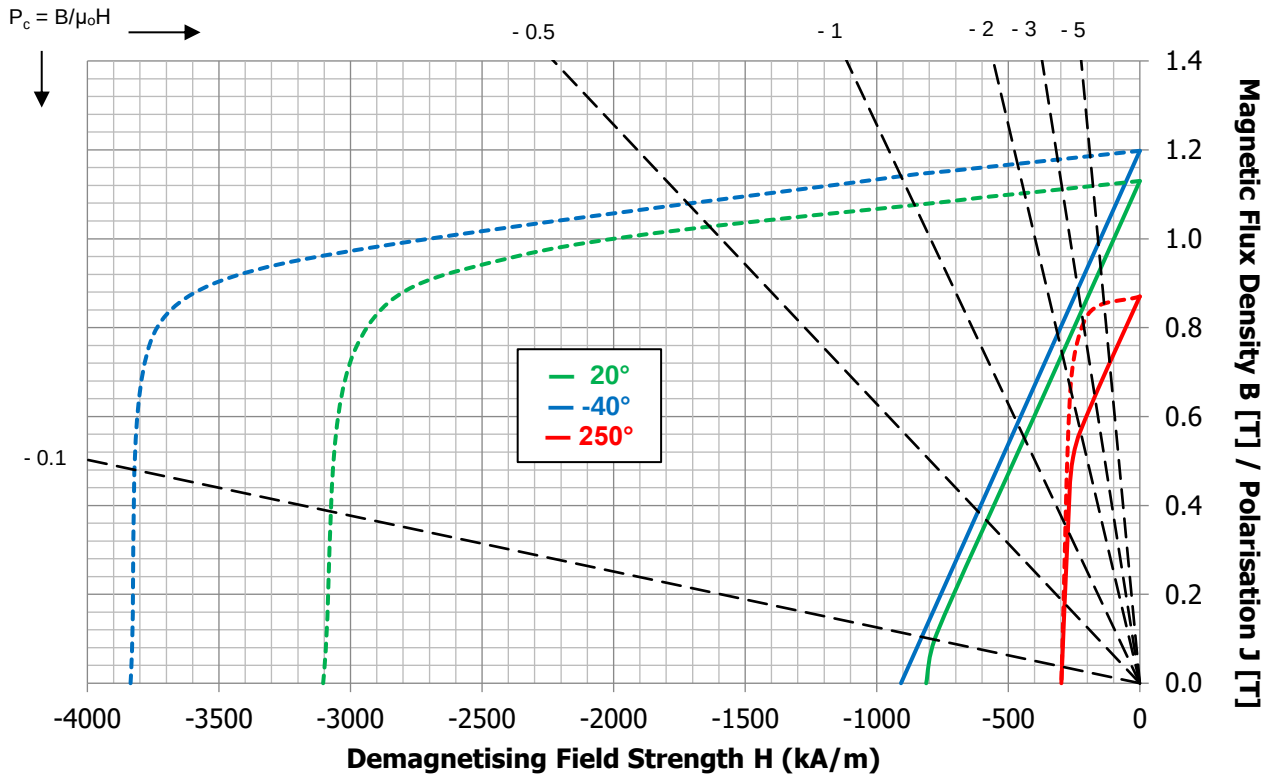

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmiit grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C				
B_r	min	1.13	T	
H_{cB}	min	812	kA/m	
H_{cJ}	min	3104	kA/m	
$(BH)_{ma}$	min	247	kJ/m^3	
$\alpha(B_r)$	min typ	-0.10	%/°C	
$\beta(H_{cJ})$	min typ	-0.393	%/°C	
T_{max}		250	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N35VH – Anisotropic Sintered

Demagnetisation Curve N35VH

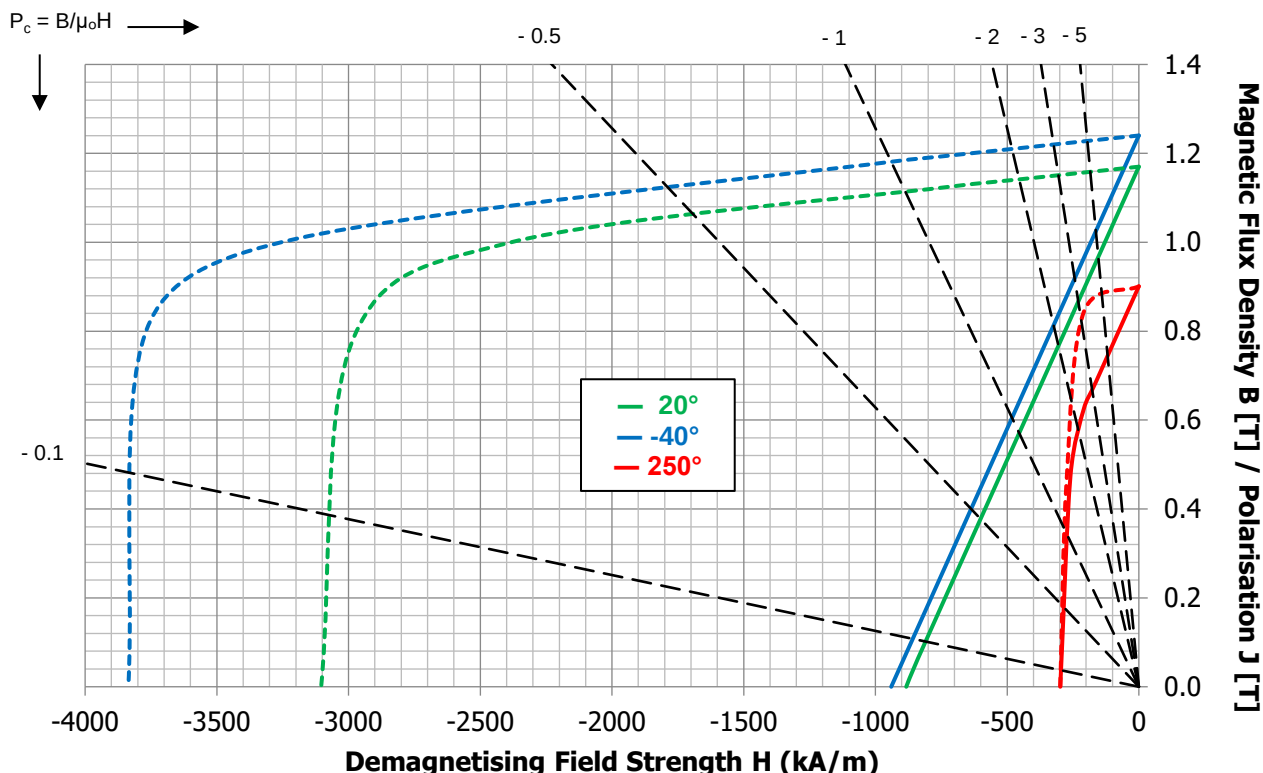

Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmut grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.


Magnetic Properties @20°C			
B_r	min	1.17	T
H_{cB}	min	883	kA/m
H_{cJ}	min	3104	kA/m
$(BH)_{ma}$	min	263	kJ/m ³
$\alpha(B_r)$	min typ	-0.10	%/°C
$\beta(H_{cJ})$	min typ	-0.393	%/°C
T_{max}		250	°C
μ_r	typ	1.05	-

Physical & Mechanical Properties @20°C			
Density	typ	7400 - 7800	kg/m ³
Vickers Hardness	typ	500 - 700	HV
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa
Flexural / bending strength	typ	100 - 400	MPa
Compressive strength	typ	600 - 1100	MPa
Tensile strength / ultimate strength	typ	74 - 90	MPa
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega m$
Specific heat capacity	typ	350 - 550	J/(kg K)
Thermal conductivity	typ	5 - 15	W/(m K)
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/K$
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/K$

* DOM = Direction Of Magnetisation

Technical Datasheet: Neodymium N38VH – Anisotropic Sintered

Demagnetisation Curve N38VH

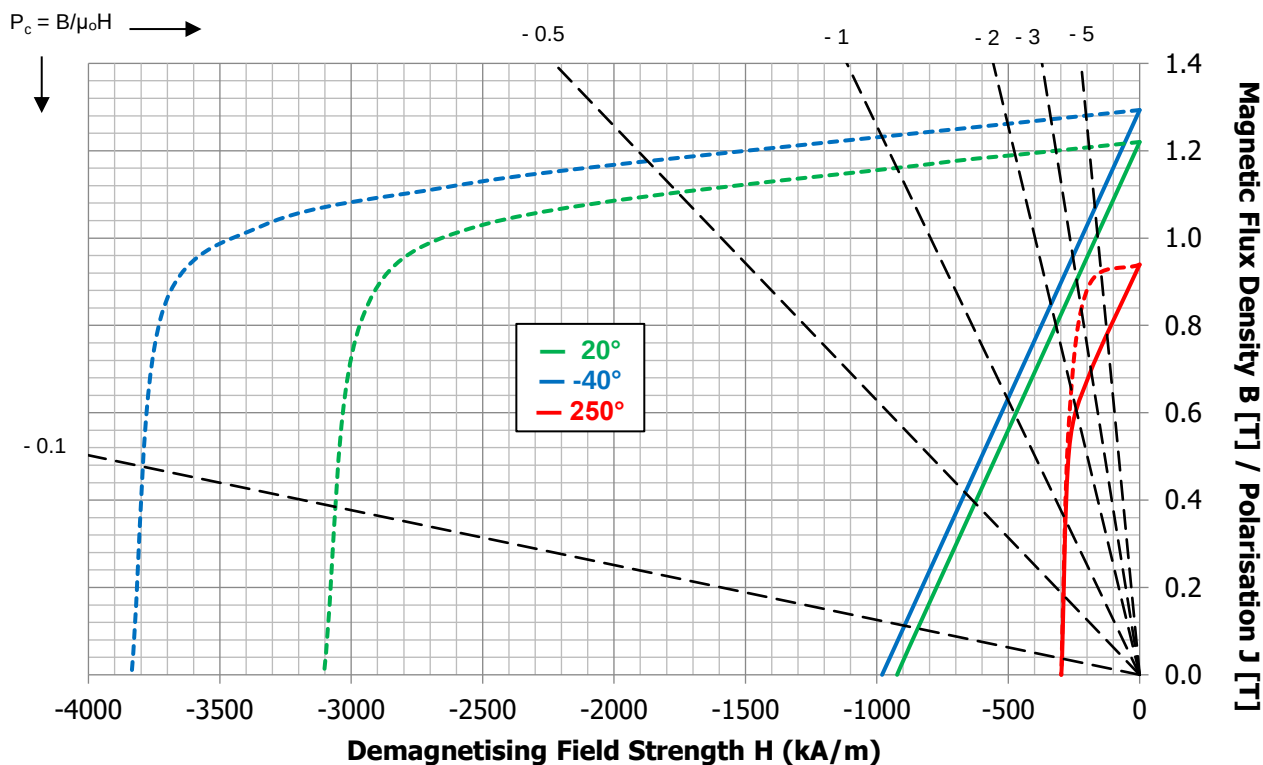


Solid lines represent magnetic flux densities. Dashed lines represent polarisations. The curves here are estimates obtained from data available from the current Goudsmi grade system (Available on the website. See also the magnetic properties below). On request, actual measurements of demagnetisation curves can be obtained. For that, contact us on the address below.

Magnetic Properties @20°C				
B_r	min	1.22	T	
H_{cB}	min	923	kA/m	
H_{cJ}	min	3104	kA/m	
$(BH)_{ma}$	min	287	kJ/m^3	
$\alpha(B_r)$	min typ	-0.10	%/°C	
$\beta(H_{cJ})$	min typ	-0.393	%/°C	
T_{max}		250	°C	
μ_r	typ	1.05	-	

Physical & Mechanical Properties @20°C				
Density	typ	7400 - 7800	kg/m^3	
Vickers Hardness	typ	500 - 700	HV	
Modulus of Elasticity / Young's modulus	typ	140 - 200	GPa	
Flexural / bending strength	typ	100 - 400	MPa	
Compressive strength	typ	600 - 1100	MPa	
Tensile strength / ultimate strength	typ	74 - 90	MPa	
Electrical resistivity	typ	1.1 - 1.7	$\mu\Omega\text{m}$	
Specific heat capacity	typ	350 - 550	$\text{J}/(\text{kg K})$	
Thermal conductivity	typ	5 - 15	$\text{W}/(\text{m K})$	
Coefficient of linear thermal expansion, DOM*	typ	3 - 9	$10^{-6}/\text{K}$	
Coefficient of linear thermal expansion, $\perp$ DOM*	typ	-3 - 0	$10^{-6}/\text{K}$	

* DOM = Direction Of Magnetisation

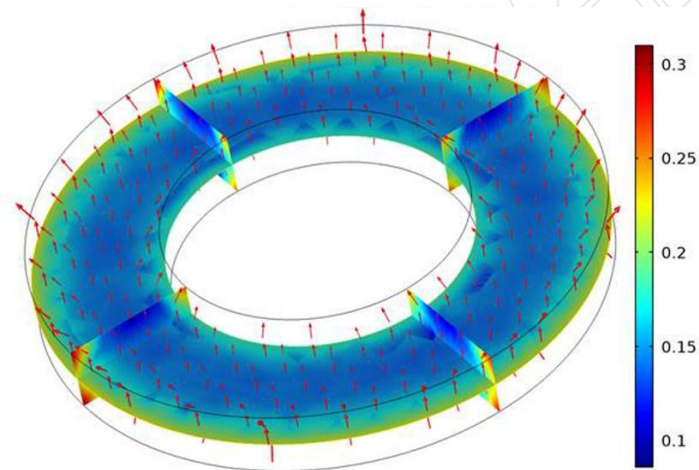

Goudsmit offers a wide range of services with regards to the design and selection of the appropriate magnet for your specific application. For instance, we apply magnet calculations and FEM simulations to quickly identify the best magnet for your product.

The possibilities with magnet technology are endless, which is why it can quickly become confusing. Goudsmit has more than 60 years of experience in the world of magnetism and is happy to help you with advice and a range of services:

- FEM simulation & magnet calculations: gain quick insight into the operation of your design.
- Prototyping & samples: tangible magnet technology based on your requirements.
- Engineering: development of magnet assemblies and components.
- Quality control: critical properties tested and validated in our own measurement lab.
- Stock management service: delivery of your magnets on demand through our modern warehouse.

You can choose whatever form of support you want. This guarantees you the right magnet for your specific application.